

ADA031501

SSC-280

A SURVEY OF FASTENING
TECHNIQUES FOR SHIPBUILDING

BEST AVAILABLE COPY

This document has been approved
for public release and sale, its
distribution is unlimited.

SHIP STRUCTURE COMMITTEE

1973

SHIP STRUCTURE COMMITTEE

AN INTERAGENCY ADVISORY
COMMITTEE DEDICATED TO IMPROVING
THE STRUCTURE OF SHIPS

MEMBER AGENCIES

U.S. Coast Guard
U.S. Navy
U.S. Army
U.S. Air Force
U.S. Marine Corps
U.S. Atomic Energy Commission

ADDRESS CORRESPONDENCE TO


Secretary
Ship Structure Committee
U.S. Coast Guard Headquarters
Washington, D.C. 20390
SR-207

U.S. GOVERNMENT PRINTING OFFICE

The Ship Structure Committee recognized, as a result of studies sponsored by the use of aluminum and fiberglass in ship construction, that a variety of joining techniques must be considered. Many mechanical and adhesive techniques have been employed in other industries. Some of these methods might have a marine application and provide an alternative to welding.

This report describes the study that was made of these alternative fastening techniques. It is not an endorsement by the Ship Structure Committee of any concept or process. Many of these concepts would require a more penetrating examination before they could be adopted. However, much of the material has not been readily available to the marine community. In some cases this information might prove useful especially in weight critical applications.

This report is published to assist in developing cost effective and safe fastening techniques. Comments on this report and suggestions for areas of structural research would be most welcome.


W. M. BENNETT

Rear Admiral, U. S. Coast Guard
Chairman, Ship Structure Committee

DISCLAIMER NOTICE

**THIS DOCUMENT IS BEST QUALITY
PRACTICABLE. THE COPY FURNISHED
TO DDC CONTAINED A SIGNIFICANT
NUMBER OF PAGES WHICH DO NOT
REPRODUCE LEGIBLY.**

SSC-260
Final Report
on
Project SR-207, "Fastening Techniques Evaluation"

A SURVEY OF FASTENING
TECHNIQUES FOR SHIPBUILDING

by
N. Yutani, and
T. L. Reynolds
Boeing Commercial Airplane Company

CODE-23

under
Department of the Navy
Naval Sea Systems Command
Contract No. N00024-73-C-5077

*This document has been approved for public release
and sale; its distribution is unlimited.*

U. S. Coast Guard Headquarters
Washington, D.C.
1976

ABSTRACT

This report is aimed at defining fastening processes and techniques that are not widely used in ship construction today in terms of their applicability and potential for improving cost, construction, reliability, and maintenance of hull structures and attachments. The study includes similar and dissimilar metal-to-metal and metal-to-nonmetal joints, a generic fastener matrix of typical fasteners, fastener installation equipment and processes, proposed applications of explosion-bonded materials, and cost comparisons of various fabrication techniques. Fusion welding, diffusion bonding, friction welding, and adhesive bonding are discussed. Several fastener standards and vendor proprietary fasteners are included as figures. Extractions from Boeing Design Manual sections on mechanical fastening and adhesive bonding are included as reference attachments. Fastening systems and techniques that merit further study or verification are identified.

CONTENTS

	<u>PAGE</u>
I. INTRODUCTION	1
Background	1
Scope	2
II. INVESTIGATION AND ANALYSIS	4
Identification of Problem Areas for Study.	4
General Fastener Matrix.	4
Mechanical Fastening and Hole Preparation.	9
Explosion Bonding.	31
Adhesive Bonding	46
Welding.	48
Mechanical Bonding	51
III. CONCLUSIONS AND RECOMMENDATIONS.	51
IV. RECOMMENDED AREAS FOR FURTHER STUDY.	53
APPENDICES	54
A Piping Systems	55
B Water Systems.	57
C Oil and Air Systems.	59
D Bonding Facilities Equipment	61
E In-Place Tube Welding.	63
F Electrical Systems and Their Attachments	67
G Optical Laser Applications	69
H Boeing Design Manual, Section 17, Fasteners.	72
I Boeing Design Manual, Section 26, Adhesive Bonding	114
LIST OF REFERENCES	133
ADDITIONAL SOURCES OF INFORMATION.	134
ACKNOWLEDGEMENTS	135

LIST OF FIGURES

<u>FIGURE NO.</u>	<u>PAGE</u>
1. Example Machine Bolt Standard	10
2. Example Blind Rivet Standard.	12
3. Example Taper Shank Bolt Standard	13
4. Omark-Winslow HS-2 Spacematic Drill	14
5. Squeeze Yoke Rivebolt Installation on 747 Spar.	14
6. Hi-Shear Bus Hi-Lok Fastener Standard	16
7. Hi-Shear Six-Wing Fastener Standard	18
8. Wing Splice Joint	22
9. Hand Riveting 727 Spar.	22
10. Riveting Stringers to 747 Upper Wing Panel on Gemcor Drivematic Riveting Machines.	22
11. Omark-Winslow Track Drill	24
12. Boeing-Developed Electromagnetic Riveter.	24
13. Boeing Electromagnetic Riveter and Omark-Winslow Track Drill.	28
14. Boeing Cold Expansion Sleeve System	28
15. Air/Hydraulic Puller for Cold Working Holes	28
16. Schematic of Explosion Bonding Process Illustrating Jetting Phenomenon Which Removes Oxides and Foreign Matter From Surfaces Being Joined	32
17. Corrosion Test Results.	36
18. Deckhouse Mockup--Aluminum/Steel Transition Joints.	41
19. Proposed Bimetallic Applications.	44
20. Typical Chemical Processing Line.	60
21. Typical Spray Booth for Applying Adhesive Primer.	60
22. Typical Oven For Precuring Adhesive Primer.	60
23. Clean Room For Assembly of Parts to be Bonded	60
24. Aluminum Honeycomb Core Machining Equipment	62
25. Ultrasonic Nondestructive Testing Equipment	62
26. Typical Commercial Inplace GTA Tube Welding Power Supply/ Programmer and Weld Head.	64
27. Typical Commercial Inplace GTA Tube Welding Head With Auxiliary Bridge Tool	64
28. Clearance Envelope for Typical GTA Pipe Welding Crawler Head.	64
29. Auxiliary Bridge Tool	64
30. Tubing Weld Joint Configurations for GTA Tube Welder.	65
31. Typical Commercial Miniature GTA Tube Welding Crawler Unit With AVC, Torch Oscillation, and Wire Feeder.	66
32. Typical GTA Tube Welding Head	66
33. Typical MCT Cable & Tube Assemblies	68
34. Installation of Multicable Transit Frame	68
35. Flat Cable Assembly Compared to Round Wire Bundle	70
36. Flat Cable to Round Wire Transition	70
37. Flat Cable/Round Wire Junction Box	70

LIST OF TABLES

<u>TABLE NO.</u>		<u>PAGE</u>
1.	Alternate Applications Table	5
2.	Generic Fastener and Applications Matrix	6
3.	Blind Nut Selection Chart--Countersunk Head Type	19
4.	Blind Nut Selection Chart--Protruding Head Type	20
5.	Voi-Shan Visu-Lok Blind Fastener	21
6.	Interference Profiles--Hand Driven--EMR	25
7.	EMR Technical Information--Boeing 747 Production System	26
8.	Delron Selector Chart--Honeycomb and Sandwich Panel Fasteners	30
9.	Metals That Have Been Explosively Bonded to Themselves	32
10.	Dissimilar Metal Combinations That Have Been Explosively Bonded	33
11.	Corrosion Testing of Explosion-Bonded Transition Joints	36
12.	Mechanical Testing of Explosion Bonded Transition Joints	38
13.	Fatigue Testing Explosion-Bonded Transition Joints and Mechanical Connections	39
14.	Comparative Maintenance and Repair Associated With Mechanical Fastening Versus Detastrip for Attachment of Aluminum Deck Houses to Steel Decks	40
15.	Aluminum Deck House Fabrication Cost Analysis	42
16.	NAA Dissimilar-Metal Bonding Processes	50
17.	Cost Comparison for Aluminum Alloy and Stainless Steel Valves	56
18.	Material Costs--Bilge System in Ballast Tanks (U.S. Dollars)	56
19.	Material Cost--Ballast System (U.S. Dollars)	58

SHIP STRUCTURE COMMITTEE

The SHIP STRUCTURE COMMITTEE is constituted to prosecute a research program to improve the hull structures of ships by an extension of knowledge pertaining to design, materials and methods of fabrication.

RADM W. M. Benkert, USCG
Chief, Office of Merchant Marine Safety
U.S. Coast Guard Headquarters

Mr. P. M. Palermo
Asst. for Structures
Naval Ship Engineering Center
Naval Ship Systems Command

Mr. M. Pitkin
Asst. Administrator for
Commercial Development
Maritime Administration

Mr. K. Morland
Vice President
American Bureau of Shipping

Mr. C. J. Whitestone
Maintenance & Repair Officer
Military Sealift Command

SHIP STRUCTURE SUBCOMMITTEE

The SHIP STRUCTURE SUBCOMMITTEE acts for the Ship Structure Committee on technical matters by providing technical coordination for the determination of goals and objectives of the program, and by evaluating and interpreting the results in terms of ship structural design, construction and operation.

NAVAL SEA SYSTEMS COMMAND

Mr. C. Pohler - Member
Mr. J. B. O'Brien - Contract Administrator
Mr. G. Sorkin - Member

U.S. COAST GUARD

LCDR E. A. Chazal - Secretary
CAPT C. B. Glass - Member
LCDR S. H. Davis - Member
LCDR J. N. Naegle - Member

MARITIME ADMINISTRATION

Mr. N. Hammer - Member
Mr. F. Dashnaw - Member
Mr. F. Seibold - Member
Mr. R. K. Kiss - Member

MILITARY SEALIFT COMMAND

Mr. D. Stein - Member
Mr. T. W. Chapman - Member
Mr. A. B. Stavovy - Member
CDR J. L. Simmons - Member

NATIONAL ACADEMY OF SCIENCES SHIP RESEARCH COMMITTEE

Mr. R. W. Rumke - Liaison
Prof. J. E. Goldberg - Liaison

AMERICAN BUREAU OF SHIPPING

Mr. S. G. Stiansen - Chairman
Mr. I. L. Stern - Member
Dr. H. Y. Jan - Member

SOCIETY OF NAVAL ARCHITECTS & MARINE ENGINEERS

Mr. A. B. Stavovy - Liaison

WELDING RESEARCH COUNCIL

Mr. K. H. Koopman - Liaison

INTERNATIONAL SHIP STRUCTURES CONGRESS

Prof. J. H. Evans - Liaison

U.S. COAST GUARD ACADEMY

CAPT W. C. Nolan - Liaison

STATE UNIV. OF N.Y. MARITIME COLLEGE

Dr. W. R. Porter - Liaison

AMERICAN IRON & STEEL INSTITUTE

Mr. R. H. Sterne - Liaison

U.S. NAVAL ACADEMY

Dr. R. Bhattacharyya - Liaison

I. INTRODUCTION

IA. BACKGROUND

There are many differences and similarities between conventional ship and airframe assembly methods. These differences range from the obvious to the very subtle and are related to the particular fabrication techniques and the design philosophy of the structures.

In both industry situations, customer/user performance criteria within the context of regulatory agency requirements influence the direction taken by the designer and builder in producing a vehicle to satisfy customer needs for a price.

The aerospace industry has been challenged to extend its capability in many areas. Premiums attached to weight of airframes resulted in the introduction of honeycomb construction and adhesive bonding. Several other joining processes received impetus. These include plasma and electron beam welding, diffusion bonding, and mechanical fastening.

Parallel with the above activity, the jet commercial transport came of age. This growth in the commercial market provided the opportunity to develop new processes offering cost-effective returns. The quest for increased customer acceptance emerged in one form as extended-life airframe warranties (fatigue-rated structure).

These factors contributed to the utilization of a full complement of material forms (sheet, plate, extrusions, castings, forgings, weldments); materials (aluminum, steels, titanium, nickel magnesium, glass-reinforced plastics, etc.); alloys within a basic metal family; and heat-treat tempers to their best advantage. As a result, a delivered aircraft represents a conglomeration of materials and material conditions, each of which may require a unique joining method. Outfitted ships represent a similar conglomeration of materials and joining methods. The net result is a full complement of joining methods ranging from diffusion bonding, fusion and resistance welding, adhesive bonding, and a wide variety of mechanical fasteners. This area of joining becomes extremely significant and is the basic subject of this report.

The principal method of airframe structural joining is mechanical fastening. These fasteners range in size from 3/32-inch diameter, for riveting of floating nut plates, to high-strength alloy steel and titanium bolts of 2-inch diameter. Structurally rated blind rivets, families of vendor proprietary interference fit fastener systems, and several classes of riveting make up the process inventory. These include fastener types and installation processing criteria for fluid-tight fasteners classified for use in integral fuel tank structures. Another classification of fasteners is available for fatigue-rated fluid-tight applications. Some of the principal considerations for fastening of airframe include low fabrication cost and capital equipment requirements, proven reliability, repairability/panel replaceability, fail-safe design philosophy, and fatigue considerations. End item inspectability is also a pertinent consideration.

Portable tools and mechanized equipment (including multiaxis numerically controlled panel riveters) have been developed to install the various types of fasteners.

Unlike aircraft, the quantities of ships constructed on a particular production run are relatively few in number. The extensive use of hard tooling and jiggling is not warranted in the assembly stages due to the high costs involved. However, production and modular assembly concepts developed in the shipbuilding industry have been adopted for widespread use in the airplane industry. These include the use of full-scale lofting, free-floating jigs (one degree of freedom) common to both industries and construction by compartments or sections.

The interest of the government and the civilian sector in fast-ship concepts, such as the hydrofoil and surface-effect ships, has led to the need for new fastening or joining techniques. Some of the newer techniques already being investigated in the shipbuilding industry (such as bimetallic joinings) are documented in this report, along with fastening systems that have in the past been used primarily in the aircraft industry.

IB. SCOPE

On the basis of prior screening, a selection was made of specific types of attachments to be studied in greater detail. These include: Several aspects of equipment and systems installation and joints between dissimilar materials (metals and nonmetals combinations). Both of these were studied for:

- a) Fabrication cost and practicality
- b) Maintenance requirements and savings
- c) Corrosion and fracture characteristics
- d) Inspection requirements
- e) Weight
- f) Fatigue capabilities
- g) Comparison with other methods
- h) Reliability

The following joining problems were studied with respect to the above criteria:

- a) The use of bimetal strips or fillers produced by diffusion bonding, roll bonding, or explosive bonding for conventional welding of dissimilar metals
- b) Use of flanged, formed bead structure for dissimilar metals explosively bonded in place

- c) Use of friction welding for dissimilar metal stud welding
- d) Use of explosive or diffusion bonding to produce dissimilar metal sleeves for melt-through joining with portable, automatic tube welders
- e) Use of explosive bonding to jacket foreign metal structures for prevention of underwater electrolysis
- f) Use of special edge members and shock-absorbing sleeves for attachment of nonmetals
- g) Bulkhead penetrations
- h) Mechanical fastening for structural and nonstructural joints
- i) Adhesive bonding of similar and dissimilar metal joints
- j) Hole preparation
- k) Coldworking holes for increased fatigue strength
- l) Fluid-tight flush fasteners for hydrodynamic environments.

As this study is conceptual in nature, no hardware has been fabricated. Individual applications of proposed techniques will require evaluation on their own merits.

II. INVESTIGATION AND ANALYSIS

IIA. IDENTIFICATION OF PROBLEM AREAS FOR STUDY

This part of the program involved research of available data from several sources, including the Defense Documentation Center, local and company libraries, reports made available to Boeing from the Ship Structure Committee, and visits to vessels under construction and in service. These visits provided first-hand information as to use-experience problems associated with ship structure, and, in addition, served to familiarize the authors in the language of the industry.

Based on initial discussions with the advisory group and subsequent consultations and reviews, it was determined that connections and attachments made below a ship's waterline would be internal connections only and that nothing should penetrate the outer hull. However, above the waterline, where connections and attachments other than welding have been proven economical and safe, such information is in the recommendations contained in this report.

Welding of conventional steel ship structure is discussed briefly in this study because it is based on well-established processing knowledge. Emphasis was placed on identifying fabrication problems in steel and aluminum structure, systems attachments, and what is generally known as outfitting.

Based on service experience and history, it has been determined that one of the major problems encountered in the fabrication of aluminum structure is that of galvanic incompatibilities caused by the coupling of dissimilar metals in the presence of a sea-water electrolyte. The galvanic-corrosion problem manifests itself in many areas during initial construction and while the vessel is in subsequent use. The areas where galvanic corrosion can be located and identified range from the attachment of the deckhouse to hull structure and of equipment foundations to structure. The major emphasis of this problem is to identify these areas and to suggest alternative fabrication or attachment methods. Table 1 identifies areas pertinent to the scope of this input and includes a brief summary of proposed alternatives. Discussion in the remarks column is sometimes brief because of space limitations. Additional discussion may be found in the sections of this report referenced in the remarks column.

IIB. GENERIC FASTENER MATRIX

Mechanical fasteners are produced commercially in a wide variety of sizes, shapes, alloys, protective finishes, and heat treatments. Their respective installation requirements vary from squeeze deformation to interference fits. The current fastener inventory can satisfy a multitude of requirements, both structural and nonstructural. These applications include fluid-tight and fatigue-rated joints, riveted lap joints in thin structure, and attachment of systems and equipment.

The generic fastener matrix (Table 2) lists a number of different families of fasteners used in the aircraft industry that have potential for application in fabrication of ship structure. With few exceptions, these are government-approved standard parts. In fact, several of these fasteners are already being used in specialized applications in the shipbuilding industry.

TABLE 1
ALTERNATE APPLICATIONS TABLE

Problem area or type	Present practice	Proposed alternatives	Remarks
Aluminum deckhouse fabrication	Steel and aluminum structure Weld stiffeners and hatch covers to bulkheads Deckhouse to deck major load carrying joint	Prefabricate superstructure Rivet stiffeners to bulkhead Design framing to be primary load carrying members	Conventional riveting Cost effective method of joining Less distortion and warpage High maintenance and repairability Rivet detailing safe operations, low costs No welding allowances or quality limitations Applicable to other structure joiner bulkheads, frames, etc. (Refer to section 11)
Joining aluminum deckhouse to steel deck (galvanic corrosion)	Lap joint Apply primers and sealants Drill and install Huck bolts Apply sealants to joint fillets Prime and paint Requires steel coaming above deck	Prefabricate deckhouse superstructure Use bimetallic strip as interface Weld strip to coaming Eliminate coaming, weld directly to deck (Litton Shipyard practice)	Explosive bonded bimetallic strips afford Multiple bond of dissimilar metals Excellent corrosion resistance Low maintenance requirement Formed in place Cost effective installation (Refer to section 11)
Attachment of steel deck machinery to aluminum deck (galvanic corrosion)	Apply primer and paint to facing surfaces Install gaskets, plastic chocking, or washer pieces Bolt through deck framing Apply sealant to fillets Paint	Install bimetallic pads at interface Weld steel to steel, aluminum to aluminum Add CRES bolts if necessary	Bimetallics Allow similar metal to metal joints Galvanic couple isolators Machineable Can be shimmed for critical alignments (Refer to section 11) (and enclosures)
Compatibility of pump, pump connections, valves, and fittings	Conventional steel structure Allow steel to be pump systems Allows bronze steel valve connections Requires heavy duty pipe (schedule 80) Aluminum structure Install washer/washer Requires primers, sealants	Aluminum structure Use bimetallic for aluminum pipe to steel pump valve connections Use bimetallic as isolation mounts Use bimetallic as bulkhead penetrations for watertight compartment	Bimetallics Allow dissimilar metal pipe to pipe connections Lessen ship weight with aluminum pipe Save costs of nonsteel pumps and valving Watertight bulkhead penetrations Allow projection stud welds where necessary Eliminate washer pieces for pump mounts (Refer to section 11) (and enclosures)
Mechanical fastening	Steel structure attachments Projection stud welding Fusion welding Cost effective processes Aluminum structure Isolation mounts CRES fasteners Sacrificial bushings and washers	Steel structure Projection welding best cost-effective method Proprietary high strength fasteners available for systems attachments Aluminum structure Families of commercial fasteners available in various alloys and configurations Bimetallic and trimetallic strip and sheet available in many alloy combinations	Refer to fastener matrix section of this report for specific types, applications, and specifications. Refer to Table 2

TABLE 2
GENERIC FASTENER AND APPLICATIONS MATRIX

Generic name	Identification	Alloys	Characteristics and suggested applications
Solid-shank structural rivet (see Appendix H 17.611)			
Flush head	MS20426 BACR15DY MS20427M BACR15EE	5056 AR A-286 Monel Ti-6Al-4V	Characteristics Primarily shear rated Available with protective coatings Fluid-tight processes available Fatigue rated
Universal head	MS20470 BACR15DX MS20615M BACR15EW	5056 AI A-286 Monel Titanium alloys	Applications Below waterline applications Thin-gage applications Thin sheet lap and butt joints
Slug	BACR15BD	5056 AI	Structural shear and tension joints
Index head	BACR15FH	2117 AI 2024-T351	Fluid-tight assemblies and bulkheads Hand-driven installations Machine or yoke squeeze installations Electromagnetic riveting
Structural blind fasteners (see fig. 2)			
Protruding head	NAS1398C NAS1398NW NAS1398B BB678 BB352	A-286 Monel 5056 AI CRES CRES/6061	Characteristics High strength Available with protective coatings Labor saving installations Shear and tensile rated
Flush head	NAS1399B NAS1399C NAS1399MW BB677 BB351 BB449	5056 AI A-286 Monel CRES CRES A-286 6061 AI	Locked stem—hold filling and non-hole-filling Fluid tight with sealant Applications Limited-access areas Thin sheet and sandwich construction Bracketry attachments Temporary repairs Closeout panel attachment
Nonstructural blind fasteners (see Appendix H 17.613)			
Protruding head	MS20602 NAS1738 NAS1738	5056 AI 5056 AI Monel	Characteristics Low strength Locked stem—hole filling and non-hole-filling Hollow shank
Flush head	MS20603 MS20605 NAS1739 NAS1739	5056 AI Monel 5056 AI Monel	Applications Nonstructural attachments Nutplates Name plates
Blind nuts (see table 3)			
Protruding head	BN540 BN549	CRES A-286	Characteristics Structural rated Fluid tight
Flush head	BN360 BN555 BN562 BN158	CRES A-286 Ti-6Al-6V-2Sn 5056 AI	Flush and protruding head Labor savings
Three-piece system	BNB1108 BNB1109 BNB1110 BNB1111	A-286 A-286 A-286 Ti-6Al-6V-2Sn	Applications High-temperature applications Fuel and fluid tanks Structural and bracketry attachments Systems attachments Honeycomb sandwich panel attachments

TABLE 2
CONCLUDED

	Structural threaded fasteners (see figs 6 and 7)		
Protruding head	BUS1634 BUS1734 BUS1936	Steel alloy CRES Steel alloy	Characteristics High strength Fluid tight (with seal nuts or sealant) Tensile and shear rated Predetermined torque without torque wrench Various protective coatings and finishes Removable for repair and modification Applications High-temperature applications Fit-up bolts for joining assemblies Above and below waterline applications Deck machinery attachment
Flush head	BUS1434 BUS1535 BUS1836	Steel alloy CRES Steel alloy	
Six wing	SW1050 SW1055 SW2060 SW2262 SW2565 SW2855	4140 A-286 H-11 270 ksi H-11 230 ksi Ti-6Al-4V Ti-6Al-6V-2Sn	
	Structural lockbolts (see Appendix H 17.634)		
Flush head	BACB30GQ NAS1436-42 NAS1456-62	Aluminum alloy Steel alloy Titanium alloy, CRES	Characteristics Shear and tension rated Fatigue rated Fluid-tight bolts and collars available Various protective coatings and finishes High-temperature and corrosion resistant Weight savings Labor saving Applications Limited-access applications Panel lap or butt joints Bracketry and equipment support attachments Fluid-tight joints
Protruding head	BACB30GP NAS1446-52 NAS1465-72	Aluminum alloy Steel alloy Titanium alloy	
Stump type	BACB30DX A NAS1414/1422 NAS1424/1434 NAS2060V/ 2712V	CRES 4037/8740 Optional Ti-6Al-4V	
	Quick release fasteners (see Appendix H 17.634)		
Protruding head	BACS21Y	Steel alloy CRES	Applications Equipment covers Access panels Tension loads to 1700 lb Shear loads to 3580 lb
Flush head	BACS21X	Steel alloy CRES	

Note: See text for general discussion and cited enclosures and figures for additional details.

Before some of these fasteners can be used for broad applications by the designer or naval architect, it is essential that design parameters or engineering allowables be established for each fastener system. A wealth of data exists within the shipbuilding and aerospace industry on the various physical and chemical properties of these fasteners. This information is usually a part of the individual fastener standard and is usable at "par" in any industry.

This degree of transferability does not always apply in the case of product applications. These application criteria are often called design allowables, design parameters, or design standards. They are defined as the complex body of information that delineates the limits within which a structure can be designed. They often include the maximum safe stress levels for a desired environment for fasteners; allowances for structural mismatch at the time of joining; allowances for fitup stresses; corrosion allowances; fatigue considerations; etc. In sophisticated structural systems, such as large commercial ships and aircraft, they vary widely as a function of the intended performance envelope and useful life of the particular vehicle.

Specifically, these involve:

- a) A full range of fastener sizes, lengths, and materials
- b) Various types of joints
 - 1) Single lap
 - 2) Double lap
 - 3) Butt
 - 4) Fluid tight
 - 5) High load transfer
- c) Various applied loads
 - 1) Direction
 - 2) Magnitude
 - 3) Frequency
- d) Environment
 - 1) Thermal considerations
 - 2) Corrosion-prevention requirements
 - 3) Material compatibility
 - 4) Material properties
- e) Structural life requirements
 - 1) Stress limitation, corrosion

- 2) Fatigue limits
- 3) Stress concentration factor
- f) Structural maintainability and repairability
 - 1) Tooling required for installation
 - 2) Tooling required for maintenance
 - 3) Accessibility after assembly
- g) Safety margin and fail-safe requirements
- h) Hole tolerances
 - 1) Fastener fit
 - 2) Fastener installation
 - 3) Fastener repair/replacement.

For nonstructural attachments and joints, not all of the above considerations would come into play. These are included and referenced primarily to structural joints as would be found in hull-plate-to-stiffener or bulkhead-to-framing joints.

This body of information has been developed in the aircraft industry over a period of several years. It is in the form of design manuals, process specifications, and manufacturing manuals. This information is subject to varying degrees of transferability to the design of ship structure for reasons previously delineated.

The problem encountered in transferring design allowables from one industry to another are typified by the following: Whereas the allowables for coldworking of fastener holes in 2000- and 7000-series aluminum alloys would be directly transferrable, the allowables for coldworking holes in 270-300 ksi steel would not be usable for the weldable alloys usually used for ship structure. It would be necessary to conduct a series of fatigue and corrosion tests before coldworking of holes in low-strength steel could be used. Obviously, in situations where the same alloys, loading parameters, and service environments are involved, the allowables are directly transferrable.

IIC. MECHANICAL FASTENING AND HOLE PREPARATION

Mechanical fasteners have been with us since the earliest days of shipbuilding and can be expected to be with us in the foreseeable future. Most of the implementation of advanced joining techniques in the fabrication of current airframe structures has been in the category of detail part and subassembly manufacture. These new processes offer significant advantages; however, they often require more stringent in-process control, new equipment, and facilities and are more efficient for shop environments in contrast to field application.

As other subassembly fastening systems (such as bonding) gain wider acceptance, mechanical fasteners will still have many applications in final assembly

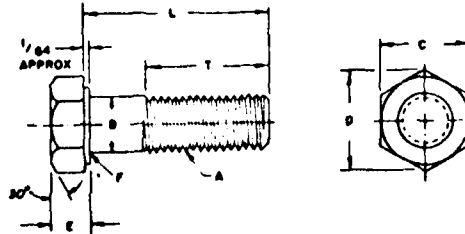
THIS PAGE IS BEST QUALITY PRACTICABLE
 DRAWING COPY FURNISHED TO DUC

BOEING

THIS COPY HAS BEEN SUPPLEMENTED BY THE ADDITION OF INFORMATION AS INDICATED
 BY THE FLAG NOTE (1) AS OF 12 DEC 66 BY THE BOEING COMPANY.

FED. SUP. CLASS
 5306

This standard has been approved by the Naval Ship Engineering Center, Department of the Navy, and
 is mandatory for use by that activity. All other military activities are required to employ this
 standard where suitable.



APPROVED BY BOEING 12 DEC 66

(Project 5306-N0125H) (1) For changes see sheets 1 through 5

CONTRACT NO.	ORDER NO.	MILITARY STANDARD	MS16208
SHIP	BOLTS, MACHINE, HEXAGON HEAD, SEMI-FINISHED, CORROSION RESISTING STEEL	UNC-2A, NONMAGNETIC	(SHIPS)
MIL-B-837			SHEET 1 OF 5

(2) ENGINEERING INFORMATION:
 THIS STANDARD WAS PREPARED BY NAVY BUREAU OF SHIPS AND SHOULD NOT BE USED
 ON CONTRACTS WITH OTHER AGENCIES WITHOUT APPROVAL OF THE PROCURING AGENCY.

MS 16208 (SHIPS)
 SHEET 1 OF 5

BOLTS, MACHINE, HEXAGON HEAD,
 SEMI-FINISHED, CORROSION RESISTING STEEL,
 UNC-2A, NONMAGNETIC

MS 16208 (SHIPS)
 SHEET 1 OF 5

FIGURE 1

EXAMPLE MACHINE BOLT STANDARD

joining and attachment of equipment and systems. Mechanical fastening is cost effective, can usually be performed with low-cost assembly tools, and is forgiving of tolerance accumulation between sections to be joined.

At one time, spot welding of skins to stiffeners was widely used in the aircraft industry. As reliability, performance, repairability, and service life requirements become more stringent, it was determined to be more effective to change to riveted and/or bolted structure. It appears that, some day in the future, the airframe will be bonded.

Mechanical fasteners have undergone a continuous evolution to keep pace with changing requirements. In fact, there is such a wide assortment of fastener types and designs available that care must be exercised to avoid the proliferation that comes from using a variety of fasteners for duplicate applications.

The Boeing Company is currently undergoing standards revisions to eliminate much of the fastener proliferation that has occurred. Fasteners that are no longer recommended for future design or current maintenance are being removed from inventory.

The Chrysler Corporation has recently reduced the number of different fasteners in its inventory from 3500 to the use of only 50 options. An internally generated fastener manual for designers consists of three main sections: general guidelines for fastener selection; a listing of preferred structural fasteners; and a listing of preferred nonstructural fasteners (Reference (1)). Metrification is another factor that should not be ignored in activities relating to the standardization of fasteners.

Methods that could be employed to control proliferation are (1) design standards, (2) central control of purchasing of fasteners, (3) controlled increments of grip length and diameter, (4) use of standard sizes, (5) use of coarse threads for fasteners over 1/4-inch diameter and fine threads for smaller diameters, and (6) standardize fasteners to one alloy for each application.

Mechanical fastening systems, per se, have as many potential applications as there are fastener types.

FASTENER STANDARDS

Standards describing fastener types and their properties include: Military Specifications (MS), Society of Automotive Engineers (SAE), National Aerospace Standards (NAS), and Army/Navy Standards (AN). In addition to these standards, there are individual company standards and specifications, such as the Boeing BAC standards and proprietary fasteners of various manufacturers. Several examples of these standards are shown in Figures 1, 2, and 3.

The Assembly Directory and Handbook, published yearly by Hitchcock Printing Co., Wheaton, Ill., is a specifications guide and technical reference that is of invaluable assistance to design and assembly personnel. It contains lists of standards and products available from absorbers to zippers. Complete sections on fastener standards and specifications (NAS, MS, AN, etc.) are printed as are manufacturer names (Reference (2)).

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

THIS COPY HAS BEEN SUPPLEMENTED BY THE ADDITION OF INFORMATION AS INDICATED
BY THE FLAG NOTE 6 AS OF 10 JUN 70, BY THE BOEING COMPANY.

NATIONAL AEROSPACE STANDARD

AEROSPACE INDUSTRIES ASSOCIATION OF AMERICA, INC. 1371 FOURTEENTH STREET, N.W. WASHINGTON, D.C. 20004

HEAD MARKING (TO BECOME EFFECTIVE 1 JUNE 1963)

MATERIAL CODE - H FOR MONEL, C FOR A-286
NO LETTER FOR ALUMINUM

GRIP NUMBER OPTIONAL FOR ALL MATERIALS

MANUFACTURER'S IDENTIFICATION
MANDATORY FOR RIVETS
RECEIVED AFTER
1 JULY 1971

LOCK MAY BE
IN THIS AREA

NOT TO EXCEED
RIVET DIA.

SEE SPINDLE
CONFIGURATION
IDENTIFICATION

COUNTERBORE OF
SLEEVE SHANK
OPTIONAL

AL. ALLOY .010R MAX.
MONEL & A-286 .020R MAX.

NOT TO EXCEED
RIVET DIA.

NOT TO EXCEED
RIVET DIA.

FULL SERRATION

PARTIAL SERRATION

INDENTED
CIRCLE

NO CODE IN
PART NO.

SPINDLE CONFIGURATION IDENTIFICATION

RIVET DIAMETER NUMBER	RIVET SIZE NOMINAL DIAMETER (DIA.)	A	B	C	L
4	.125	.125	.250 ± .012	.054	12"
5	.156	.156	.312 ± .016	.067	10"
6	.190	.187	.375 ± .019	.080	8"
8	.250	.250	.500 ± .025	.107	6"

INTERCHANGEABILITY: The "A" CODE RIVETS (FULL SERRATIONS) AND NO CODE RIVETS (PARTIAL SERRATIONS) ARE
PHYSICALLY AND FUNCTIONALLY INTERCHANGEABLE EXCEPT FOR INSTALLATION TOOLS (PULLING HEADS).

CAUTION - RIVETS WITH DIFFERENT SPINDLE CONFIGURATIONS CANNOT BE
INSTALLED WITH THE SAME TOOL (PULLING HEAD); SEE PARAGRAPH
6.3 OF NAS1400

(a) .001 SHANK DIA INCREASE PERMISSIBLE WITHIN .100 INCH OF BASE OF HEAD
FOR MATERIAL, FINISH AND COLOR SEE SHEET 2

CODES:

ADD LETTER B AFTER BASIC PART NUMBER TO INDICATE 5056 ALUMINUM ALLOY SLEEVE
ADD LETTER D AFTER BASIC PART NUMBER TO INDICATE 2017 ALUMINUM ALLOY SLEEVE
ADD LETTER H AFTER BASIC PART NUMBER TO INDICATE MONEL SLEEVE
ADD LETTER C AFTER BASIC PART NUMBER TO INDICATE A-286 CORROSION RESISTANT STEEL SLEEVE
ADD LETTER W AFTER MATERIAL CODE LETTER TO INDICATE CADMIUM PLATED SLEEVE
ADD LETTER S AFTER MATERIAL CODE LETTER TO INDICATE SILVER PLATED SLEEVE
ADD LETTER A IN PLACE OF (-) BETWEEN DIAMETER & GRIP TO INDICATE RIVET WITH FULL SERRATED STEM

EXAMPLE OF PART NUMBERS:

NAS1398H4-4 - NICKEL-COPPER-ALLOY (MONEL) RIVET, .125 DIA WITH .188 TO .250 GRIP
RANGE, WITH NO FINISH OR SLEEVE, WITH PARTIAL SERRATED STEM AND
INDENTED DOT OR CONE IDENTIFICATION.

NAS1398B4-4 - 5056 ALUMINUM-ALLOY RIVET, .125 DIA WITH .188 TO .250 GRIP RANGE,
WITH PARTIAL SERRATED STEM AND INDENTED DOT OR CONE IDENTIFICATION.

NAS1398HW4-4 - NICKEL-COPPER-ALLOY (MONEL) RIVET, .125 DIA WITH .188 TO .250 GRIP
RANGE CADMIUM PLATED, WITH FULL SERRATED STEM AND INDENTED
CIRCLE IDENTIFICATION.

NAS1398DS4-4 - 2017 ALUMINUM-ALLOY RIVET, .125 DIA WITH .188 TO .250 GRIP RANGE,
WITH FULL SERRATED STEM AND INDENTED CIRCLE IDENTIFICATION.

(2) COMPLETELY REDRAWN

List of Current Sheets	
SHEET NO.	REV. NO.
1	2
2	2

CUSTOMER: NATIONAL AEROSPACE STANDARDS COMMITTEE

**PURCHASING DEPT
SPECIFICATION**

NAS 1400

TITLE

RIVET-BLIND, PROTRUDING HEAD,
LOCKED SPINDLE

CLASSIFICATION

STANDARD PART

NAS1398
Sheet 1 of 2

Published and Distributed by National Standards Association, Inc.
1371 Fourteenth Street, N.W.
Washington, D.C. 20004

Copyright, 1969, Aerospace Industries Association of America, Inc.

APPROVAL DATE APRIL 1961 REVISION (1) OCT 1962 (2) 15 SEP 1969

BY BOEING 10 JUN 70

ENGINEERING INFORMATION: SEE BOEING SUPPLEMENT TO NAS1398 (PAGE 80.71.5.1.3) FOR
RIVET CODES, RECOMMENDED USES, MATERIALS AND FINISH.

PROCUREMENT INFORMATION: SEE BOEING SUPPLEMENT TO NAS1398 (PAGE 80.71.5.1.3) FOR
SOURCES AND RECOMMENDED SPECIFICATIONS.

WICHITA AND VERTOL DIVISIONS AND THEIR SUBCONTRACTORS:
RIVETS WITH THE "A" CODE ARE INACTIVE FOR DESIGN.




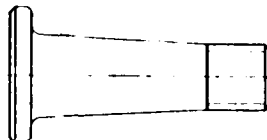
BOEING STANDARD

FIGURE 2

EXAMPLE BLIND RIVET STANDARD

BOEING

RESTRICTED USAGE : FOR REPAIR WORK ONLY , OVERSIZE SHANK



SEE SHEET 1 FOR DIMENSIONS NOT SHOWN.

[illegible]

1. RECEIVED 10/10/68 10:10 AM

[illegible]

FOR FLIGHTS, MATERIAL, FINISH, COLOR IDENTIFICATION AND DISCREPANCY INFORMATION, SEE VEH.

ALL INFORMATION CONTAINED HEREIN IS UNCLASSIFIED EXCEPT WHERE SHOWN OTHERWISE

- PLACE AND APPLICATION INFORMATION

THE ABOVE SIZE POLYMER ARE TO BE USED AS REPLACEMENT FOR POLYS SHOWN ON SHEET 1, WHEN THE SIZE IS 0.1 MICRON SIZE BUT IS UNUSABLE, OR MUST BE MADE ADJUSTED TO CORRECT DAMAGE OR MISALIGNMENT.

NOTE: FIRST DASH NUMBER INDICATES NOM. THREAD SIZE IN JOINT ELEMENTS. SECOND DASH NUMBER IS A MAX. OF THE JOINT RANGE IN INCHES PER FOOT.

EXAMPLE OF TYPICAL STANDARD NUMBER: RA-10000-10X - ROLL, UNEXPOSED, DUPO-201A DRY FILM LITHOGRAPHY OVERSLIP SHEET; FOR
RELEASEMENT OF RA-10000-10X.

SEE NOTE UNDER TABLE 2 REGARDING: "AGE" IS BASED ON 1991

DATE 10 FEB 67 REV (A) 22 NOV 67 (B) 29 MAY 68 (C) 10 MAR 70

BAC B30MW

SH 7

**BOLT, TAPER SHANK,
PROTRUDING SHEAR HEAD,
6AL-4V TITANIUM ALLOY**

BAC B30MW

SH

BEING STANDARD

PAGE 00. 12. 6. 9. 7


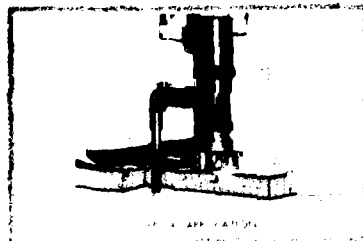
PAGE 80. 12. 6. 9. 7

FIGURE 3

EXAMPLE TAPER SHANK BOLT STANDARD

DRILLING FASTENER HOLES THRU BRAZED HONEYCOMB FOR ATTACHING WING PANELS

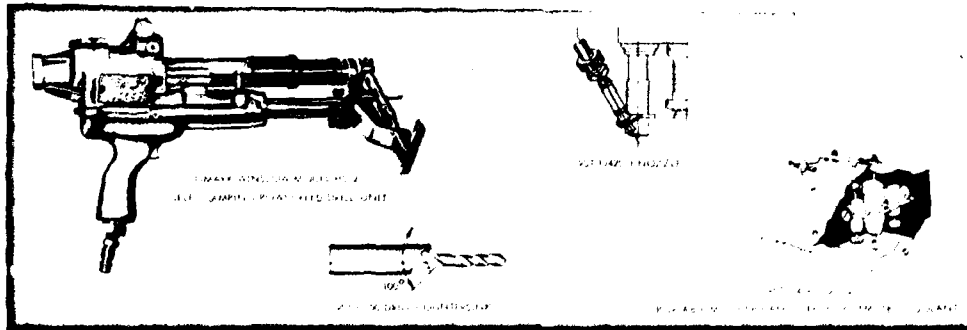THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC



- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT
- WITH ALL-CLAMPING-PISTON-FEED-DRILL-UNIT

FIG. 4 - OMARK-WINSLOW HS-2 SPACEMATIC DRILL

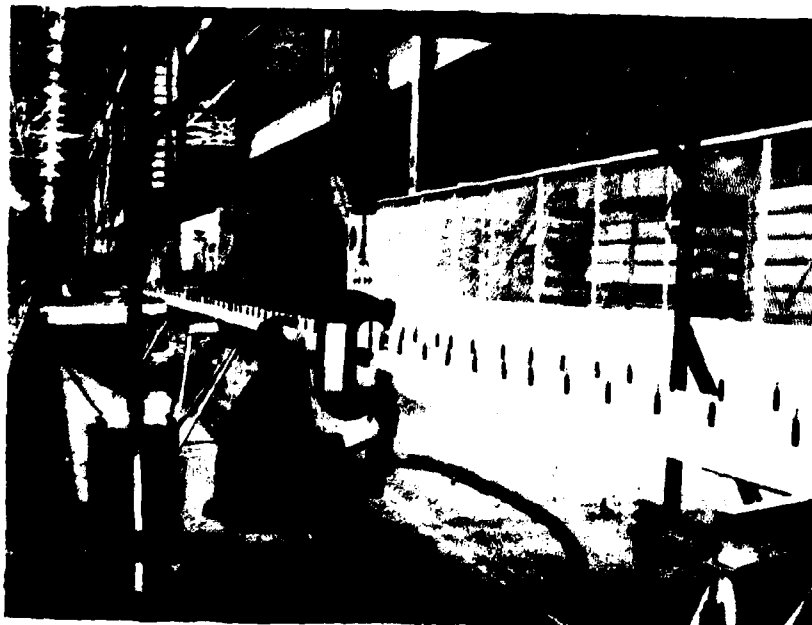


FIG. 5 - SQUEEZE YOKE RIVBOLT INSTALLATION ON 747 SPAR

Another magazine published biweekly by Penton Publication, Cleveland, Ohio, is the *Machine Design Magazine*. This journal features periodic reference issues devoted to fastening and joining and several other specific fields and areas of application. The reference issue reviewed for this report contains articles and technical literature on products ranging from screws, bolts, and studs to special-purpose fasteners such as spring clips and self-sealing fasteners.

FASTENERS: TYPES, APPLICATIONS, AND INSTALLATIONS

Fatigue-rated structural fasteners are available with straight and tapered shanks, flush and protruding heads, many alloys ranging from aluminum to titanium, and with several types of corrosion-preventive coatings or electrodepositions that can be applied to provide a fluid-tight condition.

Installation conditions include: Interference fits, net fits, clearance fits, and taper hole/shank interference fits. Holes can be precision drilled and reamed or broached, then coldworked to increase fatigue resistance.

Fasteners can be installed by squeeze operation, pull or push operation, or slip-fitted into a hole. Fastener retention is maintained by a torqued nut, a swaged collar, or by deforming the fastener.

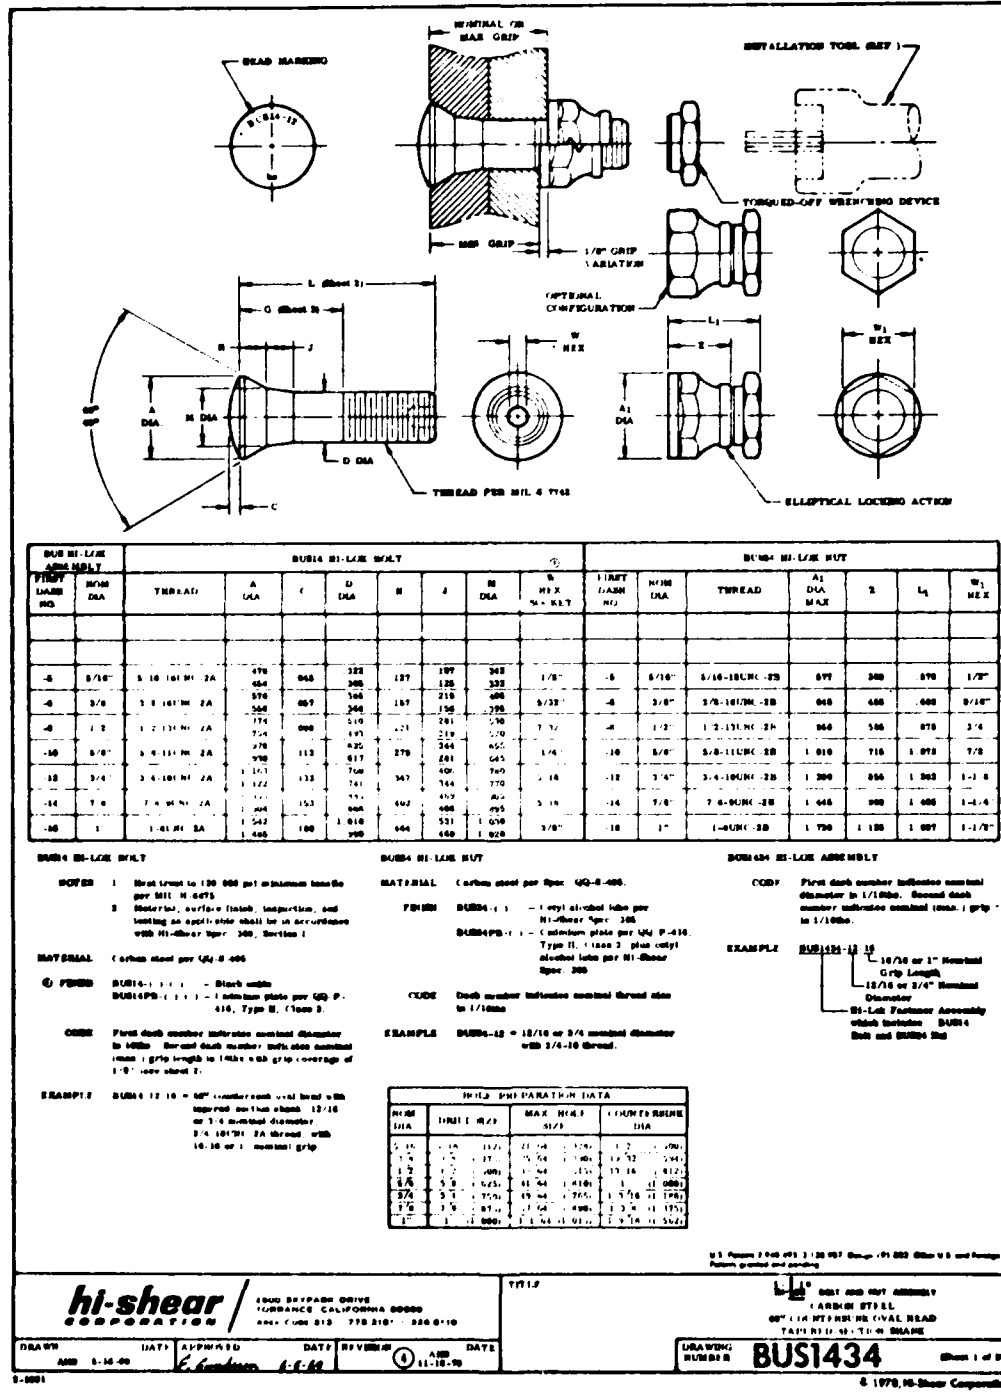
Installation processes vary from fastener to fastener, depending on the application and stress limitation. Drilling equipment required to produce holes varies in price depending upon the size and quality of the hole required. For example, the Omark-Winslow HS-2 drilling unit averages \$1,500 per unit (Figure 4). This drilling unit has very close tolerance and depth stop capabilities, and its use is intended where less sophisticated units are not adequate. They also manufacture large-capacity hydraulic drill motors.

Fastener installations are normally one- or two-man operations. The installation of titanium RivBolts in the 747 spar is shown in Figure 5. The C-yoke is semiportable and requires a spring balance for handling; however, smaller units are available. Equipment costs are generally low. Maintenance and repair are also low.

A matrix of typical fasteners is included with this report (Table 2). It is intended to serve as a guide in selecting fasteners for application in various structural and nonstructural assemblies. A few examples are discussed in the following paragraphs.

BUS Fasteners. The Hi-Shear Corporation began marketing a proprietary family of marine fasteners during the 1960s. The BUS Hi-Lok fastener (Figure 6) is a two-piece, high-strength, torque-controlled, threaded structural fastener designed specifically for naval and commercial ship construction. The BUS Hi-Lok consists of a high-strength marine-type bolt; a high-clamping nut with a wrenching hex torque-off feature for torque control; and matching lightweight, air-driven, installation tooling with Hi-Lok adapters designed for minimal clearances. This system is designed to provide hole-sealing capability. The manufacturer claims the BUS Hi-Lok system exceeds the vibration requirement of Mil-Std-167 and the strength requirement of Mil-B-23470. The Hi-Shear Corporation offers a marine fastener system booklet that contains this information.

THIS PAGE IS BEST QUALITY PRACTICE
 AND MAY BE USED FOR
 ANY PURPOSE



Six-Wing Fasteners. The six-wing fastener system is also available for high-tensile strength applications (Figure 7). These fasteners have a unique protruding torque head and are available for tensile or shear applications as well as high temperatures. The six-wing series is available in several alloys with tensile strengths from 160,000 to 240,000 psi. This fastener is designed for joints requiring high clamp forces, high tensile strength, and fatigue resistance. The attachment of machinery to the deck or the engine to the engine support mounts are examples of potential uses. The unique wrenching feature facilitates bolt removal when replacement or repairs are necessary.

Blind Fasteners. Several proprietary systems of blind fasteners and blind nuts are available from several sources (Tables 3, 4, and 5). These are available in flush and protruding heads as well as various alloys and heat treatments (see matrix). The distinguishing features of each fastener vary and depend on design or intended application.

Tables 3, 4, and 5 indicate representative fasteners and are not included as single sources or types. As an example, the Voi-Shan Visu-Lok is available in corrosion-resistant steel, a flush-head configuration, and can be used for panel closeout.

Lockbolts. In addition to the fastener systems mentioned, there are several lockbolt systems available for consideration. Lockbolts come in various configurations, such as flush and protruding heads, several alloys ranging from aluminum to titanium, various protective finishes, and are used for structural joints in tension and shear applications. Past naval applications have included use of steel protruding-head lockbolts for attachment of the deckhouse to the deck via a lap joint formed by the deckhouse and steel deck coaming. The manufacture of aircraft requires the installation of lockbolts in many areas. Structural applications include attachment of window and hatch reinforcing doublers and stiffeners in the body sections. Primary structural applications include installation of the wedgehead lockbolt on the aerodynamic surfaces of the wing to make the wing skin/stringer joint and for high-shear load-transfer joints or skin splices.

Rivets. Rivets are available in a variety of alloys, heat treats, coatings, and head configurations, a few of which are shown in Appendix H. Those listed in the matrix are fatigue rated and fluid-tight rated for structural applications. Rivets can be installed in thin sheets (less than 1/8 inch) and thick lap or splice joints; do not require tight hole tolerances; and are easily installed by hand-driving, machine-riveting, electromagnetic-riveting, and portable squeeze-riveting processes. Rivets can be installed in plain holes for interior structural applications or into countersunk holes for exterior, below-the-waterline, structural applications. Squeeze operations are generally throat limited, depending on application. Riveting the longitudinal framing on modular units and hull plates would minimize distortion of the structure caused by continuous seam welding. Splice-butt joints, similar to those in aircraft wing structure, could be applied to primary hull structure (Figure 8). An example of hand riveting is shown in Figure 9 and of numerically controlled (N/C) machine riveting in Figure 10.

Modularized or "jumboized" structure could be mechanically fastened with fatigue-rated fasteners in preassembled units. Attachment of internal structure and ribbing could be facilitated by portable rivet-squeeze units, thus eliminating the need for welding "all around" in aluminum structure.









THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

TABLE 3
BLIND NUT SELECTION CHART—COUNTERSUNK HEAD TYPE^a

			SPECIAL CSR HEADS	SHEAR CSR HEAD	SHALLOW CSR HEAD	SHALLOW CSR HEAD WITH EXPANDER	SHALLOW CSR HEAD WITH EXPANDER WITH DOVE END	SHALLOW CSR HEAD WITH EXPANDER WITH DOVE END	SHALLOW CSR HEAD WITH EXPANDER WITH DOVE END	SHALLOW CSR HEAD WITH EXPANDER WITH DOVE END	SHALLOW CSR HEAD WITH EXPANDER WITH DOVE END
MATERIALS AND FINISHES	SUGGESTED MAXIMUM TEMPERATURE FOR USE - F	SPECIAL TOOLING	"A" TOOLING	"B" TOOLING	"B" TOOLING	"B" TOOLING	"B" TOOLING	"B" TOOLING	"B" TOOLING	"B" TOOLING	"B" TOOLING
305 S.S.	431 S.S. Cadmium Plate	450°	BN387			BN318	BN388	BN388L			
305 S.S.	17-4PH S.S. Cadmium Plate	450°			BN389		BN389				
305 S.S.	431 S.S. Silver Plate	450°		BN314							
305 S.S. Sandblast	431 S.S. Cadmium Plate	450°		BN380	BN380 BN380A BN380B BN380C						
305 S.S. Sandblast	431 S.S. Silver Plate	450°			BN387						
305 S.S. Sandblast	431 S.S. Cadmium Plate	450°		BN380PS		BN318PS					
305 S.S. Sandblast	A-286 ALLOY SOLID FILM LUBRICANT	500°		BN380	BN380 BN380A BN380B BN380C						
305 S.S. Sandblast	A-286 ALLOY SILVER PLATE	700°		BN380A	BN380A BN380B BN380C						
305 S.S. Sandblast	BERYLCO 33-25 CETYL ALCOHOL	400°			BN380						
A-286 ALLOY Cadmium Plate	431 S.S. Silver Plate	450°			BN379P						
A-286 ALLOY Sandblast	431 S.S. Silver Plate	450°		BN380A BN380B BN380C	BN372						
A-286 ALLOY Sandblast	A-286 ALLOY SOLID FILM LUBRICANT	500°		BN380							
A-286 ALLOY Sandblast	17-4PH S.S. Silver Plate	500°			BN380						
A-286 ALLOY Sandblast	A-286 ALLOY SOLID FILM LUBRICANT	500°			BN377 BN380		BN377 BN380A				
A-286 ALLOY Sandblast	A-286 ALLOY SILVER PLATE	1200°			BN380						
A-286 ALLOY	CETYL ALCOHOL LUBRICANT Cadmium Plate OR SILVER PLATE	450° OR 1200°									STB1 STB2 STB3 STB4 STB5 STB6 STB7 STB8 STB9 STB10 STB11 STB12 STB13 STB14 STB15 STB16 STB17 STB18 STB19 STB20 STB21 STB22 STB23 STB24 STB25 STB26 STB27 STB28 STB29 STB30 STB31 STB32 STB33 STB34 STB35 STB36 STB37 STB38 STB39 STB40 STB41 STB42 STB43 STB44 STB45 STB46 STB47 STB48 STB49 STB50 STB51 STB52 STB53 STB54 STB55 STB56 STB57 STB58 STB59 STB60 STB61 STB62 STB63 STB64 STB65 STB66 STB67 STB68 STB69 STB70 STB71 STB72 STB73 STB74 STB75 STB76 STB77 STB78 STB79 STB80 STB81 STB82 STB83 STB84 STB85 STB86 STB87 STB88 STB89 STB90 STB91 STB92 STB93 STB94 STB95 STB96 STB97 STB98 STB99 STB100
316 S.S. Sandblast	A-286 ALLOY SOLID FILM LUBRICANT	500°		BN380							
ARMCO 10-10W S.S. Sandblast	431 S.S. Cadmium Plate	450°		BN380 BN380A BN380B BN380C							
5052 AL Sandblast	431 S.S. Cadmium Plate	350°								BN180 BN187	
5052 AL Sandblast	A-286 ALLOY SOLID FILM LUBRICANT	350°								BN180 BN187	

^aReprinted from Hi-Shear Blind Nuts and Blind Bolts catalog

BLIND NUT SELECTION CHART-PROTRUDING HEAD TYPE^a

			 STANDARD PROTRUD- ING HEAD	 STANDARD PROTRUD- ING HEAD WITH KNURLED SHANK	 THIN PROTRUD- ING HEAD	 VERY THIN PROTRUD- ING HEAD WITH KNURLED SHANK
MATERIALS AND FINISHES		SUGGESTED MAXIMUM TEMPERATURE FOR USE - F.				
SLEEVE	EXPANDER		"C" TOOLING	"C" TOOLING	"C" TOOLING	"C" TOOLING
306 S.S.	431 S.S. CADMIUM PLATE	450°		BN540		BN533
305 S.S. CADMIUM PLATE	431 S.S. CADMIUM PLATE	450°	BN356PB	BN540PB		
305 S.S. SANDBLAST	431 S.S. CADMIUM PLATE	450°	BN356 BN519LH		BN530	
305 S.S.	431 S.S. SILVER PLATE	450°				BN533G
305 S.S. SANDBLAST	431 S.S. SILVER PLATE	450°	BN356G		BN530G	
305 S.S. SANDBLAST	A-286 ALLOY SOLID FILM LUBRICANT	500°	BN542			
347 S.S. SANDBLAST	A-286 ALLOY SOLID FILM LUBRICANT	500°	BN523			
A-286 ALLOY SANDBLAST	A-286 ALLOY SILVER PLATE	1200°	BN549			

^aReprinted from Hi-Shear Blind Nuts and Blind Bolts catalog.

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO BCS

TABLE 5
VOI-SHAN VISU-LOK BLIND FASTENER

National
CALIFORNIA DIVISION

CUSTOMER: ENGINEERING STANDARD COMMITTEE FOR BLIND BOLTS
5123 SOUTH GARDFIELD AVENUE
LOS ANGELES, CALIFORNIA 90040

VSI VOI-SHAN
A DIVISION OF VSI CORP.

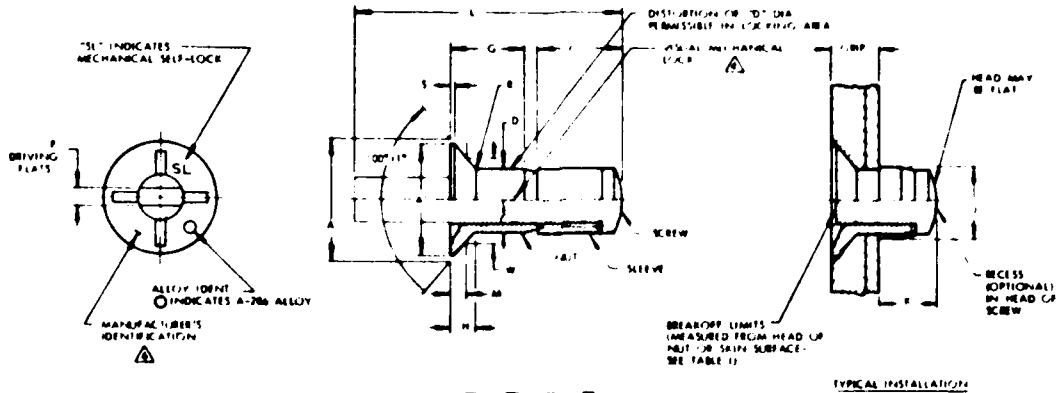


TABLE I

PART NUMBER	FORM DIA	A DIA THRU	A' DIA MIN	C MAX	D DIA	F DIA THRU PLATE	H DIA	J DIA MAX	K MAX	M GAUGE POINT	B DIA	S MAX	N GAUGE DIA	BREAK-AS LIMITS	PERMISSIBLE TENSILE STRENGTH (LBS MIN)	DESIGN SHEAR STRENGTH (LBS MIN)	TENSILE STRENGTH (LBS MIN)
PLT120-4-P	1.635	1.7	1.78	2.68	1.4	1.6	1.49	2.44	2.71	1.76 1.77	1.7	1.7	1.76 1.767	1.76 1.767	1.5	2,100	820
PLT120-4-4	1.985	1.97	1.98	3.61	1.99	1.98	1.97	3.00	3.09	1.99 1.999	1.9	1.9	1.97 1.973	1.97 1.973	1.5	4,130	1,400
PLT120-6-4	2.5	2.5	2.5	4.61	2.5	2.5	2.5	3.44	3.51	2.5 2.51	2.5	2.5	2.5 2.51	2.5 2.51	1.5	1,200	2,100
PLT120-10-4	3.155	3.15	3.15	6.72	3.15	3.15	3.15	4.27	4.36	3.15 3.157	3.15	3.15	3.15 3.157	3.15 3.157	1.5	10,350	3,600
PLT120-12-P	3.735	3.73	3.73	7.9	3.73	3.73	3.73	5.16	5.25	3.73 3.737	3.73	3.73	3.73 3.737	3.73 3.737	1.5	15,750	5,600

(*) SEE TABLE II FOR SECOND DASH NUMBERS AND APPROVED CALLOUT.

TABLE II

SECOND DASH NUMBER	G GAUGE	DRIP RATIO		TENSILE				
		MIN	MAX	PLT120-4-4	PLT120-4-4	PLT120-6-4	PLT120-10-4	PLT120-12-4
-2	1.5	.094	.156	.19	.116	1.036	1.158	
-3	2.0	.157	.219	.218	.134	1.069	1.221	1.304
-4	2.61	.220	.281	.270				
-5	.344	.287	.344	.363	1.193	1.331	1.473	1.567
-6	.408	.345	.408	1.045	1.146	1.281	1.426	1.497
-7	.469	.407	.469	1.107	1.228	1.356	1.497	1.567
-8	.531	.470	.531	1.170	1.291	1.419	1.571	1.644
-9	.594	.532	.594	1.233	1.351	1.481	1.621	1.697
-10	.656	.595	.656	1.295	1.416	1.544	1.696	1.779
-11	.719	.657	.719	1.358	1.478	1.606	1.758	1.844
-12	.781	.720	.781	1.421	1.541	1.667	1.821	1.904
-13	.844	.782	.844	1.483	1.603	1.729	1.883	1.967
-14	.906	.845	.906	1.545	1.666	1.791	1.946	2.029
-15	.969	.907	.969	1.607	1.728	1.853	2.008	2.092
-16	1.031	.970	1.031	1.670	1.791	1.916	2.071	2.154
-17	1.094	1.032	1.094		1.853	1.981	2.134	2.217
-18	1.156	1.095	1.156		1.916	2.044	2.196	2.279
-19	1.219	1.157	1.219		1.978	2.106	2.258	2.342
-20	1.281	1.220	1.281		2.041	2.169	2.321	2.404
-21	1.344	1.282	1.344		2.103	2.231	2.383	2.467
-22	1.408	1.345	1.408		2.166	2.294	2.446	2.529
-23	1.469	1.407	1.469		2.228	2.356	2.508	2.592
-24	1.531	1.470	1.531		2.291	2.419	2.571	2.654
-25	1.594	1.532	1.594		2.353	2.481	2.634	2.717
-26	1.656	1.595	1.656		2.416	2.544	2.696	2.779
-27	1.719	1.657	1.719		2.478	2.606	2.758	2.842
-28	1.781	1.720	1.781		2.541	2.669	2.821	2.904
-29	1.844	1.782	1.844		2.603	2.731	2.883	2.967
-30	1.906	1.845	1.906		2.666	2.794	2.946	3.029
-31	1.969	1.907	1.969		2.728	2.856	3.008	3.092
-32	2.031	1.970	2.031		2.791	2.919	3.071	3.154

NATIONAL ENGINEERING 98524		VOI-SHAN 92215	
APPROVED DATE 13 NOVEMBER 1970		STANDARD PLT 120 SHEET 1 OF 1	
REV LETTER AND DATE		TITLE VISU-LOK FASTENER, BLIND INTERNALLY THREADED, INTERNAL NUT HIGH TENSILE STEEL (A-706 ALLOY) FLUSH HEAD, SELF-LOCKING	



FIG. 9 - HAND RIVETING 727 SPAR

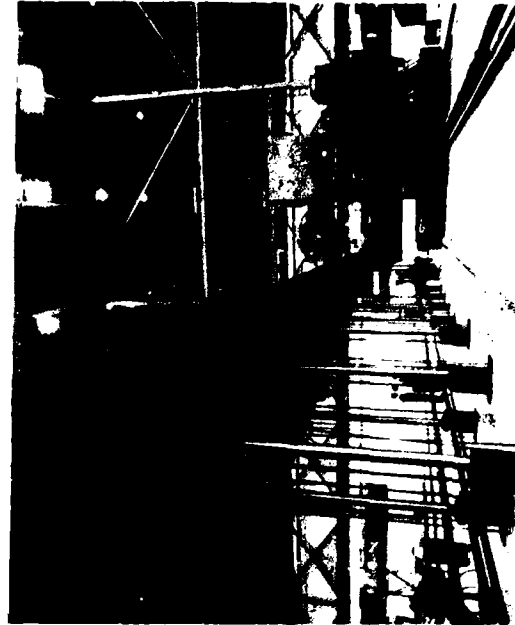


FIG. 10 - RIVETING STRINGERS TO 747 UPPER WING PANEL ON GEMCOR DRIVE-MATIC RIVETING MACHINES

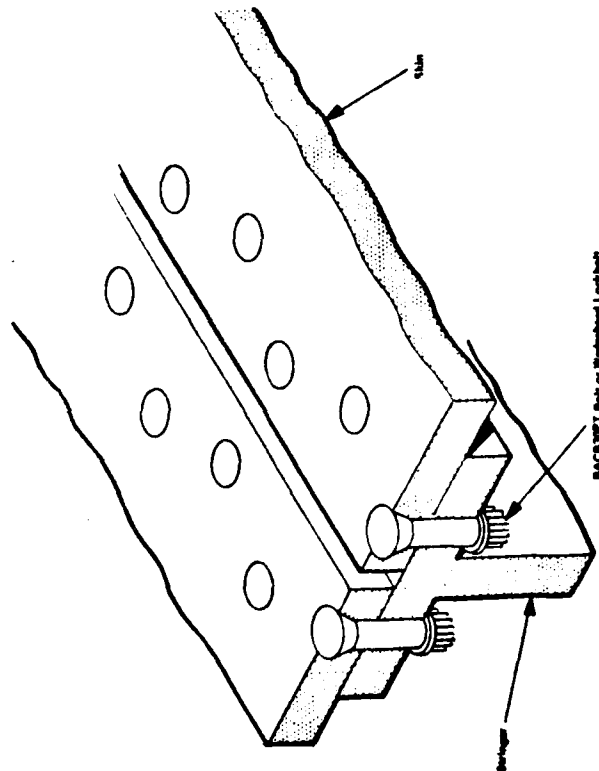


FIG. 8 - WING SPLICE JOINT

Nitinol. The Navy-developed Nitinol alloy offers promise as a riveting material. Composed of nickel, titanium, iron, and cobalt in various percentages, Nitinol can be formed to a configuration, chilled, and reformed to allow easy installation. Upon warming, the Nitinol assumes its original formed configuration. Nitinol is currently being used commercially in tubing fittings and blind fasteners. Grumman Aircraft is conducting an evaluation program on Nitinol fasteners (Reference (3)).

Drilling Equipment. Rivet installation in large panel areas, such as hull plates, can be placed on a production basis with the implementation of equipment similar to the Omark-Winslow track drill and the Boeing electromagnetic riveter (EMR). Several sources are available for various sizes of portable air and hydraulic power driven feed drill units that are equipped for speeds and feed rates for steel, aluminum, or titanium.

The track drill (Figure 11) is designed to repeatedly produce close-tolerance plain and countersunk holes. This unit travels in a vertical or horizontal motion, is self-indexing, and has a clamp force adjustable up to 1,500 pounds. The drill unit requires the attachment of a removable and reusable track and one hole initially for starting. This unit is compatible with a number of fastener systems such as precision interference pins, conventional rivets, or lockbolts. The approximate cost of the track drill is between \$8,000 and \$30,000, depending on the quantity and special features. A prototype unit has been tested and found practical. Plans defining the performance requirements for a production unit are being made.

Electromagnetic Riveting. Electromagnetic riveting (EMR) is a high-velocity, single-impact riveting process that converts electromagnetic energy into rivet forming energy. The EMR equipment (Figure 12) consists of a power pack and two, semi-portable, hand-held rivet guns with special power transmission cables, interconnecting air systems, and power pack. As compared to large automatic hydraulic riveting machines, the EMR equipment is substantially lower in initial procurement cost and, furthermore, features quieter operation and reduced floor space requirements. As compared to conventional hand gun driving, EMR is far superior in quality and repeatability while the noise level is reduced by several magnitudes (see Table 6). Standard available aluminum and titanium as well as steel rivets can be used with the EMR process, and rivet installations are uniform and repeatable with an extremely low rejection rate. The lower equipment cost (approximately \$100,000 for a complete system plus spares) allows more flexibility in manufacturing rate.

Because of the applied dynamic impact principle in the EMR process, rather than the static force application in hydraulic machines, the EMR guns can be handheld or incorporated in a lightweight truss-frame type of structure with practically unlimited throat depths.

The EMR process was initially developed by The Boeing Company for riveting portions of the large Boeing 747 wing panels, which could not be reached by automatic riveting machines. The EMR process, however, is generally applicable to any structural design where fluid-tight, fatigue-critical, and/or large-diameter fastener installations are a requirement. EMR should not be confused with electromagnetic forming. Both use electromagnetic energy to accomplish work. EM forming uses a single coil and rigid backing plate, whereas EMR uses two series coils that deform or upset the rivet placed between them.

The EMR system is composed of a capacitor bank and two coils, each abutting against a copper-faced driving ram. The coils are contained in two separate hand-held EMR guns. The work cycle consists of charging the capacitor bank to a preset

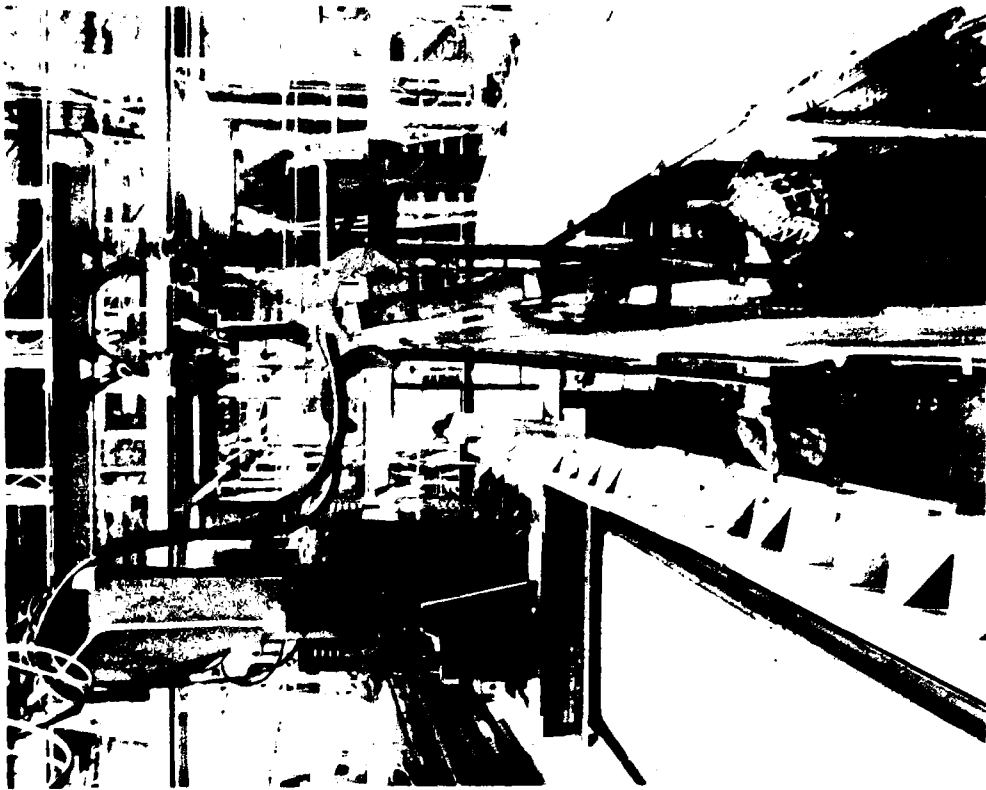


FIG. 12 - BOEING-DEVELOPED ELECTROMAGNETIC RIVETER


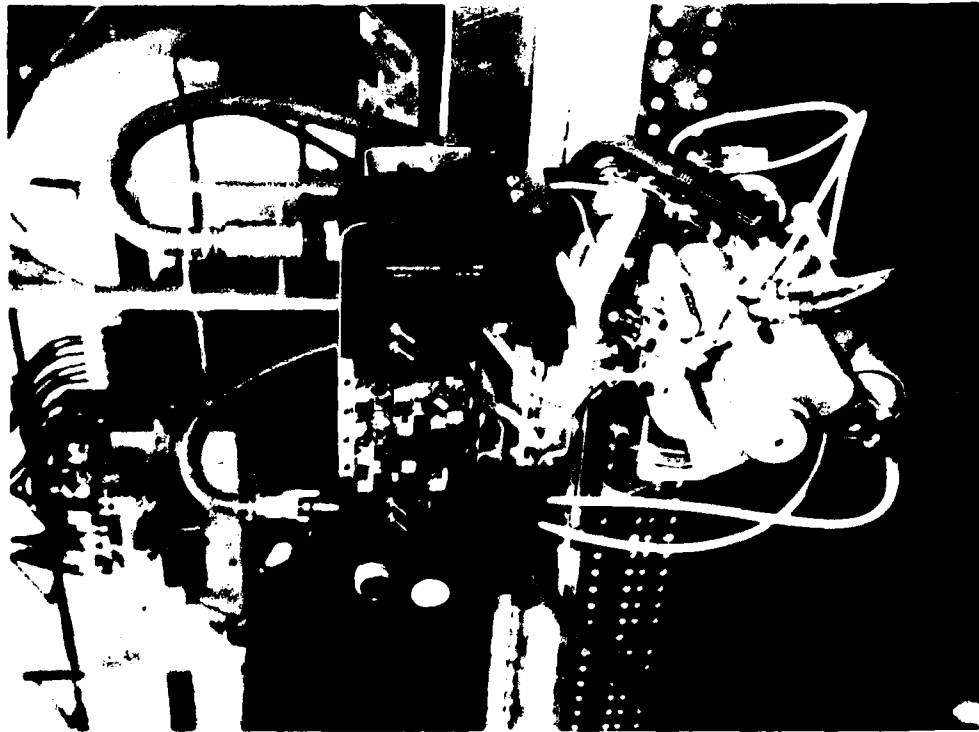


FIG. 11 - OMARK-WINSLOW TRACK DRILL

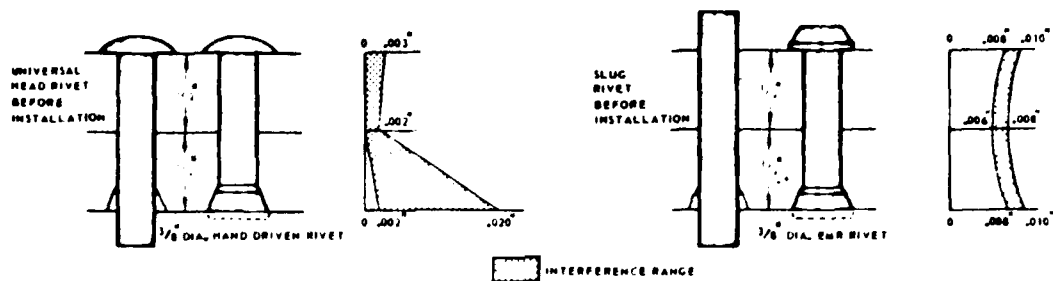TABLE 6
INTERFERENCE PROFILES—HAND DRIVEN—EMR^a



EQUIPMENT/PROCESS COMPARISONS	Large Automatic Riveting Machines	Manual Riveting	EMR
Fatigue Rated Capability	Excellent	Good	Excellent
Noise	High	Very High	Low
Maximum Practical Aluminum Rivet Capability.....	1/2"dia.	3/8"dia.	5/8"-3/4"dia.
Panel Size Capability.....	Limited	Unlimited	Unlimited
Cosmetic Quality.....	Excellent	Poor	Excellent
Reject Probability	Low	High	Very Low
Structural Distortion/Damage Probability...	Low	High	Low
System Maintenance.....	High	Very Low	Low
Maximum Rivet to Rivet Rate (3/8"dia.)..	7/minute	4/minute	20/minute
Direct Labor Ratio	0.85	2.1	1.0
Procurement Cost	Very High	Minimal	Relatively Low
Operator Fatigue	Low	Very High	Low

^aReprinted from EMR brochure.

TABLE 7
EMR TECHNICAL INFORMATION-BOEING 747 PRODUCTION SYSTEM ^a

Maximum Proven System Capability (Fatigue Rated Interference Profile)	
Aluminum Rivets.....	3/8" diameter x 1" grip
Titanium Rivets (Beta III).....	1/4" diameter x 1/2" grip
Stainless Steel Rivets (A-286).....	1/4" diameter x 1/2" grip
Deformation Time.....	5×10^{-4} Second
Deformation Energy.....	400 Ft. - lbs. (Equivalent to 30,000 lbs. static force.)
Power Pack	
Maximum Stored Energy Rating.....	6500 Joules
Energy Requirement (3/8" dia. Alum. Rivet)...	2600 Joules (3800 Volts)
Maximum Charge Voltage.....	6000 Volts
Maximum Cycling Rate.....	20 per Minute
Input Requirements	
Electrical.....	440 Volt - 3 phase
Air.....	90 psi
Dimensions.....	36" wide x 48" high x 60" long
Weight.....	2800 pounds
Hand Guns	
Body Size.....	6-1/2" dia. x 15-1/2" long
Overall Length.....	23-1/2"
Junction Box Protrusion.....	6"
Recoil Mass (Internal).....	45 pounds
Total Gun Weight (each).....	75 pounds (Used with counter balance)
Gun Power Cables	
Type.....	Multiple Low Inductance Coaxial
Minimum Bend Radius.....	10"
Protection.....	Individual coaxial insulation with armored sheathing plus neoprene sheathing.
Length.....	Cables are custom designed for specific applications as part of a " tuned " circuit.
Coils	
Dimensions.....	5" dia. x 3/4" thick
Life (Driving 3/8" dia. Alum. Rivets).....	Over 10,000 shots

^aReprinted from EMR brochure.

voltage level, followed by a rapid discharge through the series-connected coils. Synchronized by the current, the guns produce electromagnetic forces on the drivers, rapidly forming a rivet with equal and opposite forces (see Table 7). The EMR process can be used with several commercial rivet configurations and is not dependent upon high-cost proprietary fasteners. The cost of producing holes for the EMR is lower than with other fasteners such as lockbolts and requires a less expensive fastener.

EMR, when used in conjunction with the track drill, affords a cost-effective production capability for structural fastener installation (Figure 13) but is capable of functioning independently. Advantages of EMR are:

- a) Proven performance in production of Boeing 747 wing panels
- b) A high-rate installation capability (up to 20 rivets per minute)
- c) Built-in repeatability and quality assurance
- d) Interference profiles in thick material stacks not achievable with other riveting processes
- e) Rivet head uniformity
- f) Low-noise operation
- g) Minimum operator fatigue
- h) Low operator-skill requirement
- i) Rapid change, conventional rivet dies
- j) Relatively low capital acquisition cost
- k) Minimum floor space requirement
- l) Balanced impact forming of rivet to minimize structural distortion
- m) Growth potential for larger rivet installation and bolt replacements
- n) Manufacturing rate flexibility.

Cold Expansion Sleeve System. Under applied load conditions, each hole has associated with it a region of stress concentration where the applied stresses are magnified from two to three times their normal value. Hole expansion by coldworking successfully reduces the effect of this stress concentration by causing compressive radial stresses to remain around each hole. These residual compressive stress fields effectively prevent part failures from originating at the holes.

The cold expansion sleeve system (Figure 14) is a Boeing-developed process used for increasing the fatigue life of metal structures (aluminum, titanium, and steel) by causing compressive residual stresses around the fastener hole. The system consists of the radial expansion and sizing of fastener holes to achieve greatly improved fatigue performance while simultaneously reducing installed-fastener cost through the flexibility provided in fastener selection. Low-cost fasteners can be used in cold-worked holes without reducing the fatigue rating. Rivets or lockbolts can be used instead of more expensive fatigue-rated fasteners.



FIG. 14 - BOEING COLD EXPANSION SLEEVE SYSTEM



FIG. 15 - AIR/HYDRAULIC PULLER FOR COLD WORKING HOLES

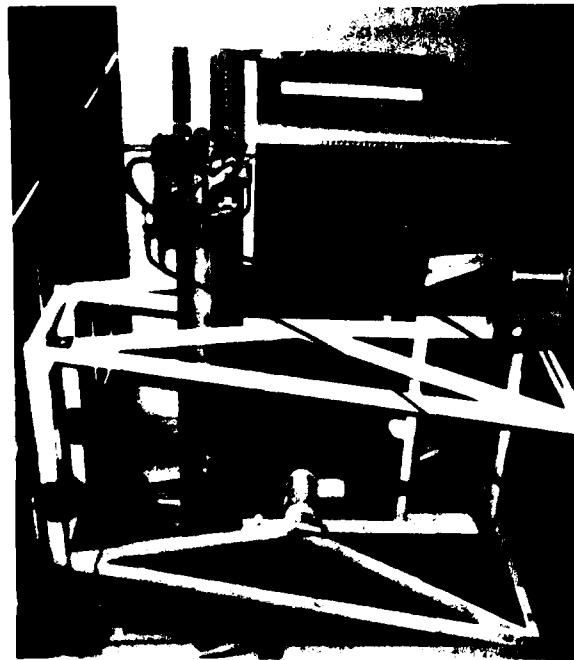


FIG. 13 - BOEING ELECTROMAGNETIC RIVETER AND OMARK-WINSLOW TRACK DRILL

Radial expansion of the fastener hole is achieved by pulling a hardened steel mandrel through a patented prelubricated sleeve using either a power or manual puller (Figure 15). Once coldworked, the sleeve is removed and the fastener is installed. The cold expansion sleeve system can be used with several different fasteners, including lockbolts and conventional rivets. For close-tolerance or interference-fit precision-shank fasteners, it is necessary to ream or broach the hole to size after coldworking.

Drawing the mandrel through the split sleeve causes a radial plastic flow of metal. Compressive stresses will be found surrounding the coldworked hole for a distance extending approximately one radius from the edge of the hole. This compressive stress region provides fatigue protection for a fastener hole. The compressive residual stresses oppose the applied tensile stresses and act as an obstacle to the initiation and growth of fatigue cracks.

The distance from the edge of the coldworked hole that the compressive residual stress extends depends upon the amount of hole expansion. Extensive testing has been conducted to determine the optimum expansion range that occurs during coldworking.

The cold expansion sleeve system has a number of advantages: (1) It allows greater expansion of fastener holes than previously used methods, (2) the process produces a controlled amount of coldworking, (3) use of the prelubricated sleeve reduces problems of galling and tool breakage, (4) all work can be accomplished by one man from one side of the structure. The sleeve process is for a high degree of coldworking (large radial expansion), but a straight mandrel process is also available. A solid, one-piece, tungsten carbide mandrel is being used to coldwork holes in high-strength steel (300 ksi) on the 747.

Honeycomb and Sandwich Panel Fasteners. Lightweight nonstructural bonded panels are being incorporated into shipbuilding. This type of structure requires special fasteners and installation techniques for attachment of support equipment and panel installation.

Honeycomb sandwich structure provides optimum strength-to-weight ratios as well as thermal and acoustic insulation. Methods of joining sandwich panels and making attachments to sandwich panels vary considerably.

Fasteners for sandwich or honeycomb structure are available commercially from several manufacturers such as the Shur-Lok Corp.; Voi-Shan, a division of VSI Corp.; or the Delron Co., Inc. Table 8 is an example of sandwich panel fasteners from the Delron Company, Inc.

Before selecting a fastener, load considerations must be made for tension, shear, or torque loads. The type of adhesive used in the sandwich and the physical properties of the sandwich must be known. Once these questions are answered, the designer can choose the suitable fastener. Additional considerations for proper fastener selection should include:

- a) Type and size of fastener to be used
- b) Blind or through-hole fastener
- c) Flush or protruding head

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

TABLE 8

DELTRON SELECTOR CHART HONEYCOMB AND SANDWICH PANEL FASTENERS²

	<p>101 & 102 Formmet type fastener consisting of a plug and sleeve section. Used for bolting and riveting panels to structural members. Riveting & threads etc. Available in three and five bolt styles.</p>		<p>400 A-Metal A metal two-piece molded-in fastener with four internal threads. Used for bolting panels to structural members. Recommended for use in applications where panels are subjected to elevated temperatures. Available in three and five bolt styles.</p>
	<p>103 Formmet type fasteners consisting of a plug and sleeve section with internal threads. Used for bolting equipment and components to honeycomb and sandwich panels without an external nut.</p>		<p>400 B-F Three piece molded-in fastener with floating nut. Used for bolting panels to structural members. Recommended for use in applications where panels are subjected to elevated temperatures. Available with or without self-locking feature.</p>
	<p>104 Formmet type fasteners consisting of a plug and sleeve section with internal self-locking threads. Used for bolting equipment to honeycomb and sandwich panels without an external nut.</p>		<p>400 S & SF Two piece molded-in fastener similar to 400 B-F & SF but with a threaded inner section that provides for use in all directional applications. Used for bolting panels to structural members. Available with or without self-locking feature.</p>
	<p>106 Formmet type fasteners consisting of a plug and sleeve section with internal self-locking threads. Used for bolting equipment to panels subjected to elevated temperature.</p>		<p>400 SF Two piece molded-in fastener similar to 400 S & SF but with a threaded inner section that provides for use in all directional applications. Used for bolting panels to structural members. Available with or without self-locking feature.</p>
	<p>293 D & F A mechanically installed blind fastener for light load applications. For use with use of heavy bonding material. Available for fast and air fast applications. Preassembled two piece construction.</p>		<p>400 HA & CA Two piece molded-in fastener adjustable for panels. Recommended for use in applications where panels are subjected to elevated temperatures. Available with or without self-locking feature.</p>
	<p>103F An adjustable type fastener for panels that vary in thickness beyond normal manufacturing limits. Available in various materials, head sizes and types including threaded self-locking. Two piece construction.</p>		<p>600 Flared A structural fastener with a floating self-locking nut. Body section is flared to grip panels. Recommended for use in applications where panels are subjected to elevated temperatures. Available with or without self-locking feature.</p>
	<p>404H & G One piece, molded-in type fastener designed for use with a minimum amount of potting material. Recommended for moderately high tension pull out and shear loads. Available with or without self-locking feature. Flared type available to be threaded into cover sheet.</p>		<p>601 & 602 A structural fastener that provides maximum strength values by supporting the cover sheets from within the core area. Available for three and five bolt applications in flared and non flared types. Preassembled two piece construction.</p>
	<p>400 HE & GE One piece, molded-in fastener for moderately high tension pull out and shear load. Minimum potting material required with vent holes for injection. Available with or without threaded self-locking feature. G type threaded into top cover sheet.</p>		<p>603 & 604 A structural fastener similar to 601 & 602 Series with internal threads for blind applications. Available in flared and non flared types with or without the self-locking feature. Preassembled two piece construction.</p>
	<p>400 HF & GF Two piece, molded-in fastener similar to 400 HE & GE but with a threaded inner section that provides 1/8 inch all directional horizontal float allowing for misalignment of mounting holes in attaching member. G type threaded into top cover sheet.</p>		<p>700 Standard A structural fastener incorporating a floating self-locking nut. Designed for post bolt misalignment in panel applications. Preassembled two piece construction. Also available 700 F with flaring feature that grips against cover sheet.</p>

²Reprinted from Deltron Honeycomb and Sandwich Panel Fasteners catalog.

- d) Torque requirement of threaded types
- e) Fastener material
- f) Environmental temperature
- g) Molded-in or mechanical connection
- h) Fastener and sandwich material compatibility.

IID. EXPLOSION BONDING

The explosion bonding process of joining dissimilar metals was first developed for the chemical and aluminum processing industries. Its potential for marine applications was recognized by Naval architects and manufacturers of the material. Extensive testing to determine the physical properties and corrosion resistance of the clad materials has and is being conducted.

Increased use of electronic equipment aboard ships for communication and navigation and the demand to lower topside weight, increase maneuverability, and reduce ballast led to the introduction of aluminum superstructures. Initial installation techniques used lockbolts and sealants. As this method proved unsatisfactory, the clad materials have been implemented as transition joints between the aluminum deck-houses and steel decks. Known as bimetallics and trimetallics or transition inserts, these clad materials have been used in some shipyards. These materials are being designed into new ships in other applications.

Physical and mechanical properties of these materials, as well as several proposed applications, are elaborated upon in this section of the report.

The explosive bonding process was developed by E. I. du Pont de Nemours and Company in the late 1950s. Several years of extensive laboratory testing were conducted, ultimately resulting in commercial production of corrosion-resistant clad metals designed primarily for the chemical industry.

The procedure for achieving an explosive bond consists basically of placing the cladding plate above and parallel to a base plate. An explosive charge is then placed over the entire surface of the cladding plate and detonated from one end. The detonation travels at a rapid rate, up to 28,000 feet per second, generating an estimated pressure of 4,000,000 psi in the vicinity of the detonation (Figure 16 and Reference (4)).

The interface formed by the impinging metal causes a fluid-flow phenomenon or "jetting". The jetting that occurs removes oxides and foreign materials between the two plates. The resulting metallurgical bond is of a strength greater than the weaker of the two sheets. Hundreds of metals have been clad or bonded either to similar or dissimilar metals (Tables 9 and 10 and Reference (5)). Many of those listed in the tables were fabricated in small strips and samples to establish feasibility and are not available commercially. Other materials were clad but not reported for proprietary or classified reasons or for not being applicable to ship construction.

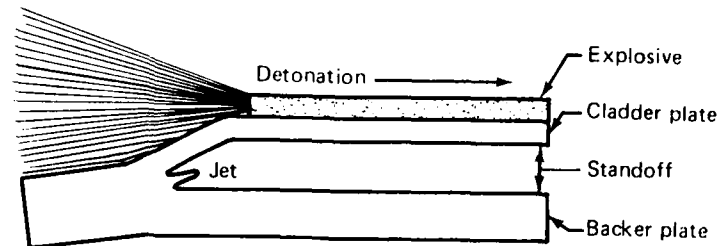


FIGURE 16

SCHEMATIC OF EXPLOSION BONDING PROCESS ILLUSTRATING JETTING
PHENOMENON WHICH REMOVES OXIDES AND FOREIGN MATTER
FROM SURFACES BEING JOINED

TABLE 9

METALS THAT HAVE BEEN EXPLOSIVELY BONDED TO THEMSELVES^a

Ferrous metals	
Low-carbon steels 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-204 Low-alloy steel ASTM A-302 Low-alloy steel ASTM A-387 Alloy steel AISI 4130 Alloy steel AISI 4340 Stainless steel type 200 series	Stainless steel 17-7PH Stainless steel type 301 Stainless steel type 304 Stainless steel type 321 Stainless steel type 347 Maraging steel, 18% nickel Ductile cast iron
Nonferrous metals	
Aluminum 1100 Aluminum 2024-T3 and -O Aluminum 2214-T6 Aluminum 5083-H24 Aluminum 6061-T6 Aluminum 7178-O Aluminum 7075-T6 Aluminum 1100/1.5 lithium Copper Brass Cupro-nickel Bronze Beryllium copper	Nickel Titanium—commercially pure Titanium-6Al-4V Titanium-5Al-5Sn-5Zr Titanium-8Al-1Mo-1V Titanium-13V-11Cr-3Al Zinc

^aExtracted from DMIC document 225, Explosive Bonding, Linse, Whitman,
and Carlson, Battelle Memorial Institute

TABLE 10
DISSIMILAR METAL COMBINATIONS THAT HAVE BEEN EXPLOSIVELY BONDED^a

<p>Low-carbon steels 1004-1020 to:</p> <ul style="list-style-type: none"> Stainless steel—ferritic Stainless steel—300 series Stainless steel—200 series Ductile cast iron Malleable cast iron Aluminum and aluminum alloys Copper Brass Cupro-nickel Nickel Zinc Titanium <p>Medium-carbon steels ASTM A-201 and A-212 to:</p> <ul style="list-style-type: none"> Stainless steel—300 series Stainless steel—200 series Aluminum and aluminum alloys Copper Brass Cupro-nickel Bronze Nickel and nickel alloys Titanium and titanium alloys Titanium 35A <p>Medium-carbon steel ASTM A-286 to:</p> <ul style="list-style-type: none"> Stainless steel—ferritic Stainless steel—300 series Stainless steel—200 series Aluminum and aluminum alloys Copper Brass Cupro-nickel Bronze Nickel and nickel alloys Titanium Titanium-6Al-4V <p>Low-alloy steel ASTM A-204 to:</p> <ul style="list-style-type: none"> Stainless steel—300 series Stainless steel—200 series Aluminum and aluminum alloys Copper Brass Cupro-nickel Nickel and nickel alloys Titanium and titanium alloys Hastelloy B, C, F Hastelloy X 	<p>Low-alloy steel, ASTM A302 to:</p> <ul style="list-style-type: none"> Stainless steel type 410 Stainless steel—ferritic Stainless steel—300 series Stainless steel—200 series Aluminum and aluminum alloys Nickel and nickel alloys Titanium and titanium alloys <p>Alloy steel AISI 4130 to:</p> <ul style="list-style-type: none"> Stainless steel—300 series Aluminum 2014-T6 and -T3 <p>Alloy steel AISI 4340 to:</p> <ul style="list-style-type: none"> Stainless steel—300 series <p>Maraging steel to:</p> <ul style="list-style-type: none"> Stainless steel—300 series <p>Hadfield steel to:</p> <ul style="list-style-type: none"> Aluminum and aluminum alloys <p>Stainless steel—200 series to:</p> <ul style="list-style-type: none"> Low-carbon steel AISI 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-204 Low-alloy steel ASTM A-302 Low-alloy steel ASTM A-387 Aluminum and aluminum alloys Brass <p>Stainless steel—300 series to:</p> <ul style="list-style-type: none"> Low-carbon steel AISI 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-204 Low-alloy steel ASTM A-302 Low-alloy steel ASTM A-387 Alloy steel AISI 4130 Alloy steel AISI 4340 Maraging steel Aluminum 6061-T6 Copper Brass Nickel and nickel alloys Titanium and titanium alloys Molybdenum <p>Stainless steel type 301 to:</p> <ul style="list-style-type: none"> Stainless steel type 347 Titanium-6Al-4V Aluminum 2219
--	---

^aExtracted from DMIC document 225, *Explosive Bonding*, Linse, Whitman, and Carlson, Battelle Memorial Institute

TABLE 10 (CONCLUDED)

<p>Stainless steel type 304 to: TD nickel-chromium</p> <p>Stainless steel type 321 to: Stainless steel type 347</p> <p>Stainless steel type 347 to: Stainless steel type 301 Stainless steel type 321 Hastelloy X Aluminum 6061-T6</p> <p>Stainless steel—martensitic, type 410 to: Low-alloy steel ASTM A-3870</p> <p>Stainless steel—ferritic to: Low-alloy steel ASTM A-387 Medium-carbon steel ASTM A-285 Low-carbon steel AISI 1004-1020 Titanium and Titanium alloys</p> <p>Aluminum and aluminum alloys to: Low-carbon steel AISI 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-212 Low-alloy steel ASTM A-302 Low-alloy steel ASTM A-387 Stainless steel—300 series Stainless steel—200 series Copper Titanium and titanium-6Al-4V</p> <p>Aluminum 1100 to: Titanium-6Al-4V Aluminum 1100/1.5 lithium</p> <p>Aluminum 2014-T6 to: Alloy steel AISI 4130</p> <p>Aluminum 2219 to: Stainless steel type 301</p> <p>Aluminum 6061-T6 to: Beryllium copper Stainless steel type 347 65% beryllium-35% aluminum Titanium-6Al-4V Zircaloy-2 Molybdenum</p> <p>Brass alloys to: Low-carbon steel AISI 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212</p>	<p>Low-alloy steel ASTM 204 Low-alloy steel ASTM A-302 Cast steel Stainless steel—300 series Stainless steel—200 series Nickel and nickel-base alloys</p> <p>Cupro-nickel alloys to: Low-carbon steel AISI 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-204 Low-alloy steel ASTM A-302</p> <p>Bronze alloys to: Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Alloy steel 4340 Alloy steel A6</p> <p>Nickel and nickel-base alloys to: Low-carbon steel AISI 1004-1020 Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-204 Low-alloy steel ASTM A-302 Low-alloy steel ASTM A-387 Stainless steel—300 series Brass Titanium and titanium alloys Copper Nickel and nickel-base alloys Columbium and columbium-base alloys Tungsten Inconel X</p> <p>Titanium-6Al-4V to: Stainless steel type 301 Aluminum 1100-0</p> <p>Titanium and titanium alloys to: Medium-carbon steel ASTM A-285 Medium-carbon steel ASTM A-201 Medium-carbon steel ASTM A-212 Low-alloy steel ASTM A-204 Low-alloy steel ASTM A-302 Low-alloy steel ASTM A-387 Stainless steel—ferritic Stainless steel—300 series Maraging steel Aluminum alloys</p>
---	---

In mid-1966, development work was started to produce a bimetallic transition insert for joining aluminum bus to steel anodes and cathodes in aluminum smelting plants. This joint used 1100 aluminum and 1008 steel.

BONDED SHEET

Recognizing the need for a marine industry application, Du Pont started development in 1966 of a clad sheet that would facilitate attaching the aluminum superstructure to the steel deck. The resulting bonded sheet is a triclاد employing aluminum alloy 5456 bonded to A516 Grade 55 steel with a commercially pure 1100-series aluminum interface between the structural materials. The 1100-series aluminum makes a significant contribution to the ductility and impact resistance of the triclاد. The resulting thickness is 1-3/8 inches. A similar product, Transition Insert, is produced commercially by the Kaiser Aluminum Co. (Reference (6)) and Northwest Technical Industries, Inc., of Port Angeles, Washington. The final product is a purchased item available in sheet or strips and is not an item that requires bonding in the shipyards. Mechanical cutting to the desired part configuration is performed in the shipyard.

Most commercial applications encountered to date utilize Du Pont's Detacouple/Detaclad sheet and plate. Thicknesses range from a few thousandths of an inch to over a foot, while the cladding metal thickness varies from 0.0001 to 1-1/2 inches (Reference (7)). The bimetallic sheet is produced in the same manner as the triclاد but does not have the 1100-series aluminum alloy in the interface and can be of numerous alloy combinations. Standard welding techniques available in shipyards are acceptable for fabrication with this material. As with all inert gas welding techniques, however, adequate provisions for protection from the elements should be provided.

TUBE CLADDING

Successful tube-cladding experiments have been conducted resulting in bond combinations for tubes in the 1/2- to 8-inch-diameter range. Materials that have been bonded include: Inconel and Zircaloy, stainless steel and Zircaloy, stainless steel and 6061-T6 aluminum, stainless steel and aluminum, 6061-T6 aluminum and titanium, and 1100 aluminum and magnesium (Reference (8)). Tubing can be clad internally or externally, depending on the design application.

Applications for explosive bonding include tubular cladding in condenser or heat-exchanger applications and underwater spot welding of dissimilar metals without removing the water interface; both processes were developed by Battelle Institute (Reference (5)). These processes afford the possibility of cladding stern tubes and rudder stocks in aluminum or other dissimilar structure to eliminate galvanic couples.

CORROSION TESTS

Several seawater/salt-spray corrosion tests are currently under way, the most extensive being conducted by International Nickel Co., at Wrightsville Beach, North Carolina. In conjunction with Du Pont, several samples of the Detacouple strip were welded to 5456 aluminum alloy and mild steel panels and have been subjected to splash-spray tests in excess of 5 years.

A graph of the result of the unpainted sample is shown in Figure 17. Galvanic corrosion penetration has reached approximately 0.063 inch in the unpainted samples.

TABLE 11 - CORROSION TESTING OF EXPLOSION-BONDED
TRANSITION JOINTS^a

Test and specimen description	Specimen condition	Exposure duration	Depth of penetration (in. b)
Transition joint welded to 3" X 7" X 1/4 in. 5456 aluminum and mild steel panels; splash spray test, Wrightsville Beach, N.C., begun 11/70/67	Unpainted	3 months	0.027
		12 months	0.033
		27 months	0.042
16 in. X 1 in. wide transition strip; welded on stern area of SS American Legion behind stack area, begun 6/18/68 ^d	Completely painted ^c	12 months	None
		34 months	None
	Aluminum panel unpainted; steel panel and transition joint painted ^c	12 months	None
Continuous 5's salt spray test ASTM B-117/57T	Unpainted	12 months	0.033
	Painted ^e	12 months	None
	Painted ^e	1000 hr ^e	0.060
	Painted ^e	1000 hr	None

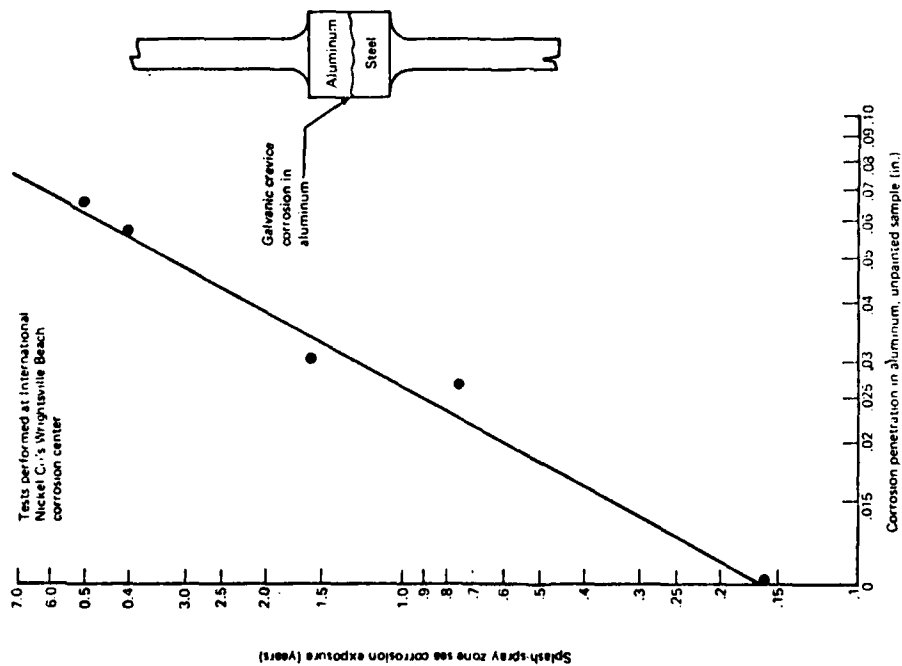
^aInformation from *Marine Technology*, July 1971.

^bPenetration is maximum depth in aluminum.

^cJoint consists of first coat zinc chromate vinyl paints, Pettit Paint Co., no. 8455 metal prime; second and third coats were oil-base paints.

^dOwned by United States Lines, work performed by Sun Ship Building & Dry Dock Co.

^eSixteen hours of testing is considered comparable to 1 year exposure in the Detroit, Michigan environment.



Initial samples demonstrated the corrosion resistance of the bond zone. The initial corrosion product, hydrated aluminum oxide, occupies a larger volume than the aluminum consumed and acts to seal the area from additional corrosion (Reference (9)).

An identical series of corrosion tests for painted samples is currently being conducted in conjunction with the unpainted samples. The painted samples were scratched across the bond zone to simulate localized paint failure. No significant corrosion or pitting was noted after 27 months of continuous testing (Table 11).

MECHANICAL PROPERTIES

Mechanical property tests have been conducted by Du Pont (Table 12); Boeing (Reference (10)); and the Naval Ship Research and Development Center (NSRDC) Reference (11). Results of these tests are documented by the respective agencies. Results of these tests and the fatigue tests conducted by Du Pont (Table 13 and Reference (12)), can be summarized by the following:

- a) Explosive bonded samples meet or exceed the claims made by the manufacturers.
- b) Fracture along the aluminum-to-steel interface of a composite could not be induced by shear or tensile stress if applied evenly to both sides of the bond on equal and continuous areas.
- c) Fatigue tests yielded no failures in the bond zone.
- d) Continuous salt-spray corrosion tests and user contacts show the material to be acceptable for use in the saltwater environment with only minimal maintenance.
- e) Use of clad materials is a cost-effective method of fabrication and in many cases offers an attractive alternative (Table 14 and Reference (13)).

SUPERSTRUCTURE/DECK INTERFACE

One major structural area where galvanic couples have caused problems has been in the attachment of aluminum superstructure to primary steel-hull structure. The initial methods for this attachment involved applying primers and sealants to the faying surfaces, fastening with steel lockbolts, and fillet sealing. This method has proved troublesome from a maintenance standpoint as sea action has caused fasteners to shear or loosen.

A typical installation of Du Pont's Detacouple as a transition joint for aluminum deckhouse to steel deck joints is shown in Figure 18 (Reference (13)).

INSTALLATION COST STUDIES

Installation cost studies conducted by Hunter's Point Naval Shipyard in 1972 reported the installation cost using Detacouple to be lower than a similar joint made with lockbolts (Table 15). While the initial costs for first-time installation show only a 14% savings over the lockbolt assembly method, it is their estimate and opinion that an additional 10% saving will result from (1) reduced forming costs for the Detacouple with the use of dies, (2) greater efficiency by mechanics as they

TABLE 12
MECHANICAL TESTING OF EXPLOSION-BONDED TRANSITION JOINTS^a

Description of test and specimen	Specimen condition	Results	Remarks
Standard ram tensile, testing 1100 aluminum/A 516 gr. 55 steel interface	As clad As welded ^b	20,000 psi typical ultimate tensile 15,000 psi typical ultimate tensile	Broke at 1100 aluminum/steel interface Broke at 1100 aluminum/steel interface
Extended ram tensile, testing strength of the 1100 aluminum interlayer	As clad As welded ^b	18,500 psi typical ultimate tensile 13,500 psi typical ultimate tensile	Broke in 1100 aluminum Broke in 1100 aluminum
Triple-lug shear ASTM A 263	As clad As welded ^b	14,000 psi typical shear stress 11,000 psi typical shear stress	Shearing of the 1100 aluminum Shearing of the 1100 aluminum
Welded tensile; 1/4-in. thick 5456 aluminum plate welded to 1-in. transition joint welded to 1/4-in. mild steel	As clad and welded	51,600 psi typical ultimate tensile	Failed in 5456 aluminum plate at heat-affected zone
Charpy V ASTM A 370 Testing A-516 steel	Specimen cut from steel portion of clad parallel to interface (a) Notch in steel below bond zone (b) Same as above but notch at underside of steel	60-130 ft-lb 70-130 ft-lb	All tests carried out at 15° F ^c
IZOD (unnotched) 1/2-in. 1100 aluminum 1-1/2-in. 1008 steel	As-clad sample cut perpendicular to plane of clad Grip on steel, impact on aluminum	Tearing of aluminum	No debonding or separation of the aluminum/steel interface
Drop weight test, E-208-66T, type P-2; 1/2 in. 1100 aluminum on A-516 gr. 55 steel	As clad	NDT-15° F	No debonding and no crack propagation into the aluminum layer
Shear test (A-263) after thermal cycling between 500° F and water (80° F), 2500 cycles; 1/2-in. 1100 aluminum/1-1/2-in. 1008 steel	As clad	14,000 psi typical shear strength	

^aInformation from *Marine Technology*, July 1971

^bHeat treated at 600°F for 1/2 hour in air to exaggerate heat during welding. Decrease in strength is due to partial annealing of the 1100 aluminum.

^cTypical requirement for shipboard application is 15 ft-lb at 15° F.

TABLE 13
FATIGUE TESTING EXPLOSION-BONDED TRANSITION JOINTS
AND MECHANICAL CONNECTIONS^a

Specimen type	Size (in.)		Loading per linear inch (lb) ^{b, c}		Cycles to failure	Remarks
	Thickness	Width	Tension	Compression		
Mechanical connections Four rivets Six rivets Explosion-bonded transition joints ^e	1/4	3-1/2	1250	3750	31,600	Rivet failed
	1/4	5	1250	3000	63,300	
	1/4	2	1250	3750	395,000	
	1/4	2	750	2560	1,267,400	Fractured in heat-affected zone of 5456 aluminum weld
	1/4	2	250	3750	721,500	

^aInformation taken from *Marine Technology*, July 1971

^bTests performed Budd Co., Philadelphia, Pa., by means of a Krouse double direct stress testing machine at 800 cpm.

^cSince the tension and compression stresses on the transition joint cannot be directly correlated with shear stresses on the rivets, data are presented in actual load per running inch. By holding the aluminum and steel thickness constant, data comparing actual operating capabilities are obtainable.

^dSpecimens consist of 5456 aluminum joined to HY 80 coaming using 3/8-in. CRES rivets. Specimens fabricated by shipyards using standard production procedures.

^eTransition joint strips were 1 in. X 2 in. X composite thickness welded to 5456 aluminum and HY 80 coaming using the 4- to-1 design ratio.

TABLE 14
COMPARATIVE MAINTENANCE AND REPAIR ASSOCIATED WITH MECHANICAL FASTENING
VERSUS DETASTRIP FOR ATTACHMENT OF ALUMINUM DECK HOUSES TO STEEL DECKSA

Maintenance problem or type of repair	Lockbolt fastening technique	Detastrip fastening technique	Comparative costs
Galvanic corrosion at aluminum/steel interface	There may be serious damage where the insulation is broken; repair involves dismantling, cleaning, and reassembly; damage not readily detected.	Normal ship's painting should provide adequate protection; in addition, corrosion tests indicated there would be no significant damage in case of paint failure; initial corrosion easily detected.	The Detastrip method offers potentially large savings in this area; in general, repairs will not be needed; paint failures will not be easily repaired requiring only simple cleaning and repainting; ease of detection and proper maintenance should prevent extensive repairs.
Corroded steel coaming in areas where moisture hinders maintenance	Requires replacement of coaming; involves disassembly of joint, removal of coaming, fitting new coaming, drilling holes, and reassembly.	Requires replacement of coaming; generally flame-cut coaming 1 or 2 inches below Detastrip, remove coaming, and install new coaming as if installing a patch.	Detastrip repairs should be much cheaper due to savings in labor (both removal and reinstallation) and savings in material costs.
Replacement of steel coaming and aluminum bulkhead due to structural damage (such as fire, collision, etc.) or corrosion at aluminum/steel interface	Requires removal of damaged area and replacement with new material.	Requires removal of damaged area and replacement with new material.	Removal costs will be approximately the same; reinstallation costs should reflect the 24% savings as determined for initial installation.
Replacement of aluminum due to corrosion at aluminum/steel interface	Sometimes required at interface where severe corrosion has taken place before detection; requires dismantling, fitting new aluminum section, drilling new holes, and re-assembly.	This repair is not anticipated for the Detastrip method of attachment due to its expected durability (based on corrosion test).	This type of repair will not be required with the Detastrip method thus providing significant improvement and savings over mechanical fastening.

^aInformation from "Fabrication Cost Comparison Study," project 2-0094 Quality Assurance Office, Hunters point Naval Shipyard.

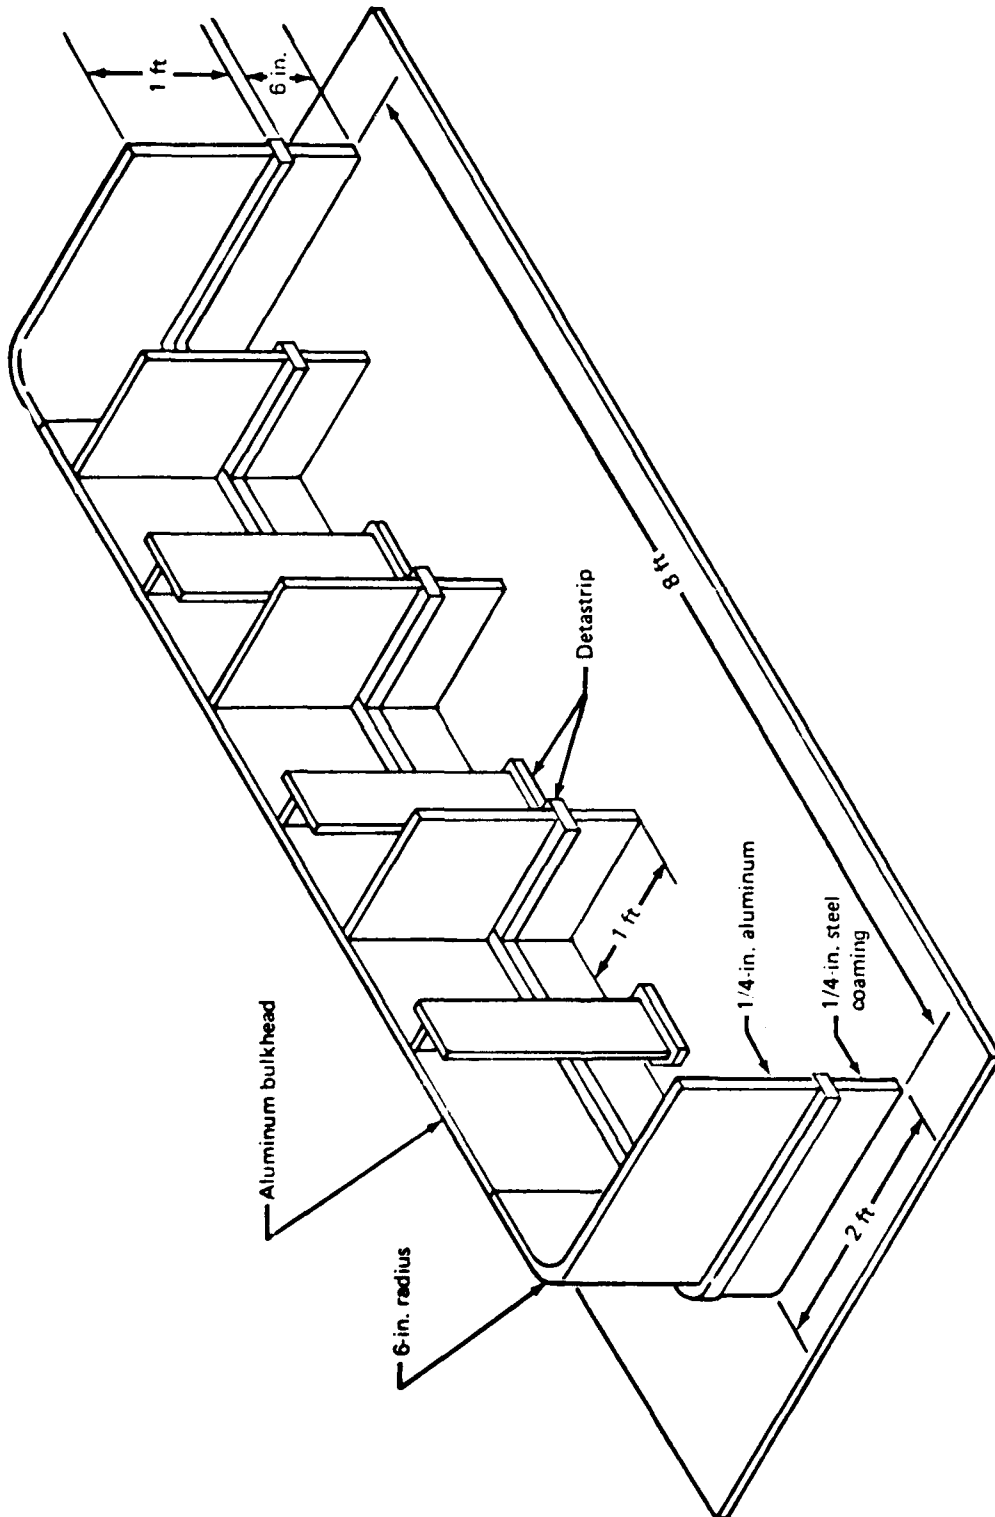


FIGURE 18
DECKHOUSE MOCKUP—ALUMINUM/STEEL TRANSITION JOINTS

TABLE 15
ALUMINUM DECK HOUSE FABRICATION COST ANALYSIS^a

Item	Labor in manhours per linear foot			Estimated Boeing Costs
	Shop	Lockbolt	Detastrip	
Loft templates	11	0.09	.080	\$0.09
Duplicate loft templates	11	0.02	.070	0.08
Fabricate steel coaming	11	0.17	.100	0.17
Drill holes (3/8 inch holes, 18/linear foot)	11	1.08	N/A	0.64
Install gasket material	11	0.02	N/A	N/A**
Install lockbolt (18/linear foot)	11	0.90	N/A	0.02
Cut to length and bevel (Detastrip)	11	*N/A	.110	N/A
Form Detastrip (radius corners)	11	N/A	.067	N/A
Fit up Detastrip (align)	11	N/A	.359	N/A
Fit up Detastrip (tack)	26	N/A	.164	N/A
Weld Detastrip to coaming 1/4 inch	26	N/A	.184	N/A
Weld Detastrip to BHD 3/8 inch	26	N/A	.365	N/A
Weld tee joint (Detastrip)	26	N/A	.109	N/A
Weld butt joint (Detastrip)	26	N/A	.067	N/A
Weld stiffener to Detastrip (aluminum)	26	N/A	.034	N/A
Drill holes (3/8 inch holes 12/stiffener)	11	0.11	N/A	0.43
Install lockbolts (12/stiffener)	11	0.10	N/A	0.01
Straight bulkhead, Detastrip welded	11	N/A	.280	N/A
Total manhours/linear foot		2.55	1.989	1.44
Labor cost at \$12.00/manhour/\$10.50 (Boeing)		\$30.60	\$23.89	15.12
Material		\$12.60	\$13.22	12.60
Total cost/linear foot		\$43.20	\$37.11	\$27.72
Savings per foot: \$43.20 - \$37.11 = \$6.09/linear foot/\$15.48 per linear foot Boeing				

- Note:**
1. Detastrip fabrication values were obtained from direct time study of a mockup per code 138 sketch MFI 48-72.
 2. Values for lockbolt fabrication were obtained from "E" standards 383.2-0517, 0543, and 0612.
 3. Boeing estimates for lockbolt installation were conducted by Industrial Engineering and based on the production capabilities and labor cost at Boeing.

Hole preparation with Quackenbush QOA-11 to drill ream, countersink, and apply SRF and install cadmium-plated sheet lockbolt in standard manhour (SMH) is:

Item	Per hole	Per foot	Per stiffener
Hole preparation	0.0356 SMH	0.64 SMH	0.43 SMH
Fastener	0.0001 SMH	0.02 SMH	0.01 SMH
Total		0.66 SMH	0.44 SMH

*N/A - Not applicable

**N/A - Note: If two coats of BMS 10-11 H(SRF) type 1 are used, no gasket material would be required.

^aInformation extracted to include Boeing cost estimates from Hunter Point Naval Shipyard report 2-0094, and modified

become familiar with this fabrication method, (3) use of mechanized welding to reduce welding cost, and (4) greater overall efficiency for all operations due to refinement in production sequences and techniques (Reference (13)). It could also reduce costs by eliminating requirements for stocking lockbolts and purchasing the tooling required for their installation. This test represented a first-time use of Detacouple compared to 12 year's experience using mechanical fastening techniques. Boeing Industrial Engineering has conducted a similar cost analysis of the lockbolt joining method. Using the tooling data from the Hunter's Point study, the total installed cost per foot of lockbolts is \$27.72. Use of aircraft fabrication techniques results in savings of 36% when compared with the shipyard installation of lockbolts.

Tacoma Boat Building Company, Tacoma, Washington indicates a man-hour labor saving of \$5.00 per foot when using 345 feet of Detacouple to attach the aluminum deckhouse to steel deck on a tuna seiner. (This figure is based on labor rates only and does not include material cost. Cost studies indicated deckhouse fabrication rates to be 7.3 feet per hour for Detacouple as compared to 3.6 feet per hour for similar lockbolt installation methods.) The customer benefits from lower fabrication costs in addition to lower maintenance requirements (Reference (14)).

MACHINERY AND EQUIPMENT ATTACHMENT

Two areas subject to galvanic corrosion in aluminum structure involve outfitting and systems attachments. These areas encompass everything from the mounting of deck machinery to the attachment of nameplates and operating instructions.

Due to strength considerations, cost, and availability, most deck machinery is fabricated from steel and iron. While this does not present a problem in conventional steel ship construction, it does compound problems when the same equipment is attached to aluminum structure.

The current method of attaching steel deck machinery and related equipment to aluminum structure requires the use of primers, leaded paints, neoprene gaskets, sacrificial pads, phenolic bushings, and liberal applications of sealant around joints. This method is not only time-consuming, costly, and inefficient, but also requires repeated applications when sacrificial pads corrode or paint and sealant are damaged.

An alternate method to this approach, still allowing the use of conventional deck gear, would be to use the bimetallic sheets as pads to interface the steel machinery to the aluminum deck. With this approach, the deck machinery could be welded or mechanically fastened directly to the deck through compatible materials and would not require costly maintenance. Several suggested applications of explosion bonded materials are shown in Figure 19.

The Alcoa deep-reaching oceanographic research vehicle, Seaprobe, uses Detacouple mounts to attach equipment supports to the aluminum structure.

Northwest Technical Industries, Inc. (NTII) is currently working with Boeing to produce a reinforced explosive-bonded aluminum skin for the Space Shuttle program. Eight by 10-foot sheets of 2219 aluminum have had 12-inch-square plates of 2219 aluminum explosively bonded in places where cutouts will be made in the skin. These plates serve as reinforcements and eliminate the need for steel reinforcing doublers or thick plate sculpturing and machining.

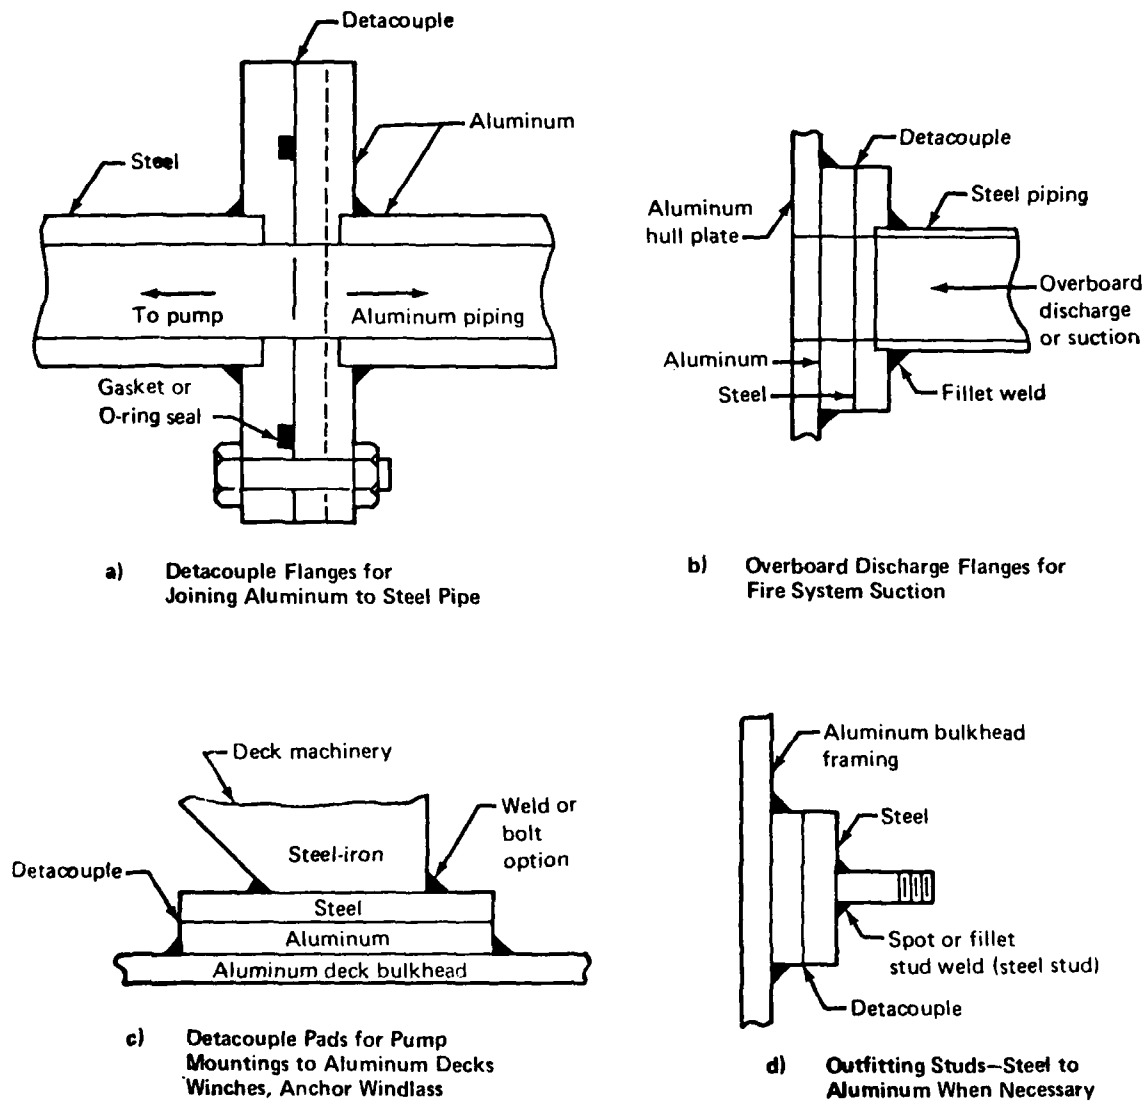


FIGURE 19
PROPOSED BIMETALLIC APPLICATIONS

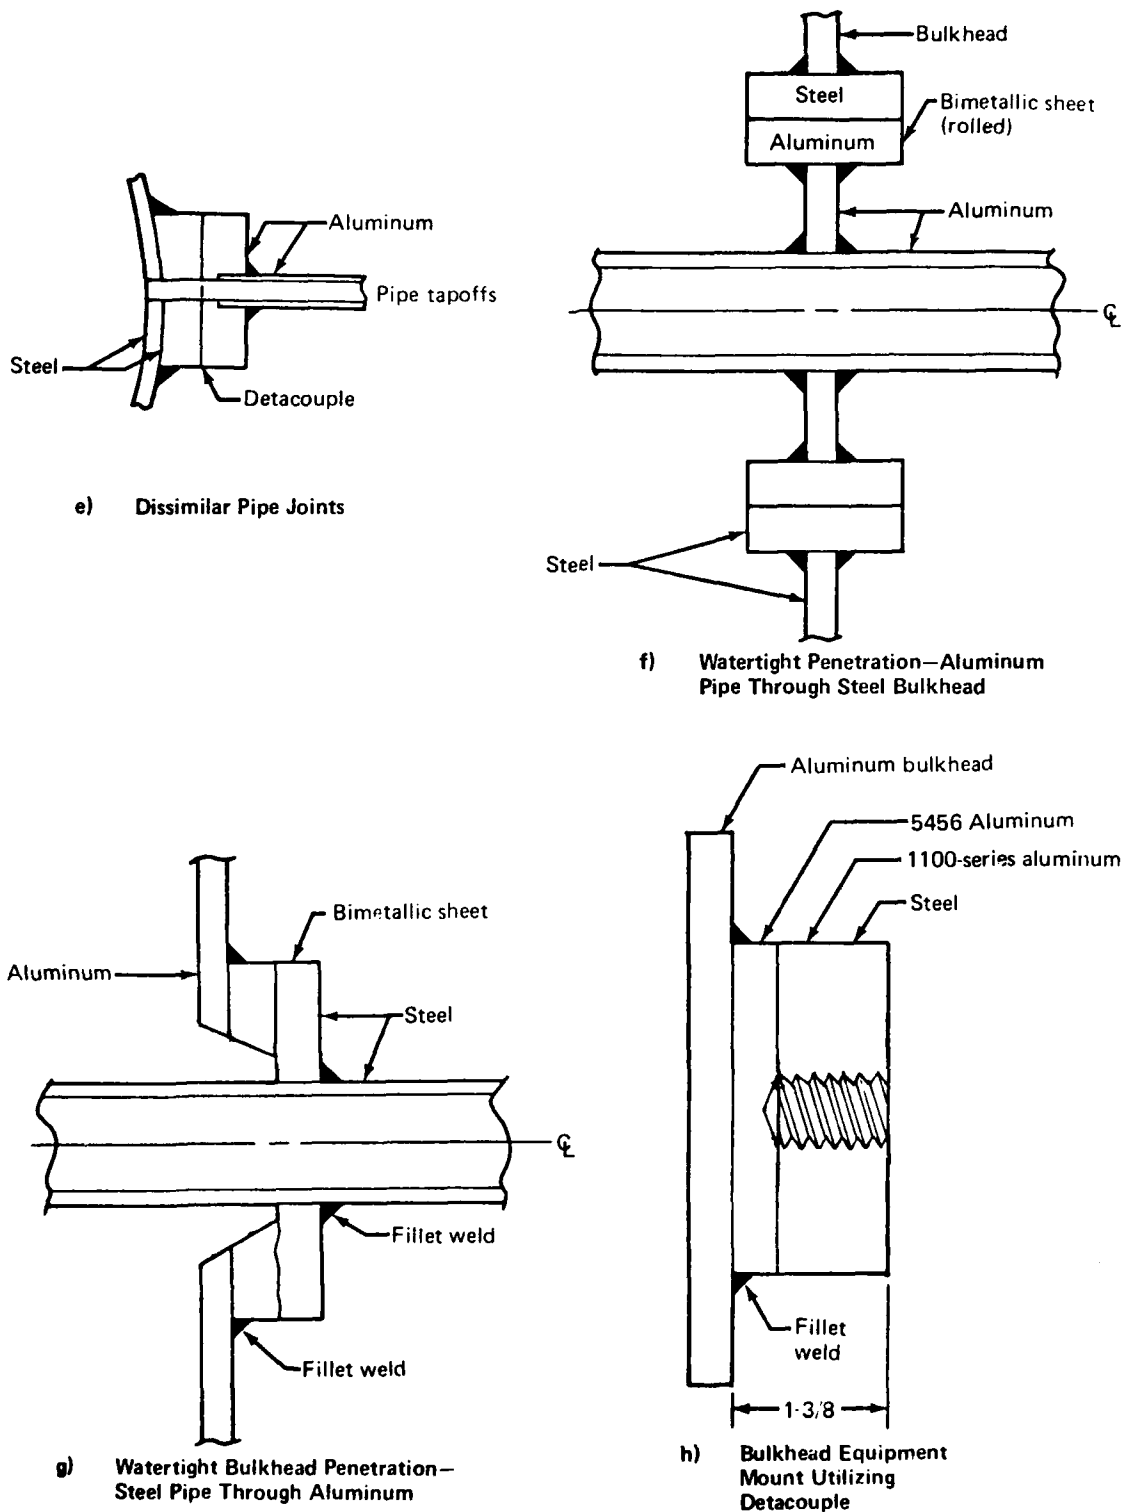


FIGURE 19 (CONCLUDED)

NTII also produces chill bars used for welding thin-gage aluminum by explosively bonding copper and aluminum. Thinner copper blocks are used over the standard solid copper block, thus lowering the cost of the chill bars.

The current design and development effort by Pittsburgh-Des Moines Steel and General Dynamics to fabricate liquid natural gas tankers uses Detacouple in attaching the steel support skirt from the primary structure to the 25,000-cubic-meter aluminum LNG spheres (References (15) and (16)).

III. ADHESIVE BONDING

The demand for high-performance military aircraft, reliable commercial transportation, and strong lightweight space vehicles has hastened the development of lightweight, high-strength-to-weight-ratio honeycomb sandwich panels and structures. Bonded honeycomb sandwich materials are incorporated into aircraft as flight control surfaces (flaps, ailerons, and rudders), as acoustical attenuating structures on turbine inlet and exhaust ports, or as insulating walls of cryogenic tanks of space vehicles.

Information on the thermal properties, structural limitations and applications, and fatigue resistance of adhesive-bonded structure is available through government agencies such as the Air Force and NASA. Sections of the Boeing Design Manual, Section 26, on adhesive bonding have been included with this report for reference (Appendix I).

The state of the art in adhesive bonding in the aerospace industry has progressed significantly in the past 20 years. Advances in polymer chemistry have made possible the development of new adhesive systems with high strengths, good environmental resistance, excellent manufacturing properties, and moderate costs. The ultimate performance of the adhesive systems are highly dependent on the surface preparation process of the materials to be bonded. Materials such as wood, GRP, or glass may be prepared for bonding by a simple solvent wipe and/or light abrasion. Consistent, high-quality bonds in metal surfaces normally require a chemical-immersion-type prebond treatment. The state of the art of surface preparation for aluminum is far more advanced than for other metals such as steel, titanium, or magnesium. (The highest percentage of adhesive-bonded structures in aerospace applications involve aluminum alloys.) New full-curing chromated adhesive primers allow long-time storage (up to 12 months) and handling of parts to be bonded before final curing; they also provide much improved environmental resistance in the bond facing surfaces. Although bonding directly to a steel surface is not generally considered a good adhesives application, bonding to a chromated primer on an abraded steel surface should provide acceptable results for secondary structural applications.

Adhesive bonding of steel has not received as great an emphasis because of its lower strength-to-weight ratio as compared to aluminum or titanium. In general, low-carbon steels are normally sand-blasted or vacu-blasted with aluminum oxide particles to remove lubricants and scale prior to bonding. As indicated above, a good chromated primer may then be applied or if the adhesive system to be used has a primer system of its own, it should be applied. The more common adhesives like the epoxies, phenolics, nitrile-phenolics, etc., normally have primer systems that provide better wetting of the surfaces to be bonded. Considerable evaluation of chemical treatment of steel to prepare the surface for bonding has been performed recently, primarily on AISI 300-series stainless steel, but also on low- and high-carbon steels and high-strength

alloy steels. Most of the treatments are satisfactory for bonding where the stress levels are quite low and are pointed primarily at nonstructural applications such as rub strips and fire shields. To bring the confidence level in bonded steel up to the level that prevails for aluminum, an extensive test program would be necessary. Such a program must consider surface treatment and long-term exposures (15-20,000 hours) in high humidity and salt spray and also at intended operational temperatures. The bonded specimens should be exposed to the various environments while under stress to obtain the most meaningful results. This type of testing necessarily is expensive and requires an extended test schedule.

Adhesive bonding can be considered as a fastening technique for noncritical, structural applications, especially on the newer type ships such as hydrofoils and surface-effect vessels where aluminum structures are more common. Even on steel structures, however, adhesive bonding can be used to an advantage over classical welding or mechanical fastening techniques, especially where dissimilar materials are involved. The adhesive provides an excellent barrier between the dissimilar materials to prevent galvanic corrosion. Two-part adhesive systems can be used to provide very short cure cycles--as short as 2 minutes--or thermosetting materials can also be used with short applications of heat in the 300°-400° F range for cure. Bonding pressure can be supplied through mechanical clamping devices, simple vacuum bagging techniques, or through clamp-up pressure supplied through the use of bolt-type fasteners that can be removed after the adhesive is cured or be retained in the assembly. For example, the flanges on noncritical duct work or piping can be bonded together when they are installed. Either two-part or thermosetting adhesives can be used. If a thermosetting adhesive is used, heat lamps or an electric blanket or heated pads on mechanical clamps can be used to cure the adhesive. Pressure can be supplied through clamps or fasteners through the flanges. The fasteners can be removed after the adhesive is cured or left in place unless dissimilar materials are involved and then could still be used if some dielectric jacket material were used to separate the dissimilar materials. Bond strengths from 1,000 to 5,000 psi in shear or flatwise tensile can be developed, depending on the specific adhesive materials used and/or the particular means of cure and pressure application.

Generalized statements on adhesive applications cannot be made. Each particular type of structure, material combination, fabrication sequence, etc., requires individual consideration to obtain the optimum physical properties from the materials as well as the most economical cost.

With the exception of the chemical processing requirement for surface preparation of aluminum, most two-part adhesives and the fast-curing thermosetting adhesives can be handled and applied in normal shipyard conditions. Personnel working with the adhesive materials must be trained in their handling, application, and curing. Written instructions alone should not be considered adequate.

Another consideration for adhesive bonding as a fastening technique is the joining of noncritical structural parts rather than welding or using mechanical fasteners. For example, nonstructural bulkheads fabricated as skins with welded or riveted stiffeners could be changed to adhesive-bonded stiffeners or have honeycomb sandwich structure substituted in their place. In addition to bulkheads, modular-type divider panels in crew quarters or office spaces on large ships, partitions in heads, galley cabinets, decorative interior panels, and some types of floor structure all lend themselves to bonded sandwich-type structures. This is especially true in aluminum structure. It is also assumed that the newer surface-effect ships or hydrofoil

ships are more weight-critical than some of the larger, steel-hulled ships, and the higher strength-to-weight ratio of bonded sandwich structure could prove advantageous.

Since many of the newer ship designs are powered by gas turbine engines, sonic fatigue of the structure closely adjoining the powerplants can be a problem. Bonded structure is often superior in sonic fatigue resistance compared to conventional structure. Interior paneling, whether decorative in nature or as nonwatertight bulkheads, can be fabricated from bonded sandwich and be both light in weight and low in cost. Also associated with the gas turbine powerplants is consideration of acoustical treatment of both the inlet and exhaust areas to lower the powerplant noise level as much as possible. Bonded acoustical sandwich panels have not become very widely used on commercial jet aircraft in structural areas due to the permeability of adhesives to moisture. Here again, generalized statements about the overall applicability of the bonded structure is usually not feasible from a cost standpoint, since more tooling is normally required than would be needed for welded or riveted structure. An exception would be the application of standard module sizes for bonded partitions, but if some amount of duplicate production is involved, then tooling costs of bonded structure can be amortized. Consideration of each structure must be analyzed on an individual basis.

If studies show definite cost or installation advantages for bonded structures, related studies should be made to determine whether subcontracting the fabrication is more cost effective than equipping existing shipyards to fabricate on site. The decision to make or buy finished honeycomb sandwich structure is one of economics. The size and quantity of parts will determine the physical plant dimension required to fabricate bonded structure. In addition to this, the personnel needed to provide finished parts are of skills not commonly found in shipyards and would have to be trained. In-process controls and the necessary nondestructive test equipment will have to be included in the final analysis. The equipment required for a typical bonding facility for aluminum structures is shown in Appendix D.

IIF. WELDING

The advancements made in the art of welding ships are historical and well documented. It is sufficient to say that advances in welders, automated panel fabricators, and welding equipment and improvement of flame cutting techniques have advanced the state of shipbuilding severalfold. Numerous publications on cost and time savings studies have been conducted to establish the merit and economics of the aforementioned equipment, so further elaboration on these advancements will not be made here.

DISTORTION

One problem causing considerable difficulty and expense to shipbuilders is distortion caused by the welding of thin plate in secondary structure. Some shipbuilders design for heavier plate than structurally needed to reduce distortion problems. This practice may prevent some of the distortion, but its effect of adding additional weight, fabrication, and material costs would seem to open considerations of alternate approaches. Proposals for using riveted points in thin plate have been discussed in the mechanical fastening section of this report and will not be reiterated here.

FRICTION WELDING

Interest has been expressed in using friction-welding techniques to projection-weld studs in aluminum structures. As a result of investigation, the friction-welding techniques are not recommended. The required thrust value to friction weld a 1-inch-diameter bar of 6061 aluminum is approximately 7,000 pounds. This is in addition to the torque parameter also required. Such forces could not be exerted by manual application; however, friction welding has proved to be a satisfactory method of joining dissimilar metals with machine application.

DISSIMILAR METAL JOINTS

Several methods of joining dissimilar metals have been advanced. Generally, the research and development that went into these methods was aimed at satisfying particular needs such as tanks and vessels for corrosive and cryogenic propellants and fluids.

The Space and Information Systems Division of North American Aviation has advanced the field of dissimilar metal joining. Their primary interest is oriented toward large boosters and space vehicles. Their studies indicate that, while entirely feasible and practical, many combinations joined by welding or brazing result in brittle phases that are sensitive to shock and exhibit inferior mechanical properties. Aluminum-to-steel brazed joints are examples of this characteristic.

Table 16 lists a number of dissimilar materials that have been joined by several different techniques and processes. Again, these examples reflect the aerospace application and are included as information only.

STUD WELDING

In addition to fusion welding, the resistance-projection-stud-welding technique affords the contractor a flexible method of systems installation and attachment in steel structure. Projection-stud welding offers the most cost-effective method of installing support bracketry. To attempt to replace this system today with a mechanically fastened joint would not be cost effective.

Advancements in stud-welding techniques are available on a commercial basis. For example, the Nelson Electric Company produces marine cable and pipe-changer supports for a range of pipe and cable sizes as well as the necessary stud welder. Once the stud is welded into position, the cable clamp is threaded on the stud and crimped around the cable. The pipe hanger is welded directly to the bulkhead and is available in various lengths, or a channel stud is welded in position with an adjustable strap and carriage bolt. The pipe hanger uses a rubber insert between clamp and pipe for vibration dampening. Once the pipe is installed, a locking tab is inserted and bent over, retaining the pipe and insert. This system would facilitate adding or subtracting pipes of different sizes.

RECENT DEVELOPMENTS

In recent years, both shipbuilding and aerospace industries have expressed continued interest in processes such as plasma arc, electron beam, and laser applications. The need has been generated by specific product applications such as heavy plate welding for deep submersibles and titanium airframe structure.

TABLE 16

NAA DISSIMILAR-METAL BONDING PROCESSES

Union	Procedure
Aluminum to stainless steel	Dip-braze after tin-coating the stainless steel.
Aluminum to stainless steel	Solder after nickel-plating the aluminum.
Aluminum to stainless steel	Diffusion-bond after interface coating application.
Stainless steel to molybdenum	Vacuum-braze.
Titanium to aluminum	Solder after nickel-plating nickel on titanium and aluminum.
Copper to nickel	Diffusion-bonding after tin soldering.
Aluminum to stainless steel	Dip-braze after silver-plating of stainless steel.
Aluminum to beryllium	Direct dip-braze.
Stainless steel to beryllium	Vacuum-braze.
Columbium to molybdenum	Diffusion-bond honeycomb sandwich
Columbium to stainless steel	Inert-gas braze.
Tungsten to titanium	Tungsten-ARC inert-gas braze with aluminum brazing alloy.
Tungsten to copper	
Tungsten to stainless steel	
Tungsten to aluminum	
Titanium to aluminum	
Titanium to stainless steel	Resistance-weld-machine braze.
Tungsten to molybdenum	Electron-beam weld
Molybdenum to columbium	Electron-beam weld
Molybdenum to stainless steel	Electron-beam weld
Nickel wire to copper wire	Capacitor-discharge-resistance microweld
Stainless steel to low-alloy steel	Percussion-stud weld.

IIG. MECHANICAL BONDING

Mechanical bonding is a general term that is applied to three separate processes. These being diffusion bonding, deformation bonding, and roll bonding.

The diffusion bonding process essentially takes place in two stages: (1) microscopic plastic deformation results in intimate metal-to-metal contact and (2) diffusion completes the bond and ultimately eliminates the interface. Stage 1 plastic deformation is due to the limited metal-to-metal contact caused by surface roughness and contaminations, as no real surfaces are atomically flat. Applied bonding loads are borne by the "high" point of the surface irregularities. Sustained loading causes continued plastic deformation until the net area of surface contacts approaches the gross bonding area and bonding occurs, stage 2.

Deformation bonding involves gross plastic flow (30% to 60%, depending on alloys and temperatures), which promotes intimate contact and breakup of surface oxides. Plastic flow is accomplished by mechanically rolling the sheets to be bonded. The rollers supply the forces necessary to achieve plastic flow. Deformation bonding is conducted at room temperatures.

As aluminum alloys form tenacious refractory oxides, the usual and most successful methods of static diffusion bonding use a eutectic material between the aluminum sheets. These bonding processes require consideration of surface conditions, alloy compositions, temperature, prior coldwork, crystallographic orientation, post-heat treatments, and joint design.

Roll bonding is similar to diffusion bonding but does not employ a eutectic material as is used in diffusion bonding.

Both diffusion and roll bonding are time, temperature, and pressure controlled. Roll bonding requires higher pressures and temperatures and a shorter time for processing than the diffusion process.

At cryogenic temperatures (-423°F), the bond becomes stronger due to shrinkage, but when raised to elevated temperatures (960°F) and quenched, the irregularities holding metals together shear, thereby reducing the shear properties of the overall joint.

For shipyard applications, these bonding processes would not represent a cost-effective approach to dissimilar metal-to-metal joints. This is partly due to the limited applications available, limited quantities produced, and the cost of equipment necessary to complete the processes.

III. CONCLUSIONS AND RECOMMENDATIONS

1. Mechanical fastener systems have had and will have continued application in ship construction. Their major areas of application have been in secondary structure and system attachments. The modern fastener systems available today have demonstrated their performance in structural, fatigue-critical, and fuel-tight joints and other special applications. The merits of some of the newer fastener systems

in shipbuilding applications remain to be demonstrated. Families of high-strength, corrosion-resistant, fatigue-rated fasteners are available for implementation into ship designs as well as for special applications such as those required for use with honeycomb sandwich panels.

Conventional rivets can be employed in some areas to replace welding of thin sheet and plate. Flush-head rivets can be used to attach thin-sheet aluminum panels to stiffeners and stringers and can be installed in drag-critical areas where flushness control is mandatory.

The welding of thin plate (less than 3/8 inch) creates distortion problems that can be reduced by conventional riveting, which is also one of the most cost-effective methods of joining, where necessary. Rivets are easily removed and replaced with simple pneumatic drilling and riveting equipment.

2. Explosion-bonded metals have much to offer in the design and construction of ships, particularly those with mixed aluminum/steel structure where galvanic incompatibilities occur.

Bimetallic and trimetallic materials can be formed or machined into various shapes and configurations and offer good corrosion resistance, as shown by 5 years of continuous sea-water tests. Physical-property tests and structural testing have verified the integrity of explosion-bonded joints. Tests conducted by the Naval Ship Research and Development Center led to their recommending the use of these materials in the construction of naval combatant vessels.

Comparative installation tests conducted by Hunter's Point Naval Ship yard and private shipbuilding yards have shown the explosion-bonded materials to be a cost-effective method of making dissimilar metal joints (superstructure to deck).

3. The current method of systems installation in steel structure is projection stud welding. Currently, there is not a more cost-effective method of attaching equipment supports. Projection stud welding equipment and related bracketry are available commercially.

Stud welders for welding aluminum studs are commercially available for studs up to 1/2-inch diameter. Due to weight considerations of support equipment and the lower yield strengths of aluminum, the use of this type of equipment is somewhat limited. An alternate process to aluminum stud welding (as recommended by Nickum and Spaulding of Seattle and as presented in the explosive bonding section of this report) uses the bimetallic strip welded with the aluminum to aluminum and the steel stud projection welded to the steel side of the bimetallic strip. While more expensive, the reliability of the bimetallic-stud weld joint should reduce later repair or replacement costs.

Some questions arise concerning the effects of localized degradation in the structure caused by stud welding. The effects of the primer (often applied before welding) and other impurities as well as residual stresses in and adjacent to the weld area are causes for concern. The latter will become increasingly pertinent as operating stress levels approach design limits.

4. Adhesive bonding, as applied in aircraft, has been limited primarily to aluminum and titanium, due to weight considerations. Aircraft contain a wide range of

bonded material applications, ranging from control surfaces to galleys and decorative panels. These applications do not include primary structure nor would they be recommended for primary structure in shipbuilding. However, adhesive bonding can be applied to some nonstructural applications. The areas of potential application include interior bulkheads, kitchen and toilet facilities, low-pressure piping and ducting, acoustic insulation for sonic fatigue, or areas of high-frequency vibration.

Adhesive bonding and sandwich panel construction lend themselves to modular construction and have been used as deckhouses on patrol craft produced by foreign nations. Adhesive-bonded sandwich panels and construction offer a high strength-to-weight ratio for numerous applications.

IV. RECOMMENDED AREAS FOR FURTHER STUDY

It is anticipated that those interested in ideas or concepts presented in this report will conduct the necessary qualification tests before incorporating them into their design and construction efforts. The following are delineated as areas for further study:

1. Compile a fastener matrix and preferred fastener list based on fastener types approved for use in ship design. Develop design allowables and add to the list and matrix, as required, to accommodate new applications. Take care to avoid excessive fastener proliferation.
2. Investigate the use of conventional riveting for attachment of thin sheet in secondary structure and application of high-strength fasteners to primary structure.
3. Continue to develop the full potential of the explosive-bonded bimetallic and trimetallic sheet. This effort should include tube cladding techniques for rudder stock and stern-tube installations, bulkhead penetrations, pipe flange connections for dissimilar pipes, and deck pads for equipment mounts.
4. Investigate cost-effective approaches to installing mixed materials for pipe systems that would satisfy necessary regulations.
5. Study potential applications for the electromagnetic riveting process, particularly in areas where large rivets may replace more expensive fasteners. The portability of the equipment and quality of EMR-installed rivets make large rivets more attractive than they have been in the past. The process is usually cold but can be supplemented by resistance heating of the rivet.
6. Consider possible applications for items in Appendix E such as in-place tube welder, laser alignment, and new bulkhead penetrations.
7. The logical step to follow a study of this type is a developmental activity encompassing the design and fabrication of selected joint hardware to assess and validate the comparative advantages of different joining methods. For example, welded versus mechanically fastened joints for a given application should be compared, each designed for use with its unique joining process.

8. Similarly, material trades in selected applications can be evaluated with the design of a selected joint for steel, aluminum, and combinations using explosive-bonded strips as the interface. Again, each should be designed to take advantage of the properties of the particular materials being compared.
9. Following the successful validation of some of the alternative fastening methods in test hardware, selected ships (or portions thereof) undergoing modification or those of a new design should be selected for incorporation of these concepts.

In-service experience can be monitored to validate the projected performance of the new designs and fabrication methods.

10. Based on the feedback from the foregoing (items 7 through 9) an integration program, including the incorporation of alternative joining methods into regulatory documents, should be pursued.
11. A study of current maritime regulations and specifications and their relation to bonded structure should be made to determine where bonded nonstructural components can be applied.

APPENDICES

The topics listed in the appendices, while not related directly to the main scope of the report, have been included and commented upon as information that may be of interest to those functioning in these fields.

Piping systems, which include bilge, ballast, and weather deck drains, as well as water, oil, and air systems, involve high costs for materials, initial installation, and subsequent maintenance. The ideas and suggestions are presented for consideration, and the cost effectiveness of these systems over a period of operating time remains to be established.

The adhesive-bonding equipment shown, represents typical equipment found in the aircraft industry. It is not necessarily optimum for shipbuilding applications. The economics of purchasing completed parts should be considered before making a capital expenditure.

The in-place tube welder described and shown in Appendix E was developed to weld high-pressure stainless steel and titanium tubing in limited-access areas where conventional welding techniques could not be applied. High-quality welds are obtainable on a production basis.

Electrical systems encountered in shipbuilding range from electric lights to radar installations. Combatant vessels are equipped with a variety of complex electronic systems outside of the regular ship electrical facilities. Hookup of these various systems often requires multiple watertight bulkhead penetrations as well as connections between components in close proximity to each other. Compartments and passageways are often cramped and crowded, presenting additional problems.

The use of Multi-Cable Transit units for tubing, pipe, and wire connections eliminates stuffing-tube arrangements and the necessity of potting and sealing to maintain the watertight integrity of each compartment. These processes add to the cost of ships, are time consuming to install, and make modification of systems difficult.

Flat cable affords the fabricator the opportunity for additional flexibility when installing instrumentation systems, especially those involving multiple connections between components. Flat cables can be used efficiently in limited-access areas such as passageways and along framing.

Laser optics, even though remote from the subject of fastening or outfitting, remain pertinent nonetheless. Laser optics have found increasing use each year. Critical alignment of major jigs and components have been possible with laser equipment. The application of laser alignment techniques to shipbuilding is evident when you consider its being applied to alignment of stern-tube boring equipment or to placement of deck machinery or keel and side plates. It is, therefore, included in the appendices of this report for information as to the current state of the art and the joint sharing of this technology between the different industries.

APPENDIX A

PIPING SYSTEMS

Piping systems currently installed on commercial and military shipping use steel pipes, both Schedule 40 and 80, and steel pumps with bronze bushings and fittings. Large gate and globe valves can become expensive without considering compatible systems made for use with aluminum (Table 17).

Current design practices call for waste washers to be installed when it is necessary for pipes to penetrate bulkheads for overboard discharges and pump connections. This practice causes higher costs for initial construction and subsequent operation in the electrolytic environment of seawater.

Regulations currently restrict the use of any nonsteel/iron pipe and pump systems in such areas as fire protection and control. Extensive tests are now being conducted by the Naval Ship Systems Command, Annapolis, Maryland, to verify new materials such as the intumescent coatings on glass-reinforced plastic piping. While these hold some promise for future use, the current regulations are explicit.

There are possibilities of using a mixed tubing materials system such as plastics for bilges, ballast, and weather deck drains; aluminum and/or stainless steel for potable water, compressed air, and engine oil; and alloy steel and 90-10 copper nickel for fire-control systems. The merits of these systems would have to be determined from cost-effectiveness and reliability standpoints.

While these systems may save weight and installation costs, the fluid prime mover will be predominantly the steel pump due to availability and cost considerations. Again, galvanic incompatibilities can occur, especially in nonferrous ships. Since the pump can be isolated by the same method as the deck machinery, the problem lies in connecting the pump systems to dissimilar pipe systems.

TABLE 17
COST COMPARISON FOR ALUMINUM ALLOY AND STAINLESS STEEL VALVES^a

Size IPS (in.)	Pressure service (lbs)	Type	304, 316, and 25 nickel-20 chrome stainless steel (\$/each)	356-T6 aluminum alloy (\$/each)
3 flanged	150	Gate	263.00	268.00
4 flanged	150	Gate	376.00	389.00
6 flanged	150	Gate	610.00	622.00
8 flanged	150	Gate	—	809.00
3 flanged	150	Globe	407.00	273.00
4 flanged	150	Globe	478.00	512.00
6 flanged	150	Globe	809.00	891.00

^aInformation taken from SSC report 281, p. 75.

TABLE 18
MATERIAL COSTS—BILGE SYSTEM IN BALLAST TANKS (U.S. DOLLARS)^a

Item	Aluminum	Black steel	Galvanized steel	Fiberglass- reinforced plastic	PVC lined
Specification	6061-T6	A53	A53	Bondstrand or equal	Resistoflex
Thickness	Schedule 40	Schedule 80	Schedule 80	—	—
2440 feet of 4-inch pipe	\$5,967	\$5,630	\$6,750	\$10,248	\$16,104
Aluminum bulkhead penetration (50)	5,967	5,630	6,750	10,248	—
Aluminum spools (40)	—	1,800	1,800	—	—
Flanges (70)	1,376	506	760	539	Included
Ells (150)	3,420	1,014	1,402	2,520	8,295
Couplings (36)	—	—	—	194	—
Valves (10)	—	Not included		—	—
Cathodic protection	—	1,720	1,720	—	—
Total cost	\$10,763	\$10,670	\$12,432	\$13,681	\$24,399

^aInformation taken from SSC publication 218, p. 78.

Several suggested methods of pipe-to-pump attachments, bulkhead feedthroughs, and pipe tapoffs fabricated from bimetallic stock are shown in Figure 19.

While an interested party would have to develop the necessary rupture and fatigue data, the concepts are practical and offer an attractive cost-savings potential. This process could eliminate the costs of waste washers and gaskets and minimize related maintenance, corrosion, and rust allowances made for steel pipes. Hence, thinner-gage pipes could be used. Limited use of the glass-reinforced plastic and PVC pipe has been recommended by the Coast Guard, predominantly in bilge and ballast systems. Cost analyses from SSC Publication 218, *Design Considerations for Aluminum Hull Structure*, are shown in Tables 18 and 19 for bilge and ballast systems.

Nondestructive test (NDT) procedures are available commercially for in-process controls of explosion-bonded materials. These included X-ray technique and dye-penetrant inspection of the bond join and weld bead.

APPENDIX B

WATER SYSTEMS

Two water systems are in common use for ship operation. These are the fresh potable water system for sanitary engine cooling and consumption purposes and a salt-water system for ballast. The potable water is from two primary sources: (1) on-board desalinization and (2) shore supplied. The salt system is ocean supplied.

For steel structure, there is no inherent problem with either water system other than rust. Black schedule 80 steel pipe is used predominantly. However, with aluminum structure, different problems arise--some chemical and some regulatory. If aluminum pipe systems are used for both freshwater and saltwater systems, corrosion problems will occur due to the various differences in fresh water found in different ports. Minerals and free ions can contribute to the corrosion of the aluminum freshwater system.

The installation of aluminum piping in aluminum structure would simplify construction and eliminate the necessity of galvanic isolation techniques that would be required for a steel-pipe system. The aluminum pipe would be lighter than steel due to differences in density and would not have the heavy-duty (schedule 80) wall-thickness requirement as does steel pipe.

Fiberglass-reinforced plastic, on one hand, offers several advantages. Cost studies indicate the GRP system to be the least expensive of eight systems studied (see Table 19), would be chemically inert to most substances, and would not produce galvanic incompatibilities. "Sailor proofing" GRP pipe would be more difficult. Unlike heavy-duty steel pipe, the GRP could not be used as a "chinning bar." Allowances for reinforcing and protecting piping in passageways and overheads must be considered.

Difficulties encountered in a GRP system include fabrication because GRP is not bendable. Bulkhead penetration techniques would have to be developed, and regulatory agencies do not consider GRP with intumescent coatings to afford adequate fire protection.

TABLE 19
MATERIAL COST-BALLAST SYSTEM (U.S. DOLLARS)^a

Item	Material							
	Aluminum	Black steel	Galvanized steel	Fiberglass reinforced plastic	Steel pipe PVC coated and lined	Stainless steel	Stainless steel	90-10 copper nickel
Specification	6061-T6	A53	A53	—	—	AISI 304	AISI 304	MIL-T-16420
Schedule	40	80	80	—	—	10	40	Type 200
Type	Seamless	Butt weld	Butt weld	Bondstrand or equal	Resisto-flex PP	Seamless	Seamless	Seamless
400 feet of 8 inch pipe	2,940	2,962	3,554	3,180	7,900	4,744	12,732	8,372
2000 feet of 12 inch IPS pipe	31,585	22,893	27,442	29,000	59,500	41,740	124,600	108,000
Bulkhead penetration connections	31,585	22,893	27,442	29,000	59,500	41,740	124,600	108,000
8 inch aluminum spool (waster piece)	—	3,000	3,000	—	—	—	—	—
12 inch aluminum spool (water piece)	—	12,600	12,600	—	—	—	—	—
8 inch flanges (92)	4,048	3,220	3,551	1,509	Included in pipe	5,300	5,300	—
12 inch flanges (38)	5,168	2,280	2,557	1,638	Included in pipe	6,250	6,250	—
8 inch valve (23)	—	—	—	—	—	—	—	—
12 inch valve (1)	—	—	—	—	—	—	—	—
8 inch ells (37)	3,330	1,338	1,769	2,566	6,384	2,295	4,101	—
12 inch ells (82)	21,320	8,282	10,783	8,930	28,700	22,796	35,424	—
12 inch tees (20)	20,320	3,380	4,280	7,248	9,200	15,000	18,180	—
Cathodic protection	—	3,400	3,400	—	—	—	—	—
8 inch couplings (4)	—	—	—	58	—	—	—	—
12 inch couplings (18)	—	—	—	445	—	—	—	—
Total cost	88,711	63,405	72,936	54,574	111,684	98,125	207,587	Complete information not available

^a Reprinted from SSC publications 218, p. 77.

Stainless steel pipe systems have been included in smaller craft such as patrol boats and hydrofoils. These systems are costly when compared to a similar system manufactured from black steel or GRP. However, stainless steel offers good corrosion resistance, is galvanically compatible with steel and aluminum structures, and is formable. In small diameters, welding or mechanical couplings can be used effectively.

The cost analysis for several ballast systems in a ship similar to the 632-foot M.V. Challenger are shown in Tables 17, 18, 19.

For economic and regulatory reasons, future ship construction will probably use an integrated pipe system composed of different materials. The cost involved with a mixed system must be determined to decide at what point there is an economic tradeoff.

APPENDIX C

OIL AND AIR SYSTEMS

Oil systems aboard ship can be lumped into three general categories: fuel oil for propulsion systems, lube oil for deck and propulsion machinery, and bulk cargo in the case of petroleum tankers.

Current regulations explicitly require fuel and engine lube lines to be manufactured from black steel due to the nonconductive characteristics of fuel oil and fire prevention requirements. The introduction of aluminum or plastic pipe should be considered for future use. As new materials and design allowables become available, regulatory agencies should consider their implementation after appropriate testing has been completed. The installation of black-steel fuel lines in aluminum structure will create galvanic corrosion problems if isolation procedures are not adequate.

The installation of stainless steel fuel and lubricating oil systems would eliminate the need for isolation protection. Bulkhead penetrations would have to be incorporated to maintain watertight compartments. These penetrations could be either mechanical or welded connections. Aircraft-type AN fittings and the in-place tube welder would facilitate pipe system installation and connection for modular construction and jumboizing. Design and fabrication techniques used in aircraft use modular construction and systems installation for preinstallation of many of the electrical systems, hydraulic tubing, and actuator cables.

Bulk cargo transfer to shore facilities or other ships will require an extensive pipe-and-pump network within a tanker structure. Cost considerations will be a major factor in deciding what type of system will be used. Safety experience gained with mobile aluminum truck tankers should make an all-aluminum pipe system a major contender for ship service, due to their impressive safety record.

Compressed-air systems involve two major areas of ship operation. They are a 400-psi engine-start system and a 100-psi ships-service system. Current design practices call for high-strength steel for each system. For an aluminum ship, a schedule 40 aluminum low-pressure system has been previously recommended. High-pressure stainless steel could be implemented for engine-start, eliminating galvanic couple problems associated with penetrations of steel pipe through aluminum bulkheads. This, used in



FIG. 21 - TYPICAL SPRAY BOOTH FOR APPLYING
ADHESIVE PRIMER

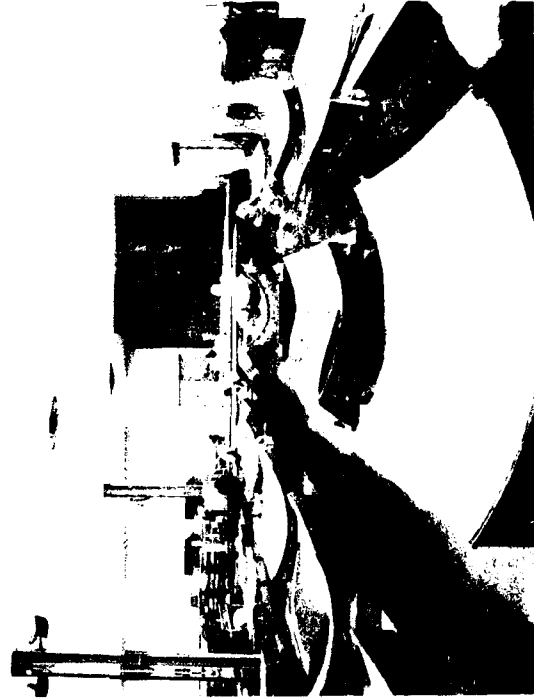


FIG. 23 - CLEAN ROOM FOR ASSEMBLY OF PARTS TO BE
BONDED



FIG. 20 - TYPICAL CHEMICAL PROCESSING LINE

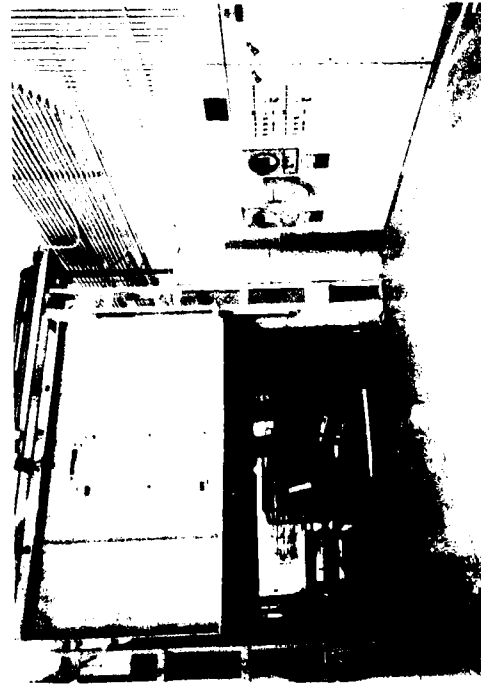


FIG. 22 - TYPICAL OVEN FOR PROCURING ADHESIVE
PRIMER

conjunction with pressure reducers and regulators, could be reduced to a single high-pressure system, with the regulators and reducers supplying the low-pressure ships service.

Should an inert-gas fire-control system be adopted, aluminum tubing would facilitate systems installation in aluminum structure.

Cost effectiveness of incorporating various systems into ship construction should be investigated. A particular system, whether single or mixed, will have to meet regulatory approval, and therefore any hard-and-fast recommendations cannot be made without knowledge of ship's purpose, current state-of-the-art information, regulatory revisions, allowances or standards, system type (oil, water, fuel, etc.), pump pressures, safety allowables, etc.

APPENDIX D

BONDING FACILITIES EQUIPMENT

A typical bonding facility for aluminum structures would require the following:

a) A chemical processing line with the following tanks (Figure 20):

- 1) Trichloroethylene degreasing tank
- 2) Alkaline cleaning tank
- 3) Warm water rinse tank, either immersion or spray
- 4) Sodium dichromate-sulfuric acid deoxidizer tank
- 5) Cold water spray rinse tank
- 6) Dryer tank

The sizes of the above tanks would have to be determined by the maximum part sizes to be run through the surface preparation process.

b) Closely adjacent to the chemical processing line should be a clean room. Operations to be included in the clean room and required special facilities are:

- 1) Spray booths and spray application equipment for applying adhesive primers (Figure 21).
- 2) Ovens to precure the adhesive primer--the sizes of both the spray booths and the precure ovens would be determined by the maximum size of parts to be processed (Figure 22).
- 3) Assembly area with adequate work space large enough to accommodate the tooling, parts, and associated assembly operations (Figure 23).

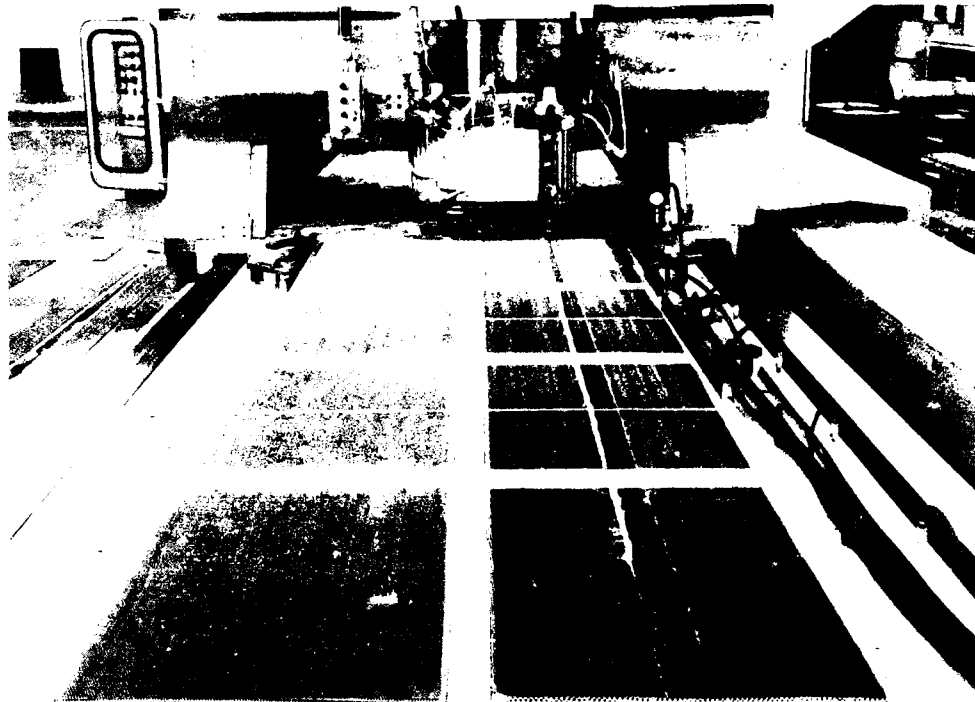


FIG. 24 - ALUMINUM HONEYCOMB CORE MACHINING EQUIPMENT

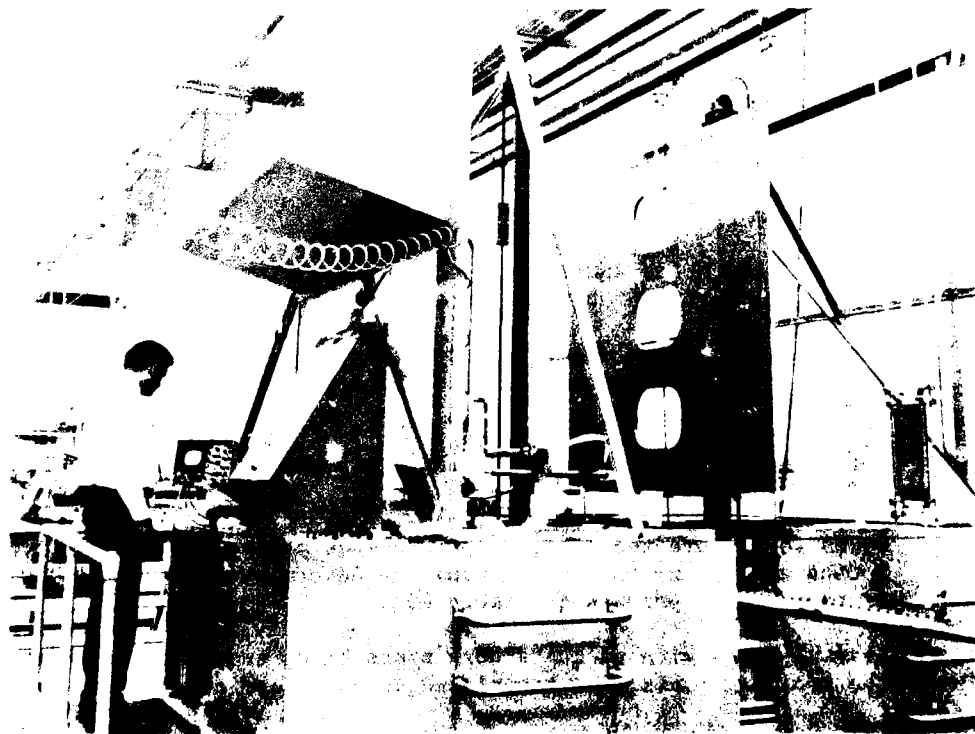


FIG.25 - ULTRASONIC NONDESTRUCTIVE TESTING EQUIPMENT

The clean room should have filtered incoming air and should be pressurized from 1/2 to 1 psi, in relation to adjacent areas, to be sure all air movement is outward from the clean-room area. The primary purpose of the clean room is to provide a segregated area for the special handling required for the "clean" part during the priming, precuring, and assembly operation.

- c) A curing facility to supply heat and pressure for the final cure of the adhesive is required. The most common curing facility now in use is an autoclave. Here again, the size of the autoclave is determined by the maximum size of the largest bonded assembly and also the total volume of bonded parts. The autoclave requires area and handling equipment for staging and handling the bonding tools in and out. There is considerable experience in the design and fabrication of autoclaves for adhesive bonding in the aerospace industry.

As indicated above, the total bonding facility would be sized in relation to the maximum size of parts to be bonded and the volume of parts to be fabricated. In addition, consideration should be given to the sheet-metal and machining equipment for honeycomb core (Figure 24), machining equipment required to fabricate the detail parts required for the bonded assemblies, and the required nondestructive testing equipment (Figure 25) for inspection of assemblies in process and after the final bonding operation. In-process controls are also required to maintain bond quality and reliability and reinforce confidence level.

APPENDIX E

IN-PLACE TUBE WELDING

The in-place tube welder (Figure 26) was developed for in-place production welding of stainless steel and titanium high-pressure hydraulic systems and is a commercially available product.

Alignment of the tubing and fitup of the abutting ends at the weld joints are major factors in consistently producing an acceptable weld joint. Auxiliary bridge tools are used to support the tubing during the weld operation and are shown in Figure 27. The space envelope dimensions required for a typical head and auxiliary bridge tool are shown in Figures 28 and 29. Depending upon the application, various types of weld joint configurations have been used successfully. Several of the more popular and practical joints are shown in Figure 30.

For those heavy-wall tube joining applications requiring the addition of filler wire, suitable miniature crawler-type weld heads are available. Due to the additional mechanisms to handle wire feed, these heads are substantially larger than the nonfiller wire adding-type head. A representative head available at this time is shown in Figure 31, with its space requirements in Figure 32.

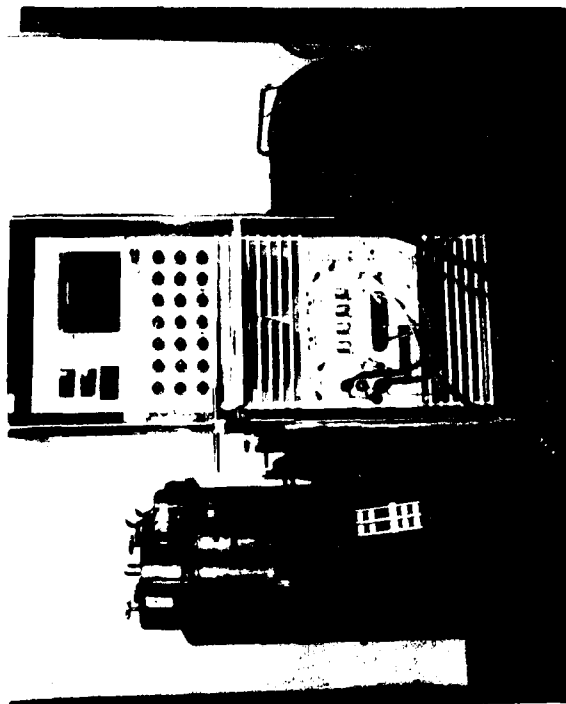


FIG.26 - TYPICAL COMMERCIAL INPLACE GTA TUBE WELDING POWER SUPPLY/PROGRAMMER AND WELD HEAD

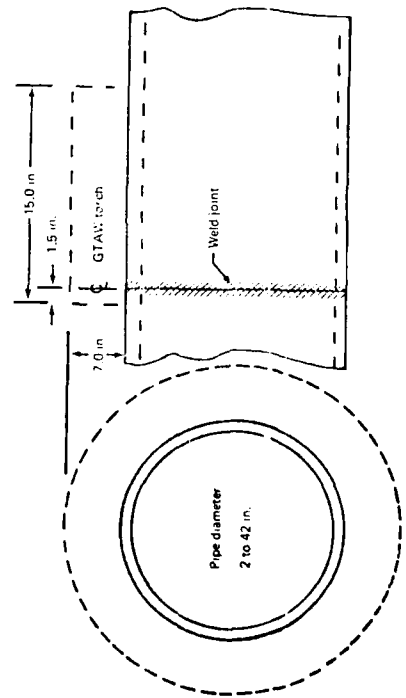


FIG.28 - CLEARANCE ENVELOPE FOR TYPICAL GTA PIPE WELDING CRAWLER HEAD



FIG.27 - TYPICAL COMMERCIAL INPLACE GTA TUBE WELDING HEAD WITH AUXILIARY BRIDGE TOOL



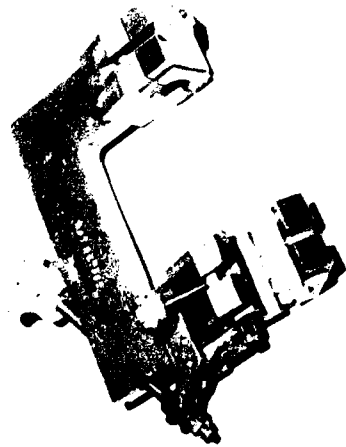



FIG.29 - AUXILIARY BRIDGE TOOL

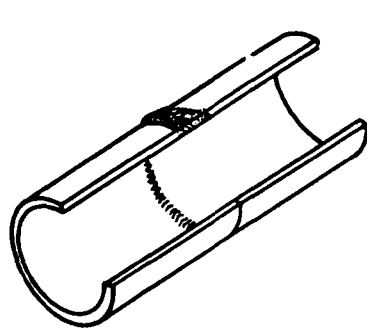


Butt Joint

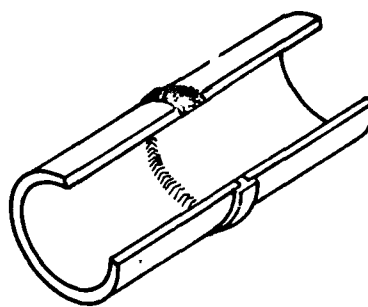


Butt Joint With
Filter Metal Insert

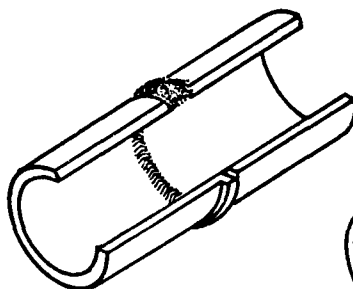


Flare Bevel Butt Joint

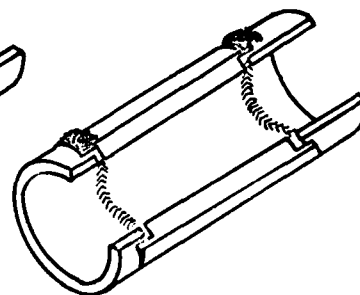

Flange Butt Joint

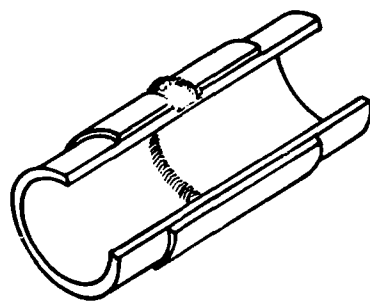

Butt-Sleeve Joint

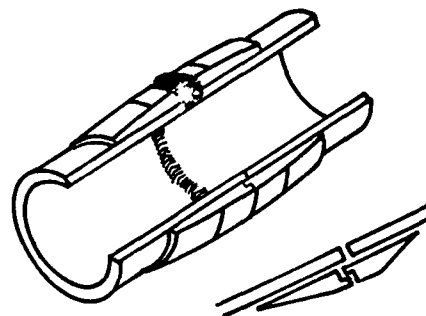

Weatherhead Sleeve Joint
(Swaged and Welded)

FIGURE 30
TUBING WELD JOINT CONFIGURATIONS
FOR GTA TUBE WELDER



FIG.31 - TYPICAL COMMERCIAL MINIATURE GTA TUBE WELDING CRAWLER UNIT WITH AVC, TORCH OSCILLATION, AND WIRE FEEDER

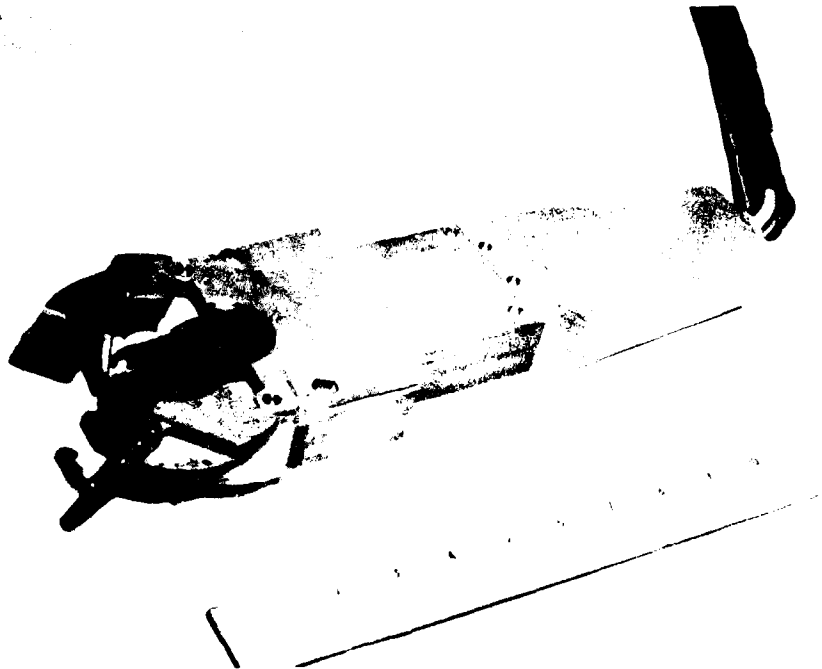


FIG.32 - TYPICAL GTA TUBE WELDING HEAD

APPENDIX F

ELECTRICAL SYSTEMS AND THEIR ATTACHMENTS

The installation of electrical systems and connections between components has presented numerous problems to the design and fabrication contractor of both steel and aluminum ships.

Regulations require many of the connecting compartments to be isolated from each other in the event of fire, flooding, or other contamination. Since control systems necessary for ship operation cannot be installed externally to the structure, it is required that bulkhead penetrations into adjoining compartments maintain the integrity of each compartment, should an emergency situation occur.

The penetration of steel piping through a steel structure, or aluminum piping through an aluminum structure, afford the opportunity for contaminants to enter adjoining compartments. This condition can be eliminated by fillet welding the pipe and bulkhead at the point of penetration. Suggestions and recommendations for dissimilar metal penetration of steel pipe through aluminum bulkheads are contained in the explosive-bonding section of this report and will not be elaborated upon here.

Electrical systems present a more difficult problem in that most of the wiring and cables are armored. Even when conduits are used, a stuffing tube arrangement must be fabricated to ensure each compartment's integrity. This process creates additional outfitting difficulties and higher costs, both in material and labor, and is not conducive to visual inspection or postservice modifications.

MULTI-CABLE TRANSIT

A commercial product, Multi-Cable Transit (MCT) bulkhead penetration, such as that marketed in recent years by Nelson Electric, offers the designer and fabricator a new method of maintaining compartment integrity when installing control systems (Figure 33).

Multi-Cable Transit bulkhead penetrations have frames made from aluminum or steel, measure approximately 2-3/8 inches in depth, vary from 5-1/4 to 5-1/2 inches in width, and have lengths of 4-3/4 to 9-3/8 inches, depending on model. The MCT uses cable modules made from Tecron, a DuPont neoprene compound that expands when heated.

The installation procedure is relatively simple. An oblong hole is cut in the bulkhead to accept the MCT frame which is then welded into position (Figure 34). Electrical cables or tubing are then run to their respective positions where they can be connected for a system check. The predrilled Tecron block, conforming to the respective cable dimensions, is installed with a slight coating of lubricant on the block. Armored cables have G.E.'s RTV-102 or 106 sealer applied in the grooves of each block to seal the space between the armor and cable sheath. A compression plate is installed, along with the end packing to seal against fire, water, and air leaks. MCT will accommodate cables or pipe ranging in outside diameter from 5/32-inch to 3-3/4 inches. These units may be purchased in gang or group mountings. Additional cables or tubing may be installed by adding the necessary insert blocks. Cables may be removed in the reverse manner. An added advantage of MCT installation is that fabricated

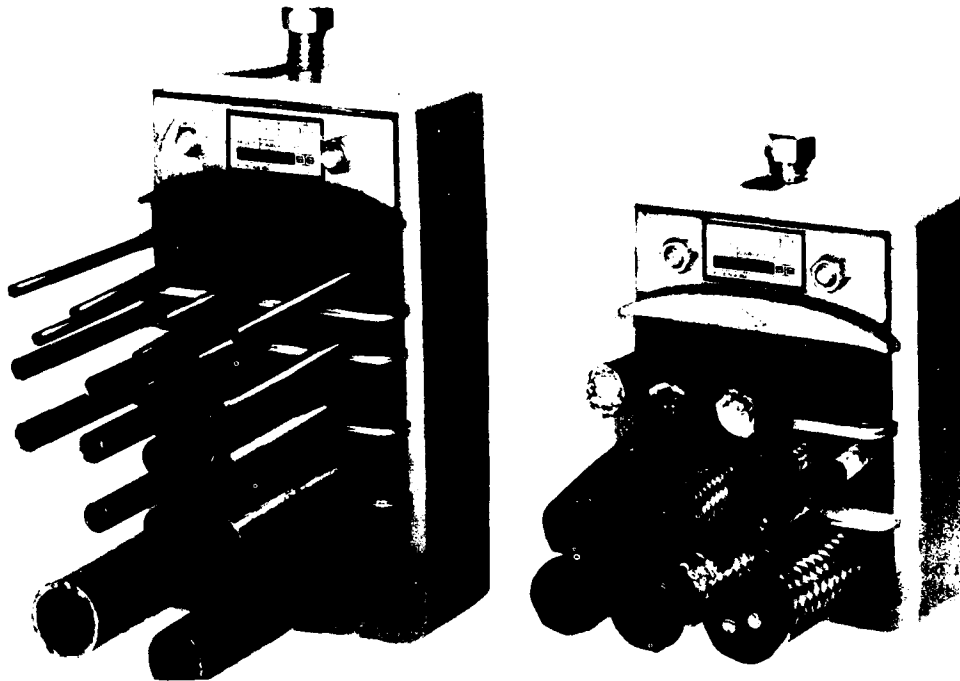


FIG. 33 - TYPICAL MCT CABLE & TUBE ASSEMBLIES



FIG. 34 - INSTALLATION OF MULTICABLE TRANSIT FRAME

cabling with connectors attached can be passed through the MCT. For rf and high-frequency applications where signal leakage and grounding are important, MCTs with conductive rubber blocks are available.

Fire tests conducted at the Lockheed Electronics Environmental Test Laboratory demonstrated that MCT could withstand 1715° F for 1-1/2 hours, when attached to a 1/4-inch steel test panel. The rear side of the MCT and cables remained relatively intact during the test. MCT inserts are not subject to attack from liquid chemicals or hydrocarbons. MCT is reputed to comply with Mil-P-16685C, U. S. Military Standard 167, Mil-S-901C, Mil-Std-108D, ASTM-E119-61, and the JCSLS fire-test standard.

Cost comparisons indicate the MCT units will save 50% of the installation costs over the cable-tray or conduit-and-sealing-compound methods of cable installation.

FLAT CABLE

Scotchflex, a family of flat cable produced by the 3M Company, currently is under study for possible introduction into commercial aircraft electrical systems connections.

The use of flat cable would provide additional advantages in ship outfitting and systems installations.

Flat cable can be installed in space-critical areas such as passageways, overheads, and bulkheads (Figure 35). This type cable is designed for hookup of connecting components, especially those using printed circuit boards in their assembly.

Transitions from flat cable to conventional round-wire connectors can be accomplished by any of several methods such as splices or junction boxes (Figures 36 and 37). Flat cable offers a decisive weight-savings advantage as well as ease of fabrication and installation. It can be prefabricated for modular construction or systems installation.

With more emphasis being placed on preassembly and modularization, implementation of the flat cable concept would be beneficial.

APPENDIX G

OPTICAL LASER APPLICATIONS

The Manufacturing Research and Development Department of Boeing is currently involved with developing a manual for using optical lasers in shipbuilding. This program is being conducted in conjunction with Toud Shipyards Corporation of Seattle.

The objective of this research program is to apply alignment state-of-the-art knowledge and experience to shipbuilding with special emphasis on hull erection and machinery installation. Although accuracy is the main criterion for using lasers in aircraft alignment, it is not the only criterion. There are more advantages that are not readily seen. A few of them are:

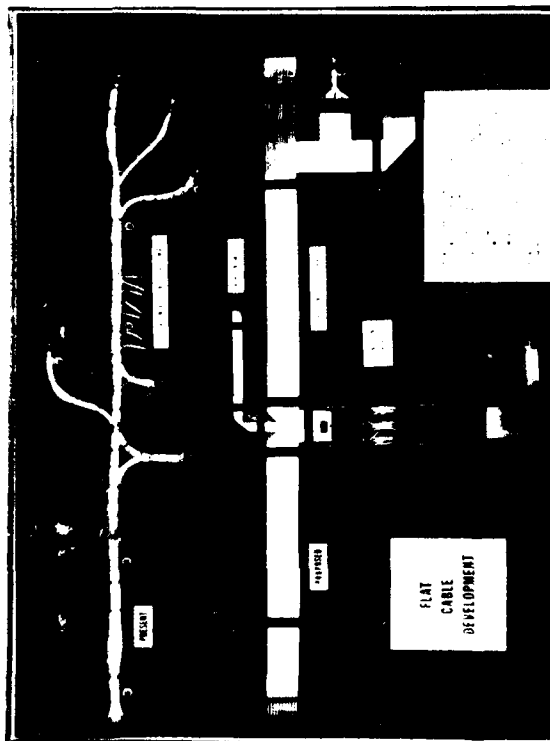


FIG. 35 - FLAT CABLE ASSEMBLY COMPARED TO ROUND WIRE BUNDLE



FIG. 37 - FLAT CABLE/ROUND WIRE JUNCTION BOX



FIG. 36 -- FLAT CABLE TO ROUND WIRE TRANSITION

- a) Optical instruments require experienced personnel. Lasers do not.
- b) The accuracy of optical instruments depends on resolution, definition, proper certification, removal of parallax, pointing (dependent on physiological and psychological characteristics of individual operators), and proper targeting and target lighting. Lasers depend primarily on certification. Human interpretations would be eliminated for machinery and other precise alignment applications.
- d) Once set up, one man can interrupt a laser beam anywhere and take a measurement much the same way as he would with a strung-out wire. The laser beam would be a precision straightedge. A piano wire, no matter how taut, still must be corrected for a perceptible catenary.
- e) The laser beam can be detected visually as well as electronically. Optics normally require two men for this operation.
- f) The laser is much more simple to buck into a line and considerably more simple to buck into a plane than is the telescope and transit under most fabrication conditions.
- g) The laser does not require initial focusing to find the target and refocusing to achieve final alignment.
- h) Unlike optics, the laser field of view is the entire field of view of the operator and any other observer. Thus, the laser can be used as a long pointing stick.
- i) Collimation or autocollimation of the laser is not limited to mirror size as it is on the telescope.

A summary of applications of the optical laser includes, but is not limited to, the following:

- a) Alignment of ways and blocks prior to laying keel
- b) Alignment of keel and panels
- c) Stiffener location and alignment for preassembly technique development
- d) Checking levelness during hull erection
- e) Hull-section alignment for modular or "jumboizing" assemblies
- f) Stern-tube and shaft alignment
- g) Hatch-coaming and guide installation
- h) Lash-rail alignment
- i) Superstructure-to-hull and deck alignments

APPENDIX H - BOEING DESIGN MANUAL

SECTION 17

FASTENERS, GENERAL

17.1 INTRODUCTION

17.11 Riveting General

17.2 SYMBOLS AND CALLOUT

17.21 Fastener Symbols

17.211 NAS Symbols

17.2111 Examples of NAS Symbols

17.2112 Basic Rivet Code

17.2113 Oversize Fastener Code

17.212 Obsolete Symbols

17.22 Fastener Callout

17.221 Parts List Callout

17.222 Location Callout

17.23 Hole Location Symbols

17.24 Matching Holes

17.241 Holes to Mate With Standard Parts

17.242 Coordinating Holes

17.243 Identical Parts Except for Holes

17.25 Hole Size Callout

17.251 Selection of Holes for Standard Fasteners

17.252 Standard Holes for Structural Fasteners

17.253 Hole Size for Blind Fasteners Group I

17.3 FLUSH REQUIREMENTS

17.31 Tolerances

17.32 Countersinking and Dimpling

17.321 Countersinking

17.3211 Minimum Sheet Thickness

17.3212 Callout

17.322 Dimpling

17.3221 Edge Margin

17.3222 Callout

17.5 SEALING

17.51 Callout

17.52 Types

17.53 Maximum Spacing

17.6 FASTENER USE CHARTS

17.61 NAS Symbol Fasteners

17.611 Solid Shank Structural Rivets

17.612 Lock Bolts & Hex Drive Bolts

17.613 Blind Fasteners

17.62 Threaded Fasteners

17.621 Bolts

- 17.6211 Titanium Fasteners
- 17.6212 Self-Locking Bolts
- 17.6213 Non-Standard Threaded Fasteners
- 17.6214 Specially Surfaced Steel Bolts
- 17.6215 Bolts Without Cotter Holes
- 17.6216 Oversize Bolts
- 17.6217 Radius Clearance
- 17.6218 Bolted Sloping Surfaces

17.622 Screws

17.6221 Tapping Screws

- 17.62211 Thread Forming Screw
- 17.62212 Thread Cutting Screw

- 17.6222 Drive Screws
- 17.6223 Wood Screws
- 17.6224 Set Screws

17.623 Nuts

17.6231 Nut Use Charts

17.624 Plate Nuts and Gang-Channel Nuts

- 17.6241 Gang-Channel Nuts- Drawing Callout
- 17.6242 Plate Nut Hole Clearance - Drawing Callout

17.625 Sheet Spring Nuts

17.63 Special Fasteners

17.631 Pins Use Chart

17.632 Shear Pins

17.633 Metal Stitching

- 17.6331 Edge Margin and Spacing
- 17.6332 Capacities and Dimensions
- 17.6333 Drawing Callout

17.634 Quick Release Fasteners

17.64 Washers, Spacers, and Shims

- 17.641 Washers
- 17.642 Shims, Plate Nuts
- 17.643 Spacer, Sandwich Board
- 17.644 Rivet, Spacer Head, Blind
- 17.645 Spacer, Rivet and Bolt
- 17.646 Spacer, Plate Nuts
- 17.647 Nut, Spacer Plate
- 17.648 Radius Fillers

SECTION 17

FASTENERS, GENERAL

17.1 INTRODUCTION

- A. Fastener information is presented in three sections.
 1. Section 17 contains callout instructions for all fasteners and holes, hole sizes, sealing information and usage charts.
 2. Section 18 provides strength data, edge margins and spacing requirements.
 3. Section 19 contains descriptions of fastener installation tools and related information which must be considered in design.
- B. The installation of fasteners is controlled by process specifications.
 1. BAC5004 for rivets, lockbolts and blind fasteners.
 2. BAC5009 for bolts and nuts.

Drawing forms contain references to these specifications in the title block area.

C. In addition, where applicable, additional process specifications should be called out on drawings. For example,

1. BAC5018 for installation of cotter pins and similar safetying devices.
2. BAC5047 for installation of fasteners which must be fluid tight.
3. BAC5049 for dimpling and countersinking.
4. BAC5085 for installation of metallic sandwich spacers.

17.11 RIVETING—GENERAL

Joint design and associated fastening concepts shall continue the practices used on previous commercial models with exceptions to provide increased reliability, weight and cost reductions. A brief review of the major current practices and recommended changes follows.

Fluid Tight

For fluid tight riveting, the use of NACA and modified NACA fluid tight riveting in accordance with BAC5047 shall be required. Avoid the use of rivets where the material thicknesses are greater than 2.5D.

For fluid tight rivet installations in exterior and aerodynamic applications, rivets shall be of the shear head type (BACR15CE) and shall be installed in accordance with BAC5047.

For fluid tight riveting on protruding head aluminum alloy structures and attachments shall be in accordance with BAC5047 and 20470.

For fluid tight riveting on blind rivets (BACR15DR), rivets shall be installed in accordance with customer specifications. In addition, rivets shall be installed in accordance with structural strength and fatigue requirements. For fluid tight riveting on blind rivets, the rivet shall be of the shear head type (BACR15CE) and shall be installed in accordance with BAC5047.

For fluid tight riveting on blind rivets (BACR15DR) shall be installed in accordance with customer specifications.

17.211 NAS SYMBOLS

The NAS523 Symbol System is used to call out permanent type fastener units on drawings. The fastener units shown in 17.211.2, Basic Rivet Code, can be called out with the NAS Symbol System. A threaded bolt that is used with various nuts, pins, metal stitching, and miscellaneous special fasteners cannot be included in the NAS Symbol System.

A. The NAS Type Symbol is basically a cross with the intersection at the center of the fastener in the plan view. Fastener identity, size and installation instructions are indicated by letter-numeric coding within the quadrants of the cross. For convenience the four quadrants are referred to as shown below regardless of rotation.



Figure 17.211.1

B. Basic Code. The fastener is identified by a non-significant two letter code in the NW quadrant, which defines all features except diameter and grip or length. It also includes the collar for lockbolts and Hi-Shears. When included in a box, installation per BAC5047 is required. For code letters, see the usage charts. Code letters to be used by the entire aircraft industry are added to NAS523 and then to the Design Manual. Code letters for individual company use begin with X. Consult Seattle Standards Unit for assignment of new code letters.

C. Diameter and head location are indicated by a number and letter in the NE quadrant. The number is the same as the diameter dash number of the part or the last one or two digits of part numbers which express the nominal diameter by these digits; the letter N or F refers to NEAR SIDE or FAR SIDE of the manufactured head. If the head location is optional, or is clearly shown by the drawing the letter may be omitted.

D. Rivet length and spotweld optional are shown in the SE quadrant by a number and letter. The number is the dash number for the length or grip of the part; it is omitted for conventional rivets except in modification kit drawings per PM, D-4900. The letter W, if used, permits spotwelding instead of riveting.

E. Countersinking and dimpling instructions are shown in the SW quadrant as follows:

1. Dimpling is indicated by a D followed by a number indicating the number of sheets to be dimpled, if more than one.
2. Countersinking is indicated by the letter C. No number is used with countersinking.
3. Flush both sides is shown by placing the letters and number (as applicable) on two lines. The upper line applies to the manufactured head, and the lower line to the driven head. The angle of the driven head shall be the same as that of the manufactured head except as noted in paragraph F below.

F. Fluid tight riveting (per BAC5047), is shown by enclosing the basic code in a square in the NW quadrant. Place 82 below the countersink code in the SW quadrant when an 82° driven head angle is required (NACA style).

G. Rivet symbol blocks as shown below will be printed on drawing forms stocked at the supply counters, or upon request to the Reproduction Unit. Several blank spaces are provided for listing the rivets used on the drawing and the code for each. More spaces may be added by the draftsman if required.

17.211 NAS SYMBOLS (Continued)

BK = MS20470B	CE = P (CKL)
BA = MS20426A	XLP = BACB30LA
DZ = SAL100-T & 6LC-C	NAS 528
XPC = BACB30MB*A**U & BACC30X	XC= BAC-R158B-AD
+ HOLE LOCATION FOR X DIAMETER RIVET	
<p>INSTALLATION: STD, PER BAC 5004; FLUID TIGHT, PER BAC 5047</p> <p>BASIC CODE —————</p> <p>ENCLOSED = FLUID TIGHT OPEN = STANDARD</p> <p>DIMPLE/CSK INFO —————</p> <p>D = DIMPLE 2 = NO. SH DIMPLES C = CSK INSTRUCTURE 2 LINES: TOP = MFD HD; BOTTOM = DRIVEN HD</p> <p>NOTE: PROTRUDING HD RIVETS DRIVEN FLUSH D/C INFO (2 LINES) APPLIES TO DRIVEN HD ONLY.</p>	
<p>————— DIA DASH NO. ————— MFD HEAD LOC N = NEAR SIDE F = FAR SIDE</p> <p>————— SPOT WELD OPT ————— LENGTH DASH NO.</p>	
RIVET SYMBOL CODE	

Figure 17.211-2

NOTE: The Basic Fastener Code and the equivalent part number(s) that are noted the Rivet Symbol Code box, shall be the same as those listed in 17.2112 and D590. These include codes for material, finish, etc., as required.

Example: XPC = BACB30MB*A**U & BACC30X

Where: BACB30MB = Basic Part Number
"A" code = A286 material
"U" code = Unplated

17.2111 EXAMPLES OF NAS SYMBOLS









$\frac{BK}{W}$	MS20470B4, UNIVERSAL HEAD, 5056-F RIVET, 1/8 DIAMETER. HEAD DIRECTION OPTIONAL. SPOTWELD OPTIONAL.	
$\frac{BA}{C}$ 6N	MS20426A6, 100° HEAD, 1100-F RIVET, 3/16 DIAMETER. COUNTERSINK 100° NEAR SIDE FOR MANUFACTURED HEAD.	
$\frac{BA}{DC}$ 6F	MS20426A6, 100° HEAD, 1100-F RIVET, 3/16 DIAMETER. MANUFACTURED HEAD FAR SIDE. DIMPLE OUTER SHEET AND COUNTERSINK IN STRUCTURE 100° BOTH SIDES.	
$\frac{DZ}{C}$ 6F 5	SAL100-T6-5 (BAC-B30P-6-5), 100° HEAD, STEEL, SHEAR LOCKBOLT, INCLUDING 2024-T4 COLLAR 6LC-C6 (BAC-C30A-C6), 3/16 DIAMETER, 5/16 MAXIMUM GRIP. COUNTERSINK 100° FAR SIDE FOR MANUFACTURED HEAD.	
$\frac{XLP}{C}$ 6 3	BACB30LA6-3, 100° HEAD, BLIND BOLT HUCKBOLT, 3/16 DIAMETER, 3/16 NOMINAL GRIP. COUNTERSINK 100° FOR MANUFACTURED HEAD (Direction assumed to be obvious).	
$\frac{CE}{D}$ 6	P6D (BAC-R15AP-6-147), BRAZIER HEAD, 5056-F BLIND RIVET (HUCK CKL), 3/16 DIAMETER, .129 - .165 GRIP RANGE. (The use of letter D for grip is an exception to the standard code). Head Direction Obvious.	
$\frac{XC}{C}$ 6F 82	BAC-R158B-6AD, 2117-T3, 3/16 DIAMETER, UNIVERSAL HEAD RIVET. MANUFACTURED HEAD FAR SIDE. FLUID TIGHT PER BAC 5047.	
$\frac{XC}{C}$ 6F 82	BAC-R158B-6AD, 2117-T3, 3/16 DIAMETER, UNIVERSAL HEAD RIVET. MANUFACTURED HEAD FAR SIDE, COUNTERSINK 82° FOR FLUID TIGHT DRIVEN HEAD PER BAC 5047.	
$\frac{6}{}$	HOLE LOCATION FOR A 3/16 DIAMETER RIVET. (The number signifies rivet diameter in thirty-seconds.)	

Fig. 17.2111-1

17.23 (Continued)

- The assembly or installation drawing shall locate the parts, indicate the fastener and associated parts such as nuts, washers, etc., and show the hole size per 17.25.

Where hole patterns are duplicated on other drawings a note shall be added stating which drawing shall be used as a pattern. Drawings showing holes which are not to be used for patterns shall show the note:

USE RIVET (BOLT) HOLE LOCATIONS SHOWN ON XX-XXXX

This note should also be shown on assembly drawings not used as hole patterns.

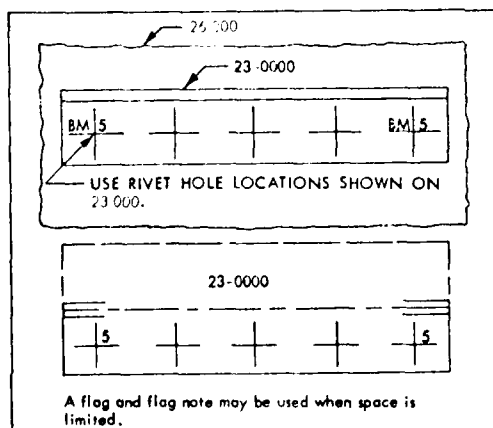


Figure 17.23-1

17.24 MATCHING HOLES

See DM 81, Section 13.

17.241 HOLES TO MATE WITH STANDARD PARTS

When holes in a detail part or assembly must mate with holes in a purchased or government furnished item the sizes and locations shall be completely dimensioned and toleranced to assure fit if assembly is on a higher drawing. The note, "LOCATE TO MATCH" shall not be used. If a G.F.E. part is brought together with Boeing parts for assembly, use note "USE HOLE LOCATIONS SHOWN ON -----" (GFE PART).

17.242 COORDINATING HOLES

Coordinating holes shall be used in accordance with DM 81, 1.532.

17.243 IDENTICAL PARTS EXCEPT FOR HOLES

Parts which are identical except holes or hole locations require different part numbers. This applies to parts drawn as separate details or called out by dash number on an assembly or installation.

A. When a standard part is drilled for installation, it shall be given a new number and treated as a MAKE FROM part--see PM 94B1, Section 5.034.

B. Boeing detailed blank parts which are used in two or more assemblies having different hole patterns shall be treated as in A above.

17.25 HOLE SIZE CALLOUT

A. HOLE SIZES NOT SPECIFIED ON THE DRAWING. Hole sizes for conventional rivets and Cherry, Olympic, Huck, Dupont chemically expanded blind rivets, are controlled by BAC 5004 or BAC 5047 and shall not be shown on the drawing.

B. HOLE SIZES SPECIFIED ON THE DRAWING. All fastener holes not included in A above must have the size and tolerance clearly specified in decimal dimensions on the drawing. These include, bolts, screws, swaged collar fasteners, blind lockbolts, Jo-Bolts, and Deutsch Blind rivets.

Hole sizes may be specified in various ways, such as by note at the fastener location, or by a general note near the title block for each size and type of fastener used, or by a combination of such notes.

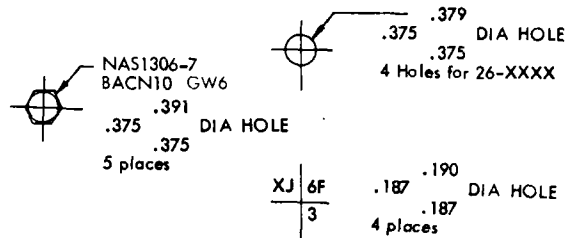
If the purpose of a hole is not readily apparent a note shall be added to reference its use. This also applies to blank holes.

When a clearance hole is one bolt size larger than the bolt, Manufacturing assumes the drawing is in error. To avoid misunderstanding and delay, a special note should be added. For example, if a .313 hole is required for a 1/4 bolt the following note may apply:

.313 .317 DIA. OVERSIZE HOLE FOR NAS 1304 BOLT

The method used to produce a hole will not be included in the drawing callout; the size and tolerance will indicate the required method.

Holes may be called out with or without the fasteners as shown:



NOTE: Solid ϕ for .5 diameter or less.

17.251 SELECTION OF HOLES FOR STANDARD FASTENERS

The precision required in drilling holes for bolted structural joints carrying shear loads is determined by the nature of the loads and by the number of bolts in the joint. See Figure 17.251-1.

SELECTION OF HOLES FOR FASTENERS			
Joint Condition or Loading		Fastener Type	Recommended Hole Type
Joint transmits large portion of load carried by airplane component (wing empennage, etc.).	Less than four fasteners in joint.	Close Tolerance Bolt	Close Ream ①
Joint subject to frequent load reversal (buffeting or vibration).		Lock Bolt	Transition Fit ②
Joint subject to rapidly applied loads as a result of high acceleration of large masses.	Four or more fasteners in joint.	Close or nonclose Tolerance Bolt, or Lock Bolt	Class I ③
Joint in fluid tight structure.		All	Close Ream ①
Joint in secondary structure.		All	Class II ③
Joint in primary structure: A. Not subject to reverse and/or rapidly applied loads. B. Over-strength (margin of safety greater than 25 per cent in shear and greater than 50 per cent in bearing). NOTE: Where resulting allowable motion in joint will tend to overload adjacent structure, use Class I hole.			
Joint in which tension only is applied to fastener with no reversed loads.		All	Class III ③ ④
Joint where close fit is obviously not required, and alignment of predrilled holes is difficult. Examples: Clamps, fairleads, instrument and equipment support brackets, junction boxes, lining trim, miscellaneous supports and brackets.			

① Close tolerance bolts may be installed in close reamed holes in all materials.

② Lock bolts in transition fit holes shall be restricted as follows (not for blind lock bolts):

A. Material single thickness next to collar shall be at least .25 times nominal fastener diameter.

B. Total material thickness shall not exceed 4 times nominal fastener diameter.

③ Hole sizes for blind bolts are shown in 17.253.

④ Class III holes do not necessarily provide the largest clearance advised for all designs. Where the design allows, and either fabrication or assembly is more economical with larger clearances, larger holes may be specified with sizes in accordance with 7.411.

Figure 17.251-1

17.252 STANDARD HOLES FOR STRUCTURAL FASTENERS

A. Hole size for bolts, screws, lockbolts, pins and other similar structural fasteners are given in Figure 17.252-1.

B. Manufacturing practices for hole preparation and fastener installation for all but extreme design requirements are specified in Process Specifications BAC5004 (for lockbolts and blind fasteners) and BAC5009 (for both screws and nuts). The requirements of BAC 5004 and BAC5009 are specified by a note silk screened on drawings near the title block. Special installation requirements, where necessary, must be clearly specified in detail on the drawings. In such cases, it must be established that the requirements are within manufacturing capabilities and are economically justified: consultation with the applicable divisional staff is recommended.

Some provisions of BAC5004 and BAC5009 are as follows:

1. Fastener holes are required to be within 2° of normal to:

- a. The surface under the head of protruding head fasteners.
- b. The surface surrounding the top of countersunk fastener.
- c. The surface in contact with the washer face of nuts.

NOTE: "within 2° of normal" is intended as a shop tolerance, in cases where design is such that the surface under the bolt head or nut is not nominally perpendicular to the hole with 1/2°, the drawing shall call for a spotface (per DM Book 81, 7.4132) as optional.

2. The perpendicularity of installed fasteners is also controlled by limiting the permissible gap under fastener head and nuts. This gap is influenced by hole abnormality, cocking of fasteners heads, lack of fastener straightness, abnormality of nut threads in relation to the washer face of nut, surface irregularities under nuts or heads of fasteners, bending of the fastener and compression of the clamped material.

C. Aluminum collars swaged on lockbolts can accommodate more slope than nuts on bolts. The permissible slopes given in Figure 19.34-1 include the 2° deviation from normal allowed for shop hole preparation.

17.252 (Continued)

STANDARD HOLE LIMITS PER NAS 618												
Nominal Diameter Fastener	Close Ream		Transition Fit				Class I		Class II		Class III	
	Min	Max	In Alum and Mag		In Steel		Min	Max	Min	Max	Min	Max
0									.062	.067	.081	.090
1									.075	.080	.093	.103
2									.088	.093	.106	.118
3									.101	.106	.120	.131
4									.114	.119	.136	.147
5 or 1/8									.127	.132	.147	.158
6									.140	.145	.161	.172
③ 8 or 5/32	.1635	.1645	.161	.164			.164	.168	.166	.171	.192	.203
10 or 3/16	.1895	.1905	.187	.190			.190	.194	.190	.199	.218	.229
1/4	.2495	.2505	.247	.250			.250	.254	.250	.261	.279	.291
5/16	.3120	.3130	.309	.313			.312	.316	.313	.327	.342	.354
3/8	.3745	.3755	.371	.375			.375	.379	.375	.391	.404	.416
7/16	.4370	.4380	.434	.438			.437	.442	.438	.457	.467	.479
1/2	.4995	.5005	.496	.500			.500	.505	.500	.521	.529	.541
9/16	.5620	.5630	.559	.563			.562	.567	.563	.583	.591	.610
5/8	.6245	.6255	.621	.625			.625	.630	.625	.645	.653	.672
3/4	.7495	.7505					.750	.757	.750	.773	.778	.797
7/8	.8745	.8755					.875	.882	.875	.898	.903	.922
1	.9995	1.0005					1.000	1.010	1.000	1.026	1.028	1.047
1 1/8	1.1245	1.1260					1.125	1.135	1.125	1.155	1.153	1.172
1 1/4	1.2495	1.2510					1.250	1.260	1.250	1.280	1.278	1.297
1 3/8	1.3745	1.3760					1.375	1.385	1.375	1.405	1.403	1.422
1 1/2	1.4995	1.5010					1.500	1.510	1.500	1.530	1.528	1.547

① Class II holes and ② thru 6 holes are not shown in NAS 618.
 ③ Oversize fasteners are for repair work only and shall not be used in design.
 Transition fit for 5/32 B30DX, B30DY, B30GP and B30GG is .162 - .165, not per NAS 618.
 ④ For holes with larger tolerances see note ① in Figure 17.251-1.
 ⑤ Washer required under fillister screw head.

Figure 17.252-1

17.253 HOLE SIZES FOR BLIND FASTENERS GROUP I

Holes listed in Figure 17.253-1 are for high strength blind fasteners (Huck Blind Bolt).

HOLE SIZES FOR HUCK BLIND BOLTS BAC B30LA & BAC B30LB		
Nominal Size	Hole Diameter	
	Minimum	Maximum
5/32	.164	.167
3/16	.199	.202
1/4	.260	.263
5/16	.312	.315
3/8	.374	.378

Figure 17.253-1

17.3 FLUSH REQUIREMENTS

The selection of countersinking or dimpling, and the flushness tolerance that must apply, shall be in accordance with this section.

17.31 TOLERANCES

A. The normal fastener flushness tolerance of $\pm .010$ is included in BAC 5004 and 5009. Drawings which require compliance with these specifications need not call out normal tolerances. However, if tolerances smaller than $\pm .010$ are necessary they shall be selected from Figure 17.31-1 and called out on the drawing by symbol or note as shown by example.

B. These tolerances are mandatory for dimpled structure to permit the use of standard dies. The same (or larger) tolerances are preferred for countersunk structure. However, countersinking tools can be adjusted to satisfy special requirements.

C. Drawing callout examples of an individual tolerance included with a symbol as a general note.

BE | ALL MS20426 RIVETS INSTALLED FLUSH $\pm .005$ (IN
D | AREA INDICATED). $\pm .000$

XFV | ALL BACB30GY RIVETS INSTALLED FLUSH $\pm .005$ (IN
D | AREA INDICATED). $\pm .002$

17.31 (Continued)

FASTENER ①	DRAWING NUMBER	FLUSHNESS TOLERANCE (TO BE SPECIFIED ON DRAWING)	REMARKS
Aluminum Rivets	MS20426 BACR15BA	+ .005 - .000	1. Preferred. Requires practically no shaving.
Aluminum Lockbolts	BACB30GQ	+ .002 - .000	2. For critical aerodynamic areas. Requires shaving.
Blind Rivets Group 11	NAS1399 BACR15DD BACR15DF BACR15DJ	+ .002 - .004 Maximum stem protrusion above skin .020	1. Usual, as driven. 2. Normal stem retention.
		+ .002 - .004 Maximum stem protrusion above skin .002	1. For critical aerodynamic areas. 2. Requires shaving. 3. Normal stem retention.
Shear Lockbolts	BACB30GY		1. Cannot be shaved. 2. Cannot be installed in below-flush applications which require aerodynamic smoother.
Tension Lockbolts Tension Lockbolts Stumps	BACB30DX BACB30HG	+ .002 - .005	1. Cannot be shaved. 2. Cannot readily be installed in below-flush applications which require aerodynamic smoother except with specialized dimple tooling.
Steel Bolts	BACB30LU NAS583-590	+ .005 - .005	
Huck blind bolt	BACB30LA	+ .005 - .005	1. May be shaved. 2. Must be corrosion protected after shaving.
Huck blind bolt	BACB30LB	± .005	1. Must be corrosion protected.
① Contact applicable divisional staff unit for data on fasteners not included.			

Figure 17.31-1

17.32 COUNTERSINKING AND DIMPLING

On a direct cost-per-fastener basis, countersinking a hole is cheaper than dimpling. However, when the increased shear strength of dimpling joints is considered, the smaller quantity of fasteners required with dimpling may occasionally make the dimpled joint less expensive than one using countersinking. In addition, limitations such as thickness, material condition, accessibility, etc., apply to both processes and will, in part, influence choice.

17.321 COUNTERSINKING

Countersinking is necessary where sheet thickness is too great to use dimpling or in applications where the size or shape of an assembly does not permit access to dimpling equipment. Countersinking and dimpling are controlled by BAC 5049.

17.3211 MINIMUM SHEET THICKNESS

The minimum material thicknesses which are recommended for countersinking are shown in Figures 17.3211-1 and 17.3211-2. Sheets thinner than those listed must be dimpled. Sheets whose thickness is sufficient to countersink, may be dimpled if within the limits of Figure 17.322-2. These limits are not valid where integral fuel tank walling is a requirement - see 17.5.

The minimum sheet thicknesses are based on the minimum practical tolerances including tolerances that would provide a satisfactory countersink. Countersinking resulting in a sharp edge is poor design practice where service life is a factor. Consult Stress Unit for information regarding sheet thickness, fit and spacing that will insure satisfactory fatigue life for a specific design.

a. For use with shop manufactured countersunk rivets

MINIMUM SHEET THICKNESS FOR COUNTERSINKING ①												
T_1 = Thickness of sheet or sheets countersunk. T_2 = Thickness of top sheet held in place by flush head.												
Fastener Diameter	3/32	1/8	5/32	3/16	1/4	5/16	3/8	7/16	1/2	9/16	5/8	
Rivets, Flush Head	.040	.051	.064	.081	.125	.125	.156					
Rivets, Shop Head	.032	.040	.040	.050	.063	.063	.063					
SCREW, Flush Head	.051	.064	.081	.125								
SCREW, Shop Head	.032	.040	.050	.063								
Pin, Flush Head			.032	.066	.073	.093	.102	.112	.121	.131		
Pin, Shop Head			.049	.049	.049	.049	.057	.057	.066	.066		
Pin, Shop Head				.085	.106	.138	.167	.195	.222	.249	.279	
Pin, Shop Head				.057	.057	.057	.057	.066	.066	.066	.066	
Pin, Shop Head												

① Values apply to any combination of fastener and fastened material, and are based upon zero flushness. Where fastener head is permitted below flush, values of T_1 and T_2 shall be increased by an amount equal to the maximum permitted below flushness.

Figure 17.3211-1

b. For use with shop driven flush heads.

Figure 17.3211-2 T_1 values apply to both countersink and protruding head rivets, whose shanks are driven flush in a countersink sheet to a diameter of 1.5 times the shank diameter.

MINIMUM SHEET THICKNESS FOR COUNTERSINKING			
T_1 = Combined thickness of sheets. T_2 = Sheet thickness at the surface in contact with the manufactured countersunk head. T_3 = Sheet thickness at the surface in contact with the shop driven head.			
Rivet Size	T_1	T_2	T_3
1/8	.080	.040	.040
5/32	.110	.040	.050
3/16	.140	.050	.071
1/4	.190	.063	.090
5/16	.220	.063	.100

Figure 17.3211-2

17.3212 CALLOUT

A. HAS-COLE FASTENERS: Countersinking is called out by the letter "C" in the SW quadrant. See 17.213.

B. OTHER: Countersink holes, the flush head fasteners, bolts and screws, which are not covered by the callout printed in 17.213, shall be specified as follows:

1. For exterior, aerodynamic, high speed applications, where an assembly, do not dimple, countersink, or flush head.

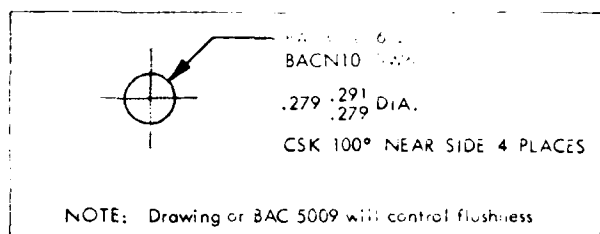


Figure 17.3212-1

2. Completely internal to the structure, countersink holes, bolts and screws, which are not covered by the callout printed in 17.213, shall be specified as follows:

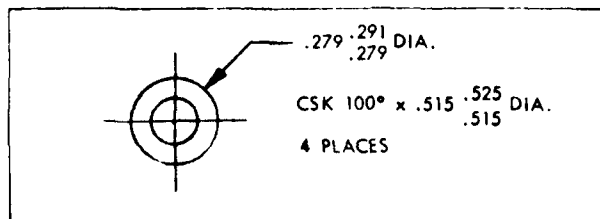


Figure 17.3212-2

17.3212 (Continued)

COUNTERSINK DIAMETERS FOR 100° FASTENERS NAS514, NAS583-590, BACB30LU, BACB30AB, BACB30BF		
Fastener Diameter	Countersink Diameter ①	Theoretical Flushness Limits - For Reference Only; Do not specify on drawing ②
No. 4	.225-.233 .225	+.000 -.009
No. 6	.280-.288 .280	+.000 -.009
No. 8	.335-.345 .335	+.000 -.012
3/16	.390-.400 .390	+.001 -.013
1/4	.515-.525 .515	+.001 -.015
5/16	.645-.657 .645	+.001 -.018
3/8	.775-.787 .775	+.001 -.020
7/16	.905-.920 .905	+.001 -.021
1/2	1.035-1.050 1.035	+.001 -.026

① A change of .001 in countersink diameter will affect flushness by approximately .00042.

② These limits are approximate because head sizes and tolerances for various fasteners are not identical. They represent variations of head diameter, head angle, countersink diameter and countersink angle.

Figure 17.3212-3

17.322 DIMPLING

Dimpling is used where sheet thicknesses are too small for countersinking and where the higher shear strength of a fastener in dimpled sheet will permit the use of fewer fasteners in a given joint.

Dimpled joints are either a combination of dimpled sheet and countersunk structure or of multiple thicknesses of dimpled sheet as shown in Figure 17.322-1.




Figure 17.322-1

A. Extruded, forged or machined sections shall not be dimpled.

B. Dimpled parts subject to fatigue and heavy vibration should be made from 2024-T3 in preference to 7075-T6 provided strength and other considerations permit.

C. Warpage of sheet during dimpling, due to metal expansion during forming, can be minimized by observing the requirements of 17.3221.

D. Warpage of dimpled joints due to rivet shank expansion can be minimized by use of countersunk structure and/or by non-expanding shank fasteners.

E. Thickness limits and allowables for simultaneous dimpling of multiple thicknesses may be obtained from the applicable staff unit. In such cases, the total thickness of sheets to be dimpled at one time is considered as a single thickness in Figure 17.322-2; drawing notes shall clearly designate areas which may be multiple dimpled.

MATERIAL THICKNESS LIMITS FOR DIMPLING

	MAXIMUM ①									MINIMUM							
	Dia	ALUMINUM		MAGNESIUM		CORROSION RESISTANT STEEL ③				Dia	.010	.016	.020	.025	.032	.040	.050
		Portable	Stationary	Portable	Stationary	Portable Annealed	1/4 H	Stationary Annealed	1/4 H								
CONVENTIONAL RIVETS (Except BAC-RISCE)	3/32	.050	.050	.050	.050	.050	.040	.050	.050	3/32	CAM						
	1/8	.063	.063	.063	.063	.063	.040	.063	.063	1/8	CA	M					
	5/32	.071	.071	.071	.071	.071	.040	.071	.063	5/32	CA	M					
	3/16	.071	.090	.090	.090	.090	.040	.090	.063	3/16	C	A	M				
	1/4	.063	.090	.125	.125	.100	.040	.125	.050	1/4		C	A	M			
	5/16	.063	.090	.125	.140	.091	.032	.125	.050	5/16		C	A		M		
BLIND RIVETS	1/8	.050	.050	.050	.050	.050	.040	.050	.050	1/8	CA	M					
	5/32	.063	.063	.063	.063	.063	.040	.063	.063	5/32	C	AM					
	3/16	.071	.080	.080	.080	.080	.040	.080	.063	3/16		CA	M				
	1/4	.063	.090	.125	.125	.100	.040	.125	.050	1/4			C	A	M		
SHEAR HEAD FASTENERS	3/16	.050	.050	.050	.050	.050	.040	.050	.050	3/16	CA	M					
	1/4	.071	.071	.071	.071	.071	.040	.071	.063	1/4	C	A	M				
	5/16	.063	.080	.080	.080	.080	.040	.080	.050	5/16		CA	M				
	3/8	.063	.090	.100	.100	.090	.040	.100	.050	3/8		C	A		M		
TENSION HEAD FASTENERS	# 8	.071	.080	.080	.080	.080	.040	.080	.063	# 8	C	A	M				
	# 10	.071	.100	.100	.100	.100	.040	.100	.063	# 10		C	A	M			
	1/4	.063	.090	.100	.140	.090	.040	.140	.050	1/4			C	A	M		
	5/16	.050	.080	.100	.160	.080	.032	.125	.050	5/16				C	A	M	
	3/8	.040	.063	.080	.125	.063	.025	.090	.040	3/8					C	A	M

① Above the heavy line is the maximum material thickness for obtaining a structural advantage over countersinking. Below the heavy line is the maximum material thickness within the dimpling machine forming capacity.

NOTE: Clearances for the stationary machine (CP-450 EA) and a typical portable dimpler are shown in Section 19. For other portable yokes see Standard Tools, Volume III.
Consult applicable C.A.D. staff unit for:

- (a) Limits for dimpling titanium, or materials other than those shown.
- (b) Limits when simultaneously dimpling multiple thickness of materials.

③ Austenitic Group which includes 301, 302, 321, 347.

C - Corrosion Resistant Steel
A - Aluminum
M - Magnesium

Figure 17.322-2

17.3221 EDGE MARGIN

Where a dimple is sufficiently coined to assure proper nesting a radial stress remains around the hole. The greater (less restricted) expansion between the hole and the edge causes distortion. This can be minimized by:

A. Adding 50 per cent to the design edge margin. For design edge margin see Section 18. Thicknesses less than .050 need only the design edge margin.

B. Adding a stiffening flange. The minimum flange heights should agree with DM 81, Section 1, or as listed for formed sections in the BAC standard pages. The flange must have sufficient flat surface for dimpling die contact.

The use of butt straps without a flanged edge is not recommended where no other stiffening member is present. Waviness in the skin splice will result because of sheet stretch due to dimpling and riveting unless stiffening restricts the waviness.

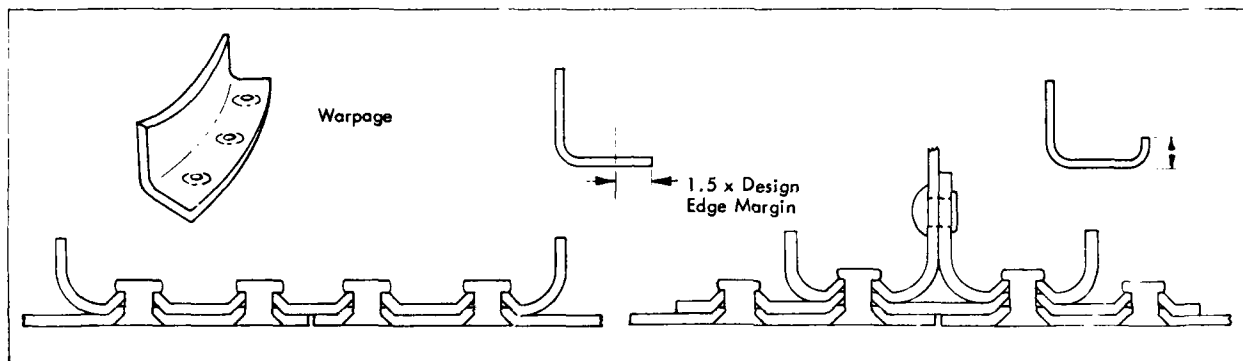


Figure 17.3221-1

17.3222 CALLOUT

A. NAS CODE FASTENERS. Dimpling is called out by the letter D in the SW quadrant. See 17.211.

B. OTHER. Dimpled holes for flush head fasteners such as bolts and screws which are not covered by NAS symbol callout shall be specified as follows:

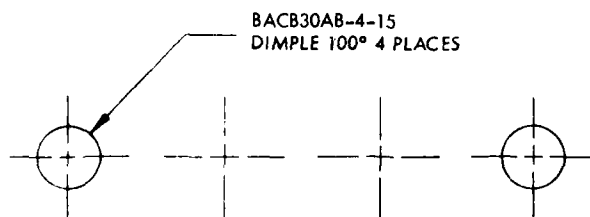


Figure 17.3222-1

C. DRAWINGS. Projects shall issue sealing installation drawings to define sealing requirements for each model airplane.

17.51 CALLOUT

The Project sealing installation drawings shall be referred to by a note SEAL PER DRAWING 29-00000 on all Project drawings requiring sealing provisions. Reference to BAC 5000, Process Specification for Sealing, shall be made as applicable on the sealing installation drawing. In addition, these drawings shall completely describe or illustrate all sealing requirements not included in BAC 5000.

17.52 TYPES

Type and levels are per BAC 5000.

17.53 MAXIMUM SPACING

See 17.5B.

17.5 SEALING

Fastener sealing information is found in:

A. BAC Process Specifications:

1. BAC 5000 Sealing (in general)
2. BAC 5047 Fastener Installation; Fluid Tight
3. BAC 5504 Integral Fuel Tank Structure Sealant
4. BAC 5732 Integral Water Tanks.

B. Documents as specified by Projects:

1. D 15248 Integral fuel tanks.

17.6 FASTENER USAGE CHARTS

The following usage charts provide convenient reference and comparative data for fasteners in common use. The BAC Standards (D-590) should be consulted for complete information.

17.61 NAS SYMBOL FASTENERS

In this classification those fasteners appear which are shown on drawings by NAS symbols.

17.611 SOLID SHANK STRUCTURAL RIVETS








SOLID SHANK STRUCTURAL RIVETS					
ILLUSTRATION	PART AND PAGE NUMBER		MATERIAL	SIZE RANGE	DESCRIPTION
	MS20470 80.90.1.2.1		AL 1100, AL ALLOY 5056, 2117, 2024, 2017	1/16 THRU 3/8	UNIVERSAL HEAD
	BACR15BB 80.90.6.8		2024, 2117, AL ALLOY	1/8 - 7/16	CLOSE TOLERANCE SHANK UNIVERSAL HEAD
	MS20615M 80.91.1.3.1		MONEL	1/16 - 7/16	CLOSE TOLERANCE CORROSION AND HEAT RESISTANT UNIVERSAL HEAD
	MS20426 80.90.1.1.1		AL 1100, AL ALLOY 5056, 2117, 2024, 2017	1/16 THRU 3/8	100° FLUSH HEAD
	BACR15BA 80.90.6.7		2117, 2024 AL ALLOY	1/8 - 7/16	CLOSE TOLERANCE SHANK 100° FLUSH HEAD
	BACR15CE 80.90.6.9		5056, 2017 AL ALLOY MONEL	3/32 - 1/4	SPECIAL LOW HEIGHT 100° SHEAR HEAD
	MS20427M 80.91.1.1.1		MONEL		CLOSE TOLERANCE SHANK CORROSION AND HEAT RESISTANT 100° FLUSH HEAD

Figure 17.611-1

17.612 LOCK BOLTS & HEX DRIVE BOLTS

These fasteners are recommended for use when a reduction in cost and weight is desired on permanent installations, provided the tensile loads do not exceed the values listed in 18.21. If the joint requires the high shear strength of these fasteners they are recommended in lieu of rivets because of greater rigidity and better clamp-up. The shear type has a head and collar of minimum size for use where loads are primarily shear, the tension type has a heavier head and collar.

The diameter tolerances for lockbolts: .0015 in. with swaged collars are per NAS618, while closer tolerances: .0005 in. and .0010 in. are offered with Hi-Lok fasteners (threaded collar). However, there is a higher cost associated with the Hi-Loks as compared to lockbolts. The pull-type lockbolts have a 1-inch pin tail. See 18.21 for allowables.

Pull-type shear lockbolts and Hi-Loks are intended for shear applications where tool clearance is adequate. They offer excellent clamping action and good sealing properties. Pull-type tensile lockbolts provide good residual tension and sealing properties. Stump-type tensile and shear lockbolts and Hi-Loks are recommended for applications where there is not sufficient tool clearance for pull-type lockbolts.















LOCK BOLTS & HEX DRIVE BOLTS - TENSION TYPE								
ILLUSTRATION	PART AND PAGE NUMBER	SIZE RANGE	STRENGTH 70°F (RATED) Fsu	MATERIAL	FINISH	MAX TEMP °F	MATING COLLAR	
	BAC B300X 80.81.6.15	5/32 - 1/4 5/16 - 3/8 5/32 - 3/8	95	ALLOY STEEL	CADMIUM	250° 250° 450°	NAS 1080 NAS 1080P NAS 1080H	80.80.5.5 80.80.5.5 80.80.5.5
	BAC B300X () A 80.81.6.15	5/32 - 1/4 5/16 - 3/8 3/16 - 1/4	95	A286	CADMIUM BARE	250° 250° 900°	NAS 1080 NAS 1080P BAC C30Q	80.80.5.5 80.80.5.5 80.80.6.30
	BAC B300P 80.81.6.23	5/32 - 3/8	44.5	ALUMINUM	ANODIZE	250°	NAS 1080L	80.80.5.5
	BAC B300Y 80.81.6.16	5/32 - 1/4 5/16 - 3/8 5/32 - 3/8	95	ALLOY STEEL	CADMIUM	250° 250° 450°	NAS 1080 NAS 1080P NAS 1080R	80.80.5.5 80.80.5.5 80.80.5.5
	BAC B300Y () A 80.81.6.16	5/32 - 1/4 5/16 - 3/8 3/16 - 1/4	95	A286	CADMIUM BARE	250° 250° 900°	NAS 1080 NAS 1080P BAC C30Q	80.80.5.5 80.80.5.5 80.80.6.30
	BAC B300Q 80.81.6.24	5/32 - 3/8	44.5	ALUMINUM	ANODIZE	250°	NAS 1080C	80.80.5.5
	BAC B300C 80.81.6.30	3/16 - 5/16 3/8 3/16 - 1/4 3/16 - 1/4	95	ALLOY STEEL	CADMIUM DIFF. CD. NT.	250° 250° 450° 900°	NAS 1080 NAS 1080D NAS 1080R BAC C30L	80.80.5.5 80.80.5.5 80.80.5.5 80.80.6.27
	BAC B300P 80.81.6.25	3/16 - 3/8	44.5	ALUMINUM	ANODIZE	250°	NAS 1080C	80.80.5.5
	BAC B300D 80.81.6.31	3/16 - 5/16 3/8 3/16 - 1/4 3/16 - 1/4	95	ALLOY STEEL	CADMIUM DIFF. CD. NT.	250° 250° 450° 900°	NAS 1080 NAS 1080D NAS 1080R BAC C30L	80.80.5.5 80.80.5.5 80.80.5.5 80.80.6.27
	BAC B300S 80.81.6.26	3/16 - 3/8	44.5	ALUMINUM	ANODIZE	250°	NAS 1080C	80.80.5.5
	BAC B300C 80.85.6.37	5/32 - 1/2	95	ALLOY STEEL	CADMIUM	450°	BAC C30X	80.85.6.28
	BAC B300C () A 80.85.6.36	5/32 - 1/2	95	A286	CADMIUM OR BARE	450° 900°	BAC C30X BAC C30Z	80.85.6.28 80.85.6.31
	BAC B300Y 80.85.6.40	5/32 - 1/2	95	ALLOY STEEL	CADMIUM	450°	BAC C30X	80.85.6.28
	BAC B300R () A 80.85.6.22	5/32 - 1/2	95	A286	CADMIUM OR BARE	450° 900°	BAC C30X BAC C30Z	80.85.6.28 80.85.6.31
	BAC B300Y 80.85.6.39	5/32 - 1/2	95	ALLOY STEEL	CADMIUM	450°	BAC C30X	80.85.6.28
	BAC B300A 80.85.6.8	3/16 - 3/8	44.5	ALUMINUM	ANODIZE	250°	BAC C30P	80.80.6.29
	BAC B300E 80.85.6.36	5/32 - 1/2	95	A286	CADMIUM OR BARE	450° 900°	BAC C30X BAC C30Z	80.85.6.28 80.85.6.31
	BAC B300Z 80.85.6.41	5/32 - 1/2	95	ALLOY STEEL	CADMIUM	450°	BAC C30X	80.85.6.28
 MB 20426 HEAD STYLE  AN 509 HEAD STYLE								

Figure 17.612-1

THIS PAGE IS BEST QUALITY PRACTICAL
FROM COPY FURNISHED TO DDC

17.612 LOCKBOLTS & HEX DRIVE BOLTS (Continued)

LOCKBOLTS & HEXDRIVE BOLTS - SHEAR TYPE									
	BAC B30GW 80.81.6.28	3/16 - 3/8	95	ALLOY STEEL	CADMIUM	250° 450°	BAC C30K NAS 1080E	80.80.6.26 80.80.5.5	
	BAC B30GW () A 80.81.6.28	3/16 - 3/8 3/16 - 1/4	95	A286	CADMIUM BARE	250° 900°	BAC C30K BAC C30L	80.80.6.26 80.80.6.27	
	BACB30GP 80.81.6.23	5/32 - 3/8	44.5	ALUMINUM	ANODIZE	250°	NAS 1080D	80.80.5.5	
	BAC B30GY 80.81.6.29	3/16 - 3/8	95	ALLOY STEEL	CADMIUM	250° 450°	BAC C30K NAS 1080E	80.80.6.26 80.80.5.5	
	BAC B30GY () A 80.81.6.29	3/16 - 3/8 3/16 - 1/4	95	A286	CADMIUM BARE	250° 900°	BAC C30K BAC C30L	80.80.6.26 80.80.6.27	
	BAC B30LD 80.81.6.37	3/16 - 3/8	44.5	ALUMINUM	ANODIZE	250°	BAC C30K () F	80.80.6.26	
	BAC B30FM 80.85.6.1	5/32 - 1/2	95	ALLOY STEEL	CADMIUM	250°	BAC C30M	80.85.6.15	
	BAC B30FM () A 80.85.6.1	5/32 - 1/2	95	A286	CADMIUM OR BARE	250° 800°	BAC C30M BAC C30AB*P	80.85.6.15 80.85.6.33	
	BAC B30GZ 80.85.6.7	3/16 - 3/8	44.5	ALUMINUM	ANODIZE	250°	BAC C30P	80.85.6.16	
	BAC B30MY 80.12.6.101	5/32 - 1/2	95	6AL-4V TITANIUM	CADMIUM	250°	BAC C30N	80.85.6.15	
	BAC B30FN 80.85.6.2	5/32 - 1/2	95	ALLOY STEEL	CADMIUM	250°	BAC C30M	80.85.6.15	
	BAC B30FN () A 80.85.6.2	5/32 - 1/2	95	A286	CADMIUM OR BARE	250° 800°	BAC C30M BAC C30AB*P	80.85.6.15 80.85.6.33	
	BAC B30HA () R 80.85.6.8	3/16 - 3/8	44.5	ALUMINUM	ANODIZE	250°	BAC C30P () R	80.85.6.16	
	BAC B30NW 80.85.6.38	5/32 - 1/2	95	6AL-4V TITANIUM	CADMIUM	250°	BAC C30M	80.85.6.15	

 MS 20426 HEAD STYLE

MS 20426 HEAD STYLE

Figure 17.612-2

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

17.613 BLIND FASTENERS

Blind fasteners are used primarily where one side of the assembly is inaccessible for the installation of conventional fasteners. For high corrosion areas, see A266 self-plugging rivets. For clearances and typical installations see Section 19.

Drawing details shall be per 17.62.

Male size callout for Group I shall be per 17.25.

Male size for Group I and Group II shall be per BAC5004 and need not be specified on drawing.

Blind fasteners are divided into three groups according to their applications.

A. (GROUP I). These are high strength steel structural blind fasteners which may be used with weight savings in place of bolts and plate nuts in permanent lockout areas. Fasteners in this group are BAC600A and BAC600B blind locknuts. See Fig. 17.613-1. They are subject to the following limitations:

1. Use primarily in shear.
2. Use where the fastener is a part of the permanent structure and is not subject to removal.
3. Use only where standard fasteners are not suitable.
4. Do not use where failed fasteners could fall into an intake.
5. Design allowables not listed must be substantiated by test data.
6. With joints of unequal sheet thicknesses, the stress allowable shall be the one that applies to the sheet with the lower allowable.



STRUCTURAL BLIND FASTENERS—BOLTS						
	AS 1398A BOLT 1398A-1	5/16 - 3/8	ALLOY STEEL	CADMIUM	400°	HIGH STRENGTH NON-HOLE FILLING
	AS 1398B BOLT 1398B-1	5/16 - 3/8	ALLOY STEEL	CADMIUM	400°	

Figure 17.613-1

B. (GROUP II). These are lower strength aluminum alloy and monel blind fasteners which may be used in areas and for applications where conventional rivets cannot be used. They are subject to the following limitations as Group II fasteners and to the following restrictions: per NAS 1392.

Do not use in high surface fatigue brackets, wing or control cable attachment fittings, landing gear fittings.

2. Do not use for fluid tight joints.
3. Chemically expanding (explosive) blind rivets may be used only in all-metal or non-inflammable media.

C. (GROUP III). These are non-structural blind fasteners which may be used for lightly loaded applications. They are subject to the same limitations as Group II fasteners.







BLIND FASTENERS—RIVETS						
ILLUSTRATION	PART & PAGE NUMBER	SIZE RANGE	MATERIAL	FINISH	MAX TEMP °F	DESCRIPTION
	AS 1398A RIVET 1398A-1	1/8 - 1/4	5052 ALUMINUM	ANODIZED	250	The minimum blind side sheet thickness allowed when using NAS 1398 or NAS 1399 blind rivets is D/4, where D equals the hole diameter.
	AS 1398B RIVET 1398B-1	1/8 - 1/4	5052 ALUMINUM	ANODIZED	250	
	AS 1398C RIVET 1398C-1	1/8 - 1/4	7050 ALUMINUM	CADMIUM	400	
	AS 1398D RIVET 1398D-1	1/8 - 1/4	5052 ALUMINUM	ANODIZED	250	Hole filling and locked stem
	AS 1398E RIVET 1398E-1	1/8 - 1/4	5052 ALUMINUM	ANODIZED	250	
	AS 1398F RIVET 1398F-1	1/8 - 1/4	7050 ALUMINUM	CADMIUM	400	
	AS 1398G RIVET 1398G-1	1/8 - 1/4	5052 ALUMINUM	ANODIZED	250	Non-hole filling locked stem - for thin sheet installations
	AS 1398H RIVET 1398H-1	1/8 - 1/4	5052 ALUMINUM	ANODIZED	250	
	AS 1398I RIVET 1398I-1	1/8 - 1/4	7050 ALUMINUM	CADMIUM	400	Non-structural Hollow rivet used only for nut plate attachment
	AS 1398J RIVET 1398J-1	1/8 - 1/4	7050 ALUMINUM	CADMIUM	400	

Figure 17.613-2

-88-
THIS PAGE IS BEST QUALITY PRACTICABLE
FIGURE 17-621 FURNISHED TO DOD

17-62 THREADED FASTENERS

17-621 BOLTS

For further information, refer to Figure 17-621 and the 4-page comparative chart on page 88. For more information on standard parts, for complete specifications, and for references, see PAC Standards, 1-1976. Other references are given in the following references.

1. **Specification for Standard Parts for Federal Services**, 1976, Department of Defense, Washington, D.C.

2. **Specification for Standard Parts for General Services Administration**, 1976, General Services Administration, Washington, D.C.

3. **Specification for Standard Parts for the Department of Defense**, 1976, DOD, Washington, D.C.

4. **Specification for Standard Parts for the Department of Defense**, 1976, DOD, Washington, D.C.

5. **Specification for Standard Parts for the Department of Defense**, 1976, DOD, Washington, D.C.

6. **Specification for Standard Parts for the Department of Defense**, 1976, DOD, Washington, D.C.

Threaded Fasteners are available in alloy steel, corrosion resistant steel, and titanium.

Alloy steel bolts shall be used whenever possible in structural applications. Tensile strengths of 160 to 280 ksi and 1/2" and larger diameters are available in standard bolts.

In primary structural applications, alloy steel bolts in sizes 1/2" and larger shall be used in accordance with the applicable design standard.

Corrosion resistant alloy steel bolts are available in tensile strengths up to 160 ksi. They are primarily used in applications where corrosion resistance is required.

Corrosion resistant alloy steel bolts are available in tensile strengths up to 160 ksi. They are primarily used in applications where corrosion resistance is required.






PROTRUDING HEAD STRUCTURAL BOLTS-ALLOY STEEL													
ILLUSTRATION	PART PAGE NUMBER AND CLASS	STRENGTH (RATED)			SIZE RANGE	SHANK					HEAD		
		70°F F _{tu}	70°F F _{tu}	MAX TEMP °F		DRILLED	UNDRIILLED	DRILLED	UNDRIILLED	LONG	TWO LENGTH	FINISH	MATERIAL
	BAC B30N 90.10.6.121 160T	95	125	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.121 95S	95	125	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.122 156S	95	125	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	MARAGING STEEL
	BAC B30N 90.10.6.122 125S	125	125	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	H-11 STEEL
	BAC B30N 90.10.6.123 180T	100	180	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.123 220T	125	220	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	H-11 STEEL
	BAC B30N 90.10.6.123 260T	156	260	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	MARAGING STEEL
	BAC B30N 90.10.6.123 95S	95	125	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.124 160T	95	160	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.124 160T	95	160	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.124 160T	95	160	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
	BAC B30N 90.10.6.124 95S	95	125	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	ALLOY STEEL
PROTRUDING HEAD STRUCTURAL BOLTS - CORROSION RESISTANT & ANTI-MAGNETIC													
	BAC B30N 90.10.6.125 95S	95	80	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.125 160T	95	160	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.125 160T	95	160	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.125 95S	95	80	450P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.126 110S	110	125	800P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.126 110S	110	125	800P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.126 110S	110	125	800P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286
	BAC B30N 90.10.6.126 110S	110	125	800P	10-32 THRU 1-1/4	X	X	X	X	X	X	X	A-286

Figure 17-621-1

THIS PAGE IS BEST QUALITY PRACTICAL
FROM COPY FURNISHED TO DDC

17.621 BOLTS

PROTRUDING HEAD STRUCTURAL BOLTS - CORROSION RESISTANT & ANTI-MAGNETIC (CONTINUED)															
ILLUSTRATION	PART PAGE NUMBER AND CLASS	STRENGTH (RATUL)		MAX TEMP °F	SIZE RANGE	SHANK HEAD THD LENGTH FIN SH									
		70°F F _{su}	70°F F _{tu}			1/2"	3/8"	1/4"	3/16"	1/8"	5/16"	3/8"	1/2"	5/8"	MATERIAL
	200T			400	1/2"-5/8"										GROUP VII
	160T			400	1/2"-5/8"										GROUP VII
	95S			400	1/2"-5/8"										GROUP VII
	95S			400	1/2"-5/8"										GROUP VII
	160T			400	1/2"-5/8"										GROUP VII
	160T			400	1/2"-5/8"										GROUP VII
FLUSH HEAD STRUCTURAL BOLTS - ALLOY STEEL															
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
FLUSH HEAD STRUCTURAL BOLTS - CORROSION RESISTANT & ANTI-MAGNETIC															
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
	95S			400	1/2"-5/8"										GROUP I
<div> PARTICULAR DETAIL LIMITED BY NUT CAPABILITY AVAILABLE IN SELF-LOCKING SERIES USE IN PERMANENT INSTALLATIONS ONLY USE ONLY NUT WITH DRY FILM LUBRICANT WITH TITANIUM FASTENER </div>															

Figure 17.621-2






PROTRUDING HEAD SCREWS - ALLOY STEEL															
ILLUSTRATION	PART PAGE NUMBER AND CLASS	STRENGTH (RATED)		MAX TEMP °F	SIZE RANGE	SHANK		HEAD	THD LENGTH		FINISH			MATERIAL	MATING NUTS
		70°F F ₄₀	70°F F ₁₀			DRILLED UNDRILLED	DRILLED UNDRILLED		LONG SHORT	CADMIUM	PASSIVATED	CHLORIDE RESISTANT	FLUOROPOLYMER		
	MC 16956 80.1.1.11 125T	—	125	450°	4-40 THRU 1/8" PLATE (1-20)	X	X							ALLOY STEEL	GROUP II
	MC 16957 80.1.1.12 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL	GROUP II
	MC 16958 80.1.1.13 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL	TAPPEL NUTS SELF-LOCKING
	BAC S128R 80.20.6.18 125T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL	GROUP II
	BAC S128R 80.20.6.18 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL	TAPPEL NUTS AND WASHERS
	BAC S128R 80.20.6.18 125T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL & TITANIUM	GROUP II
	MC 16956 80.1.1.11 125T	—	125	450°	4-40 THRU 1/8" PLATE (1-20)	X	X							ALLOY STEEL	GROUP II
	MC 16957 80.1.1.12 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL & TITANIUM	GROUP II
	MC 16958 80.1.1.13 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL & TITANIUM	TAPPEL NUTS SELF-LOCKING
	BAC S128R 80.20.6.18 125T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL	GROUP II
	BAC S128R 80.20.6.18 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL & TITANIUM	GROUP II
	BAC S128R 80.20.6.18 160T	—	125	450°	4-40 THRU 1/8"	X	X							ALLOY STEEL & TITANIUM	TAPPEL NUTS SELF-LOCKING
THESE FASTENERS HAVE NO GRIP AND ARE CONSIDERED FULL THREADED															

PROTRUDING HEAD SCREWS - CORROSION RESISTANT & ANTI-MAGNETIC															
ILLUSTRATION	PART PAGE NUMBER AND CLASS	STRENGTH (RATED)		MAX TEMP °F	SIZE RANGE	SHANK		HEAD	THD LENGTH		FINISH			MATERIAL	MATING NUTS
		70°F F ₄₀	70°F F ₁₀			DRILLED UNDRILLED	DRILLED UNDRILLED		LONG SHORT	CADMIUM	PASSIVATED	CHLORIDE RESISTANT	FLUOROPOLYMER		
	MC 16956 80.1.1.11 80T	—	80	750°	4-40 THRU 1/8" PLATE (1-20)	X	X							CHOC	
	MC 16957 80.1.1.12 80T	—	80	750°	4-40 THRU 1/8"	X	X							CHOC	TAPPEL NUTS ARE INSTALLED
	MC 16958 80.1.1.13 80T	—	80	750°	4-40 THRU 1/8"	X	X							CHOC	TAPPEL NUTS SELF-LOCKING
	BAC S128R 80.20.6.18 125T	—	75	700°	4-40 THRU 1/8"	X	X							CHOC	
	BAC S128R 80.20.6.18 160T	—	75	750°	4-40 THRU 1/8"	X	X							CHOC	TAPPEL NUTS SELF-LOCKING
	BAC S128R 80.20.6.18 125T	—	125	800°	4-40 THRU 1/8"	X	X							CHOC	

• LIMITED BY MATERIAL CAPABILITY • USE IN PERMANENT INSTALLATIONS ONLY • USE ONLY NUTS WITH DRY FILLS LUBRICANT WITH TITANIUM FASTENERS

(1) - LIMITED BY NUT CAPABILITY (2) - USE IN PERMANENT INSTALLATIONS ONLY (3) - USE ONLY NUTS WITH DRY FILM LUBRICANT WITH TITANIUM FASTENERS

Figure 17 621 3

FLUSH HEAD SCREWS - ALLOY STEEL															
		NAC 514 80.2.5.1 125T	—	125	450°	4-40 THRU 1/8"	/	X	X	X	X	X	X	ALLOY STEEL	GROUP II
FLUSH HEAD SCREWS - CORROSION RESISTANT & ANTI-MAGNETIC															
		BAC S128R 80.20.6.30 125T	—	125	450°	4-40 THRU 1/8"	X	X	X	X	X	X	X	CHOC	GROUP II
* (4) - SEE IN PERMANENT INSTALLATIONS ONLY  USE ONLY NUTS WITH DRY FILM LUBRICANT WITH TITANIUM FASTENERS															

(1) - LIMITED BY NUT CAPABILITY (2) - USE IN PERMANENT INSTALLATIONS ONLY

(3) - USE ONLY NUTS WITH DRY FILM LUBRICANT WITH TITANIUM FASTENERS

Figure 17 621 4

FROM COPY FURNISHED TO DDC

17.621 BOLTS (Continued)





TAPERED BOLTS - SHEAR TYPE							
ILLUSTRATION	PART AND PAGE NUMBER	SIZE RANGE	STRENGTH 70°F (RATED) Fsu	MATERIAL	FINISH	MAX. TEMP. °F	MATING COLLAR
	BAC B30KD 80.2.6.42	3/16 - 1	108 110	ALLOY STEEL A 286	CADMIUM PASSIVATED	450° 800°	BACN10HY(M) 80.60.6.50 BAC N10HY(A) 80.60.6.50
	BAC B30MU 80.13.6.6	3/16 - 1	95	6AL-4V TITANIUM	CADMIUM	450°	BAC N10HY(M) 80.60.6.50
	BAC B30PD 80.2.6.51	3/16 - 1	108 110	ALLOY STEEL A 286	CADMIUM PASSIVATED	450° 800°	BACN10HY(M) 80.60.6.50 BAC N10HY(A) 80.60.6.50
	BAC B30PM 80.12.6.9	3/16 - 1	95	6AL-4V TITANIUM	CADMIUM	450°	BAC N10HY(M) 80.60.6.50
TAPERED BOLTS - TENSION TYPE							
	BAC B30PD 80.2.6.53	3/16 - 1	108	ALLOY STEEL	CADMIUM	450°	BACN10RD 80.60.6.57.1
	BAC B30PD(A) 80.2.6.53	3/16 - 1	110	A 286	Cadmium Silver	450° 900°	BACN10RD(AH) 80.60.6.57.1 BACN10RD(A) 80.60.6.57.1
	BAC B30PE 80.1.6.126	3/16 - 1	108	ALLOY STEEL	CADMIUM	450°	BACN10RD 80.60.6.57.1
	BAC B30PE(A) 80.1.6.126	3/16 - 1	110	A 286	Cadmium Silver	450° 900°	BACN10RD(AH) 80.60.6.57.1 BACN10RD(A) 80.60.6.57.1

Figure 17.621-5

17.6211 TITANIUM FASTENERS

A Comparison of titanium and steel

TITANIUM - STEEL COMPARISON		
Item	Titanium	Steel
Weight	163 lbs/Cu in	.284 lbs/Cu in (74% heavier)
Corrosion Resistance	Equal to CRES	Cadmium plated steel not as good as titanium
Galvanic Corrosion	Equal to Cadmium plate	Cadmium plate - Fair
Magnetic Permeability, μ	1.00005	Alloy Steel = High 302 CRES = 1.003 304 CRES = 1.020 A286 = 1.007
Alloy	6AL 4V	See procurement specs.
Temp Limits	450° (Limit of Cadmium Plate)	450°F (Limit of Cadmium plate)
Quality Control	Equal to steel plus fatigue tests	See procurement specs for requirements.

Figure 17.6211-1

B 1 General Information

1. Drawings shall show fastener installation per Boeing process specifications BAC 5004, BAC 5009 and BAC 5054 as applicable. Drawings should specify that the torque for nuts used on titanium bolts be in accordance with BAC 5009.
2. Titanium, rubbing or sliding against itself or many other materials, such as alloy steels and corrosion resistant steels, will gall readily. This results in the creation of severe stress risers leading to early fastener failure. Avoid designs which result in motion on the bolt surface.
3. Titanium bolts shall not be used in close reamed holes in steel or composite steel aluminum structure where tightening from the bolt head side is required. Galling of the fastener shank usually results in these installations and creates stress risers leading to early bolt failure.

C. Usage

Titanium fasteners are primarily used where weight is the prime consideration (see Figure 17.6211-1 for weight comparison). Their use is subject to the following limitations:

1. Only titanium fasteners shown in Figure 17.6211-1, 2, 4, and 5 shall be used. These range from .19 inch diameter through 1 inch diameter.
2. Fasteners of .19 inch diameter shall be used only if the cost/lb. conforms to the specific requirement of the Project involved.
3. The rated ultimate strengths for titanium fasteners shall be in accordance with 18.21 and 18.22.
4. The joint strength and edge margin tables in 18.23.1, 18.23.3, and 18.23.4 shall be used for titanium fastener designs as applicable.
5. BACB30MR, titanium tension fasteners, from .25 inch diameter through .75 inch diameter, may be used in primary tension applications.
6. The use of titanium in contact with liquid oxygen is prohibited since either the presence of fresh surface, as produced by tensile rupture, or impact may initiate a violent reaction. Impact of the surface in contact with liquid oxygen may result in a reaction at energy levels as low as 10 ft lb. In gaseous oxygen, and from temperatures of 250°F and above, a partial pressure of about 50 psi is sufficient to ignite a fresh titanium surface.
7. Titanium fasteners shall not be used for single joint connections such as control rod and attachment, structural pin joints, or applications where the fastener is subjected to rotating or sliding motion because of potential fretting or galling of the titanium bolt.
8. Titanium bolts shall be used only in conjunction with steel nuts that are lubricated with a molybdenum disulfide dry film meeting the requirements of BMS 3.8. The proper nut combinations are tabulated in Figure 17.6211-1, 2, 4, and 5.
9. Collars for shear type and tension type titanium hex drive bolts are prescribed in Figure 17.612-1 and 2.
10. Nuts for Taperlok fasteners are prescribed in Figure 17.621-5.

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

17.6212 SELF-LOCKING BOLTS

Self locking bolts shall be used in installations which do not allow the use of self locking or castellated nuts (flapped holes, etc.).

1. The locking action of self locking bolts may be achieved by two methods:

1. A plastic insert installed on the threaded portion of the bolt (the use of this type is limited to temperature environments upto 250°F).
2. Mechanical displacement of the thread pitch diameter (the temperature limitations of this type are controlled by the bolt material or finish).

Both types of self locking bolts obtain the locking action from friction created by the interference between the mating threads. Locking torque and other performance requirements are subject to conformance to MIL F 18240.

B. Self Locking Externally Threaded Fasteners shall be Subject to the Following Limitations:

1. Fasteners shall be selected and used in a manner that will permit functional and dimensional interchangeability with a part that has only the attributes described and defined by the applicable standards and specifications.
2. Fasteners shall be used only in applications that permit engagement with complete internal threads over the minimum external thread.
3. Self locking externally threaded fasteners shall not be used as follows:
 - a. At joints in control systems, at single attachments, or where loss of the fastener would affect safety of flight.
 - b. As an axis of rotation for another part unless the fastener is held by a positive locking device that requires shearing or rupture of material before torsional loads would be applied to the fastener in such a manner as to relieve the initial stresses of the assembly or turn the fastener loose.

EXAMPLE Bearings, Bushings, Clamp up bushings, Pulleys, Cranks, Levers, Linkages, Hinge pins, Axles, Shafts, Spindles, Gears, Cams, Cam Followers, Sliding mechanisms, and Pivot points.

c. At any single bolted structural joint which serves as a primary load path, the failure which would endanger the safety of personnel or would render the equipment inoperative or cause its destruction.

EXAMPLE Fixed joints, Tie rods, Struts (fixed length members) Wing attachments to fuselage, Stabilizer surface attachments, Longeron joints, Ailting gear joints, and Engine mounts

4. Fasteners that contain a self locking element design which incorporates an insert or part that is non-metallic shall not be used in parts where the locking element will encounter keyways, slots, cross-holes or thread interruptions.
5. Fasteners shall not be used in assemblies which require that fasteners be removed for routine servicing purposes more times than the number of removals specified in the approved locking element or fastener specification or standard.
6. Fasteners shall not be used on jet engine aircraft in locations where a loose fastener could fall or be drawn into the engine air intake scoop.
7. Fasteners that have had the locking element reworked or reprocessed by other than an approved manufacturer shall not be used by contractors or field maintenance personnel of the services.
8. Self locking elements classified as 250°F are intended for use at ambient temperature conditions (-65°F to 250°F) and are designed to function satisfactorily at temperatures thru that range.
9. When fasteners are used in applications requiring controlled torque, such as clamping molded gaskets in fuel cells, consideration must be given to the maximum and minimum locking torque permitted by the locking element or fastener specification or standard approved for use.

17.6212 SELF-LOCKING BOLTS (Continued)

10. For the self-locking element designs that incorporate an insert or part that is non-metallic, the entering end of threaded holes used in conjunction with self-locking externally threaded fasteners shall be countersink 90 to 110 degrees. This countersink shall have a minimum diameter .015 in. larger than the major thread diameter of fastener. This is to prevent first thread from cutting the self-locking element.
11. Unthreaded holes or portions of holes thru which the locking device of fastener must pass shall have a minimum diameter sufficient to clear the locking element if the specifications of the fastener permit the locking device to protrude beyond the maximum major diameter of the thread.
12. Self-locking externally threaded fasteners shall not be used with pins, nuts, castellated nuts, or self-locking nuts.

17.6213 NON-STANDARD THREADED FASTENERS

A. DEFINITION

Bolts, screws and threaded pins which are unavailable under MS, NAS, or BAC standards because of one or more distinguishing features are classified as non standard.

B. USAGE

Avoid the design of special fasteners for the following reasons. Compared to standard fasteners, higher costs are normally incurred in procuring and using non standard items because of low volume, special identification and inspection procedures and possible requirements for customer approval. In some instances, development and qualification testing are necessary.

Customer procurement of replacement parts becomes more complex and costly.

2. When usage of non standard fasteners is necessary, their design shall be directed toward achieving the maximum degree of similarity to their standard counterparts to take advantage of existing support, hardware and technology available from the production of standard parts.

Prudent selection of the part characteristics and manufacturing options allowed will usually result in higher quality parts at the minimum cost.

C. DESIGN PRACTICE

Non standard bolts, screws and pins shall be designed in accordance with the following considerations:

1. Specifications

Bolts, screws and pins, which are similar in function, strength, performance rating and geometry to standard bolts shall, to the extent practical, be designed to utilize the corresponding procurement specification for standard bolts selected from Figure 17.6213-1. Where MIL-S-7742 threads are called out, show threads in accordance with MIL B 7838 as allowable option. It is not permissible to substitute MIL S 7742 threads for MIL B 7838 threads. For processes which must vary from the bolt specification (heat treatment, plating, etc.), call out a specification in accordance with Procedures Manual 9481 Section 10.092. See Section 18.21 for description of various thread forms.

2. Highly reliable bolts and pins

All ferromagnetic bolts and pins, which are used in areas where the failure of such a part would endanger personnel or would become a hazard to the functional operation of the vehicle, are classified as "highly reliable" and must undergo magnetic particle inspection per BAC 5424, Class A. A special note on the drawing is necessary to indicate such a requirement.

Avoid hollow shank fuse bolt design because it has proven impractical to control processing (particularly heat treatment) to an adequate level to maintain failure strength of fuse within narrow design limits. Whenever possible, use conventional bolt design as fuse bolts. Allow a minimum tensile strength variation of $\pm 15,000$ psi.

3. Materials

Although some of the specifications listed in Figure 17.6213-1 provide a larger schedule of materials, it is desirable to standardize and limit the materials selection to only those shown in the Figure 17.6213-1. See item 7.c for drawing requirements.

17.6213 NON-STANDARD THREADED FASTENERS (Continued)

4. Forged and rolled features

Forged heads, rolled head-to-shank fillet radius, and rolled threads are required for high strength and fatigue applications. The use of headed blanks is preferred. Where strength and/or fatigue considerations permit, allow machining from bar stock. A note allowing for optional machining should appear on the drawing.

5. Standard wrenching

Design permitting, non standard bolts should utilize standard wrenching by specifying head dimensions which conform to the most bolt standards. This will avoid added fabrication and maintenance costs.

6. Marking

Each separate part shall be marked in accordance with PM 5485, Section 5.6. For fasteners, head marking is normally raised or depressed in protruding heads and depressed on flush heads. Head marking should indicate manufacturer's identification.

7. Drawings

a. Separate drawings

Each separate part shall be detailed on separate drawings per PM 5485, Section 1.5.1. All differences from the standard shall be detailed on the drawing.

b. Drawing type

Non standard bolts whose variation from a standard is completely designed by Boeing, may be released by the project on a production release drawing.

Non standard bolts with some features which are varied in design should be released on specification control drawings per PM 5485, Section 1.5 and 1.1.

Non standard bolts with a requirement that absolute control of replacement bolts after delivery of end product to customer be from specified sources, should be released on a source control drawing.

c. Material column

For non standard bolts which are essentially modified standard bolts, the material column should only show materials selected from Figure 17.6213-1, whereas highly reliable parts are limited to H-11 (AMS 6485) or 4340M (BMS 7-26).

d. Stock size

It is preferable to make non standard bolts from headed blanks with an option for machining from bar stock. It is therefore desirable to indicate a "suggested stock size" for the optional machining process in the stock size column.

e. Source control

If it is required to limit the sources for reasons of special manufacturing processes, qualification tests, etc., a note should appear on the drawing as follows:

Procure from XYZ Bolt Company, Address, City, State.

H.T. Range (ksi)	Material ②	Application	Procurement Spec.	Thread Spec.	Type of Finish ①
160 - 180	④ 4340, 8740	Tension or Shear	BPS-F-69	MIL-S-7742 MOD	QQ-P-416 Type II, C1.3
180 - 200	④ 4340, 8740	Tension or Shear	BPS-F-69	MIL-S-8879 MOD	Cod. Fluob. per NAS672 or AMS2416
220 - 240	H-11	Tension or Shear	BPS-F-69	MIL-S-8879 MOD	
270 - 300	4340M	Tension or Shear	③	MIL-S-8879 MOD	BAC5804
160 - 180	A - 286 CRES	Tension or Shear	BPS-F-69	MIL-S-7742 MOD	QQ-P-416 or Passivated
200 - 220	A - 286 CRES	Tension or Shear	BPS-F-69	MIL-S-8879 MOD	

NOTE: The use of headed blanks is preferred.

Where strength and/or fatigue considerations permit, allow machining from bar stock.

① Temperature limitation 450°F. For temperatures up to 900°F use AMS 2416 finish. Other finishes may be specified if needed.

② Materials Specifications: 4340 per MIL-S-5000, 8740 per MIL-S-6049, AMS6322, 4340M per BMS 7-26C1.2. A-286 per AMS5737, H-11 per AMS6487

③ Consult Staff Unit for recommendations.

④ Use AISI 8740 or 4340 for bolt sizes through 5/8 and AISI 4340 only for sizes over 5/8.

Figure 17.6213-1

17.6214 SPECIALLY SURFACED STEEL BOLTS

Specially surfaced steel bolts, pins and studs shall be used for applications where galling would occur with standard cadmium plated steel bolts. See Book 81, Section 14 for recommended surface treatments.

17.6215 BOLTS WITHOUT COTTER HOLES

Bolts without cotter holes shall be called for when used with self locking nuts. See the code or example of part number on NAS and BAC standard pages for proper designation of bolts without cotter holes.

17.6216 OVERSIZE BOLTS

See BAC 5004 and BAC 5009 for a list of oversize bolts, lockbolts, lock shear rivets and hole sizes.

Oversize bolts shall be used for repair work only. They shall not be used in new design, and shall not be called for on drawings. However, fittings should be designed large enough to permit the use of oversize bolts in the shops or replacement by the next larger size standard bolt in service repair. Clearance and edge margin for the next larger size standard bolt must be considered in order to avoid replacement of an entire fitting due to damage of a bolt hole.

17.6217 RADIUS CLEARANCE

Due to the large head to shank radii on some protruding head fasteners, e.g., NAS 1303 Series, BACB30MT, BACB30LM Series, etc., a clearance problem exists. Radius clearance may be obtained by countersinking the structure or adding a washer under the head (preferred).

For structural reasons a clearance shall be provided for Class I and Close Fit holes as described below. Radius clearance for Class II and Class III holes is not a structural problem, however the design should provide ample clearance.

Approximately .008 chamfer can be obtained by noting

BREAK SHARP EDGES OF FASTENER HOLES
ON ENTERING SIDE PER BAC 5300

Where washers are used to provide clearance:

Use an .005 thick aluminum washer (AN 960) if loss of preload is of no concern. Use a countersunk steel washer MS 20002C, BAC W10AKC if loss of preload is of concern. Drawing notes shall specify the direction of countersink face to mate with the fastener radius.

BAC W10AKC washers may be used under the head of BACB30MT bolts.

17.6218 BOLTED SLOPING SURFACES

Self-aligning washers, BACW10B1, shall be used on bolted sloping surfaces. The maximum slope is 8° from perpendicularity with the axis of the bolt hole.

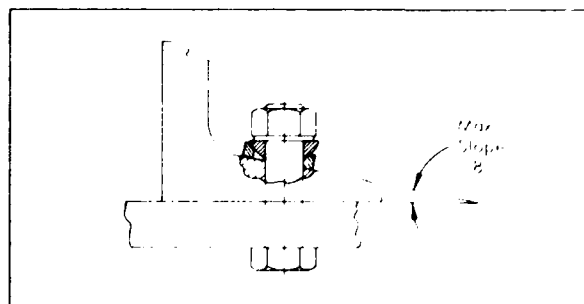


Figure 17.6218-1

17.622 SCREWS

17.6221 TAPPING SCREWS

A. LIMITATIONS for Use per ANS 10087 (Airborne Application, Tapping Screws Shall Not be Used Under the Following Conditions:

1. As fasteners for the fabrication of primary structure
2. Where the joint is subject to rotation which would tend to loosen the screw
3. As fasteners for structure or accessories where failure might result in danger or damage to the airplane or personnel
4. Where loss would permit the opening of a joint to air flow or leakage.
5. Where required to cut their own threads and are subsequently subject to replacement without increase in diameter size
6. Where subject to corrosive mediums, such as exhaust gas, salt spray, etc.

B. CLEARANCE HOLES

Clearance holes are used as necessary to permit parts to be drawn together and to allow tolerances for matching hole patterns. See Figure 17.6221-1

17.6221 (Continued)

SIZE	MAJOR DIAMETER	CLEARANCE HOLE	PROTRUDING LENGTH	
			THREAD FORMING SCREW	THREAD CUTTING SCREW
No. 2	.086	.106 .111 .106	①	.16
No. 4	.112	.128 .133 .128	.27	.21
No. 6	.138	.157 .167 .157	.32	.25
No. 8	.164	.182 .192 .182	.38	.25
No. 10	.190	.209 .219 .209	.46	.32
No. 12	.216	.234 .244 .234	.49	①
No. 14	.242	.261 .276 .261	.55	①
1/4	.25	.261 .276 .261	①	.37
① SCREWS NOT AVAILABLE IN THIS SIZE				

Figure 17.6221-1

C. LENGTH

The length of tapping screws installed in sheet assemblies shall be such that at least two complete threads of the grip extends beyond the assembly. Select standard lengths by adding the "protruding lengths" shown in Figure 17.6221-1 to the material thicknesses. These "protruding lengths" include allowance for minus tolerances on the screw. Standard screw lengths are .250, .312, .375, .50, .62, .75, .875, 1.00, 1.25, 1.50, 1.75, and 2.00. Both length and diameter are indicated by the MS dash number. In MS 24618 21, "21" indicates a diameter of .138 (No. 6 screw) and a length of .75.

D. MATERIAL AND CORROSION PREVENTION

Steel screws are cadmium plated. Corrosion resisting steel screws are passivated. Tapping screws used in aluminum alloys shall be installed with a phenolic or aluminum washer. The washer and screw shall be coated with zinc chromate paste before insertion so as to completely seal the connection.

17.62211 THREAD FORMING SCREW

A. TYPE

① TYPE A (STD PAGE NO. 80.30.1)			
MS24615	STEEL	82	
MS24616	CRES	CSK	
MS24617	STEEL	Round	
MS24618	CRES	Head	
① SPACED THREAD WITH GIMLET POINT			

Figure 17.62211-1

B. RECOMMENDED USES

1. In place of wood screws.
2. In light non-structural assemblies to reduce cost and weight.
3. In wood or plastics and in combinations of wood, plastics and metals.

C. HOLE SIZES

1. Interference hole sizes, which are sufficiently undersize to secure the screw, are listed in MS24631 (80.30.1.9). These are similar to drill sizes and should be shown in the callout as the nominal size. Fixture drilling tolerances per DM Book 81, Section 7.411 shall be added to obtain the plus tolerance. An example for a No. 8 Type A screw in 992 aluminum alloy sheet is .116 ^{.118}/_{.116}.

2. Clearance hole sizes are shown in Figure 17.6221-1.

17.62212 THREAD CUTTING SCREW

A. TYPES. Thread cutting screws have ends of Type D, F, G, or T, at the manufacturer's option. Do not specify.

① D	F	G	T
MS24627 (80.30.1)			
MS24627	STEEL	82° CSK	
MS24628	CRES		
MS24629	STEEL	PAN	
MS24630	CRES		
BAC S12BN (80.30.6.16)	STEEL	HEX SLOT OPT'N	
① MACHINE SCREW THREADS WITH FLUTED ENDS			

Figure 17.62212-1

B. RECOMMENDED USES

1. For attachment of name plates, etc., where rivets are impractical due to removal and replacement of plates. Replacement of screws requires the use of the next larger diameter screw.

2. For attachment of name plates in blind holes.

C. HOLE SIZES

1. Interference hole sizes are listed in MS24634 (80.30.1.10). These are similar to drill sizes and should be shown in the callout as the nominal size. Fixture drilling tolerances, per Book 81, Section 7.411 shall be added to obtain the plus tolerance.

An example for No. 6 Thread Cutting Screw in .063 aluminum alloy sheet is .112 ^{.112}/_{.110}.

2. Clearance hole sizes are shown in Figure 17.6221-1.

17.6222 DRIVE SCREWS

MS21318(80.50 I.I.) is a round head, carbon steel, cadmium plated screw. Insertion is by driving without wrenching.

A. RECOMMENDED USES. Drive screws may be used to attach nameplates not subject to repeated removal and replacement.

B. LIMITATIONS. Do not drive in metals too thin to resist damage. Sheet thickness equal to screw diameter is considered minimum.

C. SIZE. The recommended size for use with name plates is No. 4 which has a maximum diameter of .114.

The available lengths are as follow MS21318 19(.12), 20(.19), 21(.25), 22(.31), 23(.38).

Interference holes are .104 ¹⁰⁹/₁₀₄

For other drive screw sizes see MS21318

NAS 1081 provides self locking set screws with flat or cone point.

A. CUP POINT. The cup point is the preferred point for general use. This point is the easiest to procure from commercial sources. It may be used for permanent or semi-permanent location of machine parts where cutting of the shaft by the sharp point is not objectionable. It should not be used against hardened shafts and is seldom spotted in.

B. CONE POINT. The cone point is especially adapted for permanent location of a machine part. It may be used against hard or soft shafts and should always be spotted in. The included angles of the spot and point should be the same.

C. FLAT POINT. The flat point is to be employed where frequent resetting of the point is required with the least possible damage to the surface against which the point bears. It may be used against hardened shafts but is not suitable for spotting in.

17.6223 WOOD SCREWS

Wood screws are obsolete for new design. Use Type A Thread Forming Screws.

17.6224 SET SCREWS

Figure 17.6224-2 shows headless set screws with hex socket and with three point types. Screws with hex socket are preferred for Boeing design to standardize installation tools. The point types are illustrated and described below.

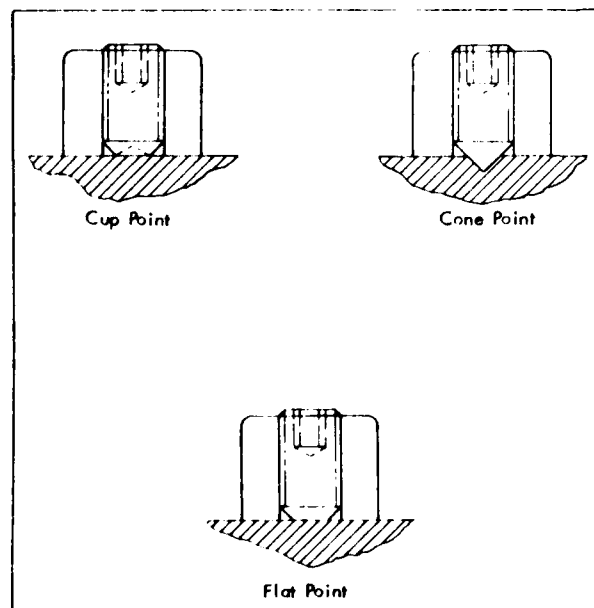


Figure 17.6224-1

17.6224 SET SCREWS



SET SCREWS — ALLOY STEEL					
ILLUSTRATION	PART & PAGE NUMBER	SIZE RANGE	MAX TEMP°F	FINISH	DESCRIPTION
	MS 10000 80.25.11.20.1	2-5/8 THRU 1/2	450	CALMIUM	FLAT POINT
	MS 10004 80.25.11.20.1	2-3/4 THRU 1/2	450	CALMIUM	CONE POINT
	MS 10005 80.25.11.20.1	2-5/8 THRU 1/2	450	CALMIUM	CUP POINT
	MS 10006 80.25.11.20.1	2-5/8 THRU 1/2	450	CALMIUM	FLAT POINT
	MS 10007 80.25.11.20.1	2-5/8 THRU 1/2	450	CALMIUM	CONE POINT
	MS 10008 80.25.11.20.1	4-40 THRU 1/2	250	CALMIUM	CUP POINT SELF-LOCKING
	MS 10009 80.25.11.20.1	4-40 THRU 1/2	250	CALMIUM	FLAT POINT, SELF-LOCKING
	MS 10010 80.25.11.20.1	4-40 THRU 1/2	250	CALMIUM	CONE POINT, SELF-LOCKING
SET SCREWS—CORROSION RESISTANT & ANTI-MAGNETIC					
	MS 10001 80.25.11.20.1	2-5/8 THRU 1/2	350	PASSIVATED	CUP POINT
	MS 10002 80.25.11.20.1	2-3/4 THRU 1/2-5/8	350	PASSIVATED	CONE POINT
	MS 10003 80.25.11.20.1	2-5/8 THRU 1/2	350	PASSIVATED	CUP POINT
	MS 10004 80.25.11.20.1	2-5/8 THRU 1/2	350	PASSIVATED	FLAT POINT
	MS 10008 80.25.11.20.1	4-40 THRU 1/2	250	PASSIVATED	CUP SELF-LOCKING
	MS 10009 80.25.11.31.1	4-40 THRU 1/2	250	PASSIVATED	FLAT POINT, SELF-LOCKING
	MS 10010 80.25.11.33.1	4-40 THRU 1/2	250	PASSIVATED	CONE POINT, SELF-LOCKING

Figure 17.6224-2

17.623 NUTS

A. CONTROL SYSTEM APPLICATION

1. CLAMP UP. Use only all metal self-locking nuts on bolts that are used:
 - a. To clamp up on the inner races of bearings and/or bushings.
 - b. Throughout the power plant control systems in all clamp up applications.

NOTE: On steel alloy bolts use steel alloy nuts such as, BACN10JC or BACN10GW; and, on CRES bolts use only CRES nuts such as, BACN10JC*C or BACN10GW*A (* dash number).

2. UNCLAMPED. Use non-self-locking nuts with a separate locking feature such as castellated nuts and cotter pins on bolts for unclamped static or rotary joints with bushings or bearings.

B. LIMITATIONS APPLICABLE TO SELF-LOCKING NUTS

1. Nuts of the No. 10 and 1/4 sizes shall be used only with bolts, screws, or studs that have not been drilled for cotter pins.
2. Corrosion-resistant steel self-locking nuts shall be used only with corrosion resistant steel bolts or screws.
3. Round or chamfered end bolts, studs, or screws must extend at least the full round or chamfer through the nut. Flat end bolts, studs, or screws must extend at least 1/32 inch through the nut.
4. Plate nuts shall be installed with rivets, screws, or projection spotwelding. If projection spotwelding is used, control shall be maintained in order that removal, by drilling out the welds, permits replacement with standard drilled plate bolts.

5. Nuts which are attached to the structure shall be attached in a positive manner to eliminate the possibility of their rotation or misalignment when tightening is to be accomplished by rotating the bolts or screws. The manner of attachment shall permit removal without injury to the structure and permit replacement of the nuts.
6. All self-locking nuts that have had the locking element reworked or reprocessed by other than a nut manufacturer shall not be used by contractors or field maintenance personnel of the services.
7. Special nuts, which depend on friction for their anchorage and torsional rigidity, such as clinch nuts, single rivet plate nuts, and similar devices, are not acceptable for use in aircraft structural applications. They may be used on aircraft equipment and component parts, such as instrument mountings and electrical equipment.
8. Self-locking nuts shall not be used in conjunction with bolts or screws on jet engine aircraft in locations where the loose nut, bolt, or screw could pull, or be drawn into the engine air intake scoop.

17.6231 NUT USE CHARTS

The following charts of nuts are divided into nine groups. These groups are determined by thread height, material, and strength.

See Figures 17.621-1 through 17.621-4 to determine nut usage for particular bolts.

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

17 6231 NUT USE CHARTS






































GROUP I 80 KSI - SHORT THREAD					GROUP II 125 KSI SHORT THREAD (CONTINUED)				
ILLUSTRATION	PART AND PAGE NUMBER	SIZE RANGE	MATERIAL	DESCRIPTION	ILLUSTRATION	PART AND PAGE NUMBER	SIZE RANGE	MATERIAL	DESCRIPTION
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	ANTICORROSION, RES 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	RES, DEEP-DRAWING 450°F, 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
GROUP II 125 KSI - SHORT THREAD						MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	RES, DEEP-DRAWING 450°F, 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	RES, DEEP-DRAWING 450°F, 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F
	MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F		MINIATURE PLAIN FACE 450°F AND 500°F	1/16-1/8	A	MINIATURE PLAIN FACE 450°F AND 500°F

Figure 17 6231-1

17.6231 NUT USE CHARTS (Continued)

GROUP III 125 KSI - LONG THREAD					GROUP I 180 KSI - LONG THREAD				
ILLUSTRATION	PART AND PAGE NUMBER	SIZE RANGE	MATERIAL	DESCRIPTION	ILLUSTRATION	PART AND PAGE NUMBER	SIZE RANGE	MATERIAL	DESCRIPTION
	BAC N114 80.100.6.20	6-32 THRU 1-20	A	CAP NUT 250°F (P. 450°F)		NAL 177 80.100.6.1	1/4 -20 THRU 1-1/2 -12	X	BARREL NUT FLOATING 450°F
	BAC N109 80.100.6.17	10-32 THRU 1-14	A X	TWO LUG FLOATING REMOVABLE NUT VARIABLE TENSILE 450°F AND 800°F		BAC N109 80.100.6.17	10-32 THRU 1-1/2 -12	X A	12 POINT EXTERNAL WRENCHING 450°F AND 800°F
		10-32 THRU 1-14	A X	ONE LUG FLOATING REMOVABLE NUT VARIABLE TENSILE 450°F AND 800°F		BAC N102 80.100.6.19	10-32 THRU 1-1/2 -12	X A	FLAMING CAP NUT SELF- SEALING, TWO LUG, FULL RESISTANT 450°F
		10-32 THRU 1-14	A X	WASHER FLOATING REMOVABLE NUT 450°F & VARIABLE TENSILE 800°F					
	BAC N101 80.100.6.15	10-32 THRU 1-14	A	NON-PLATE CAP NUT TWO LUG 450°F AND 800°F	GROUP VI MISCELLANEOUS NUTS				
	BAC N102 80.100.6.19	10-32 THRU 1-14	A X	NON-PLATE CAP NUT ONE LUG 250°F, 450°F AND 800°F		AN 514 80.100.6.1	1/4-20 -12	X A	Hex Non-Self-Locking Carbon Steel, Free and Aluminum 450°, 450° & 700°
	BAC N102 80.100.6.19	10-32 THRU 1-14	A X	FLAMING CAP NUT SELF- SEALING, FULL RESISTANT TWO LUG LOW WASHER 450°F		NAL 171 80.100.6.1	1/4-20 -12	X A	Hex Non-Self-Locking Carbon Steel & Free 450° & 700°
		10-32 THRU 1-14	A X	FLAMING CAP NUT SELF- SEALING, FULL RESISTANT TWO LUG LOW WASHER 450°F		AN 756 80.100.6.1	6-32 THRU 10-24		PLATE, SELF-LOCKING PT. ANGLE, ALUM. OR STEEL NUT ALUM. BRACKET 750°F
		10-32 THRU 1-14	A X	NON-PLATE CAP NUT TWO LUG 450°F AND 800°F					
	BAC N102 80.100.6.19	10-32 THRU 1-14	A X	WASHER FLOATING REMOVABLE NUT 450°F & VARIABLE TENSILE 800°F	GROUP VII 220 KSI - LONG THREAD				
	BAC N101 80.100.6.15	10-32 THRU 1-14	A	BARREL NUT NON-PLATE PART CAN BE TOOK FOR EITHER 450°F OR 800°F		BAC N109 80.100.6.17	10-32 THRU 1-1/2 -12	X A	12 POINT EXTERNAL WRENCHING, FATIGUE RATED 450°F & 800°F
					GROUP VIII 260 KSI - LONG THREAD				
						BAC N109 80.100.6.17	10-32 THRU 1-1/2 -12	A	12 POINT EXTERNAL WRENCHING, FATIGUE RATED 450°F
GROUP IX 160 KSI - LONG THREAD					GROUP IX BEARING RETAINER NUTS				
	BAC N101 80.100.6.15	10-32 THRU 1-14	A	NON-PLATE CAP NUT TWO LUG 450°F AND 800°F AND 12 CAN BE TAKEN FOR 450°F & 800°F		MS 19068 80.100.6.1	3/16 THRU 1-847	X	SPANNER WRENCHING NON-SELF LOCKING
	BAC N101 80.100.6.15	10-32 THRU 1-14	A X	CASTELLATED, HEX 450°F 800°F		BAC N109 80.100.6.17	1-1/2 THRU 10-565	X	SPANNER WRENCHING SELF-LOCKING
	BAC N109 80.100.6.17	10-32 THRU 1-1/2	A X	12 POINT EXTERNAL WRENCHING 450°F & 800°F		NAS 509 80.100.6.1	1/4-20 THRU 2 1/4-12	X	DRILLED JAM NUT FOR ROD ENDS
	BAC N101 80.100.6.15	8-32 THRU 1-20	A	THREADED INSERT LIGHT WEIGHT 450°					
	BAC N101 80.100.6.15	8-32 THRU 1-12	A	THREADED INSERT HEAVY DUTY 450°					

Figure 17.6231-2

17.624 PLATE NUTS AND GANG-CHANNEL NUTS

Plate nuts and gang channel nuts of aluminum alloy of any type shall not be used in primary structure for tension applications.

Steel plate nuts and gang-channel nuts may be used for tension applications.

The restrictions of 17.623 also apply to self-locking plate nuts and gang-channel nuts.

The specifications for nut plates with NAS numbers are referenced only on the BAC Standards pages with which they are grouped.

17.6241 GANG-CHANNEL NUTS - DRAWING CALLOUT

Gang channel nuts shall be called out by BAC Commercial part number as specified on the applicable pages of the BAC Standard Book, D-590, unless the stock strip must be cut other than midway between two adjacent nuts. The gang nut strip must be detailed to show the end dimensions of special cuts, and it shall be called out in the drawing parts list as follows:

- An individual dash number of the drawing shall be assigned to each gang nut channel and placed in the PART NUMBER column.
- The BAC number minus the code for the number of nuts shall be placed with the name in the NOMENCLATURE column.
- The commercial part number noted on the BAC page shall be shown in the STOCK SIZE column, together with the number of nuts in the strip.
- The name and address of the vendor as shown in the illustrated callout on the BAC page shall be placed in the MATERIAL column.


NUT GANG CHANNEL INAS 68726	G1000-3-6 12 NUTS	1
NOMENCLATURE	STOCK SIZE (APPROX. NET)	MATERIAL

1 KAYNAR MANUFACTURING CO. INC, 820 EAST 18TH STREET, LOS ANGELES 21, CALIF (OR EQUIVALENT).

A separate detail drawing shall be made for each specially cut gang nut channel which is used on more than one drawing.

17.6242 PLATE NUT HOLE CLEARANCE - DRAWING CALLOUT

The screw hole size to be punched or drilled in material where a plate nut is to be attached shall be Class III per Figure 17.252.1 and shall be specified at the part indicator for the plate nut, as shown below.



To avoid excessive repetition on drawings which call out a great many plate nuts, the clearance hole size may be omitted from the plate nut part indicators, and the hole size information added to the general drawing notes as follows:

CLEARANCE HOLE SIZES FOR PLATE NUTS SHALL CORRESPOND TO THE SIZE OF THE PLATE NUT AS SHOWN:

No. 10-32	.218-.229 DIA HOLE .218
Size Plate Nut	Clearance Hole Size





17.625 SHEET SPRING NUTS

Sheet Spring Nuts are light in weight and economical. Their use is controlled by MS 33538.

17.634 QUICK RELEASE FASTENERS

QUICK RELEASE FASTENERS

QUARTER TURN

ILLUSTRATION	STUD ASS'Y	STUD MAT'L & FINISH	HEAD STYLE						STRENGTH RATING	GRIP RANGE	TEMP RANGE	MATING COMPONENTS								
			FLUSH	PROTRUDING	SEAL	WIND	SEAL	WASHER				SNAP RING	SEAL RING	GROMMET	RETAINER	SPRINGER	RECEPTACLE			
 FIG 1	BACF31A 90.21, 6.97	Alloy Steel Zinc Plate							700	700	450°		F12X 90.22, 6.7		F12X 90.22, 6.5			F11A 90.20, 6.4		
 FIG 2	BACF31A 90.21, 6.97	Alloy Steel Zinc Plate							700	700	450°		F12X 90.22, 6.7		F12X 90.22, 6.5			F11A 90.20, 6.4		
 FIG 3	BACF31A 90.21, 6.97	Alloy Steel Zinc Plate							700	700	450°		F12X 90.22, 6.7		F12X 90.22, 6.5			F11A 90.20, 6.4		
 FIG 4	BACF31A 90.21, 6.97	Alloy Steel Zinc Plate							700	700	450°		F12X 90.22, 6.7		F12X 90.22, 6.5			F11A 90.20, 6.4		

* Strength is dependent on type of BACF11A receptacle.
 * Strength is dependent on type of BACF11AB receptacle.

MULTIPLE LEAD



ILLUSTRATION	STUD ASS'Y	STUD MAT'L & FINISH	HEAD STYLE		NOM. DIA.	GRIP RANGE	MAX. TEMP.	STRENGTH RATING			MATING COMPONENTS	
			FLUSH	HEX SOCKET				TENSILE	DOUBLE SHEAR		RECEPTACLE	RETAINER RING
 FIG 5	BACF34B-8	Alloy Steel Zinc Plate	Flush		.125	.125 to 1.967	450°	1000	5400		BACF34B-P4 90.20, 6.32	BACF34B-R 90.20, 6.32
	BACF34C-8	Alloy Steel Zinc Plate	Flush		.1375	.188 to .999	450°	1800	15000		BACF34C-P8 90.20, 6.34	BACF34C-R8 90.20, 6.34
 FIG 6	BACF34D-8	Alloy Steel Zinc Plate	Flush, Protruding		.125	.072 to 1.133	450°	2000	4500		BACF34D-P8 90.20, 6.29	BACF34D-R 90.20, 6.29
					.1125	.173 to 1.177		3500	9500			
					.175	.148 to 1.147		6000	13000			

Figure 17.634.1

17.632 SHEAR PINS

Shear pins may be used as fasteners to relieve overstress, or to provide for intentional separation of mechanically mated parts. The shear pins are designed to shear when the shearing force reaches a predetermined value.

When the design requires these types of shear pins, the following criteria must be considered:

A. The shearing edges must be well defined and sharp. Clearances must be kept to a minimum so that failure of the shear pin is not appreciably influenced by bending stresses. Shear pins should be installed with a transition fit. The interface clearance between shearing edges should be in the order of that attained when using DM 17-252 Class 1 holes (based on pin size), with a maximum interface clearance of 10 per cent of the shear pin diameter.

B. The minimum strength for shear pin materials, except for standard fastener application, is taken from the allowable strengths specified in the applicable material shear strength charts. Test results of the parts must be used in final design.

1. The predictability or variability of minimum and maximum shear strengths are strongly influenced by the shearing edge condition and clearance.
2. Shearing edge material must be hard enough to insure that the edge will not break or deform during the shearing action.

C. Strength allowances that appear in Section 18 should not be used for undriven rivets used as shear pins, since these allowances depend on the corrosion strength from work hardening during rivet installation.

D. If more than one pin is used all the directions of force applications must be covered. For example, if two parts fastened by shear pins are required to separate with application of an oscillatory lateral force, loading moments that may be inadvertently applied must also be taken into account. Where warranted, a test program should be conducted to determine the dynamic shearing force on a specific part.

E. Shear pin applications should be designed so the pins can be readily inspected for stress and integrity. Include inspecting areas, where possible, for shearing stresses on partially sheared pins and for shearing of parts on the pins. Do not use partially sheared pins. The use of nonmetallic pins is recommended for cost inspection. Avoid, where possible, use of shear pins in critical applications where periodic inspection of the pins and fastening area is not possible.

F. For critical applications, a Specification Control Drawing or a Flaming Standard may be prepared for control in minimum strength, maximum shear strength, etc. If such a drawing is prepared, the requirements must include at least the following: Material, all dimensions, strength requirements and testing method. D2-2866, Procedures of Mechanical Testing of Aircraft Structural Fasteners is recommended for fasteners. Shear pin drawings should carry a note to the effect that material substitutions per BAC 5005 are not allowed without prior approval of Engineering.

G. Always use the largest margin possible for shear out over the maximum operating stress.

NOTE: Consult the applicable divisional staff for: Stress allowances, material recommendations for shear pins, shearing edges, inserts (when used) and dimensional limitations.

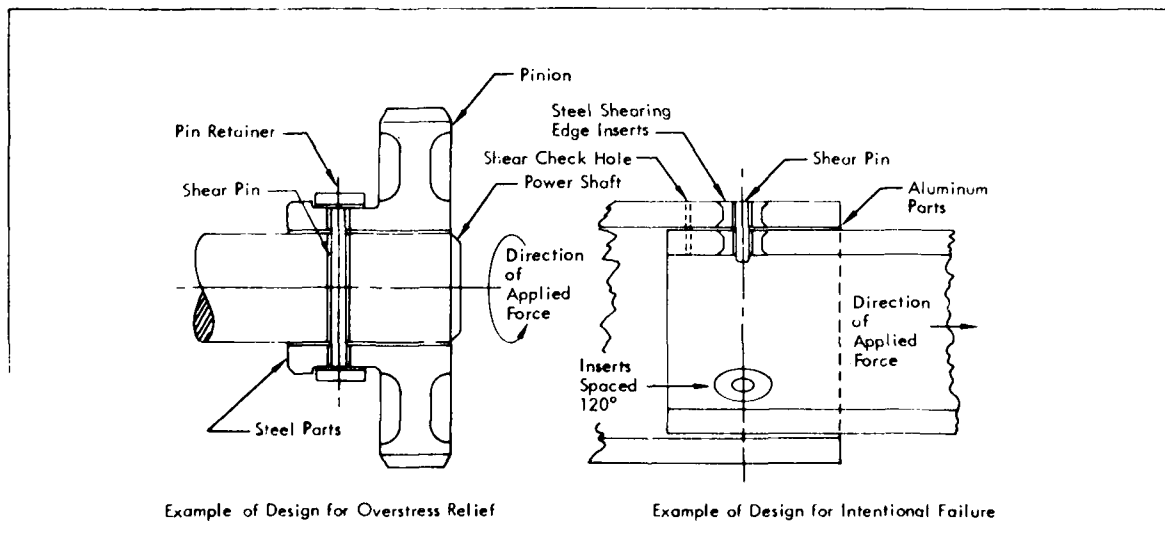


Figure 17.632-1

17.6332 (Continued)

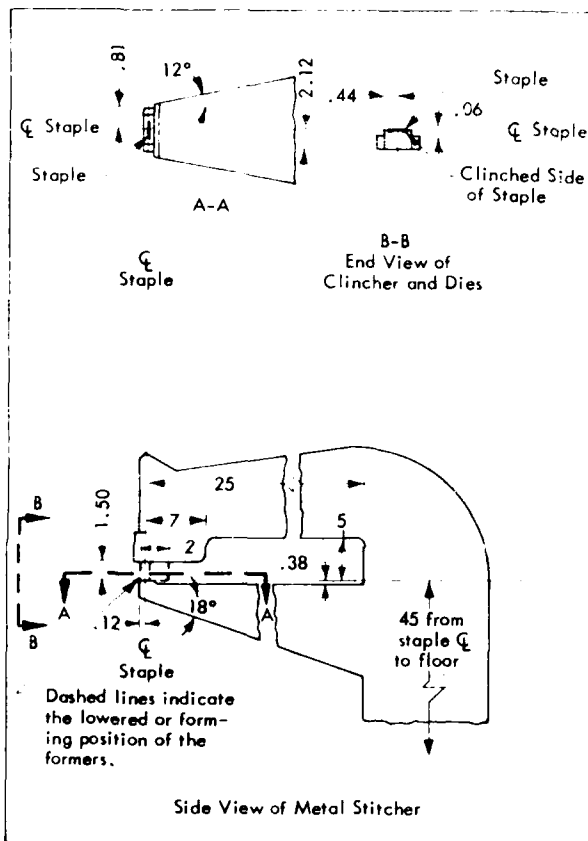


Figure 17.6332-2

17.6333 DRAWING CALLOUT

A drawing symbol shall be used to indicate metal stitches whenever they appear on drawings from either the driven or clinched side. The symbol may be made freehand using the approximate dimensions shown below. On a long row of stitches only two or three symbols on each end need be shown.



Typical Metal Stitch Drawing Symbol

The process specification shall be called for on the drawing by a general note with symbol, such as:



Spacing for metal stitches may be indicated by adding to the general note above, the required information, such as:

SPACE APPROXIMATELY ____ INCHES or ____ EQUAL SPACES.

Otherwise, the spacing shall be dimensioned on the drawing.

Flush stitches in soft material shall be indicated by a note on the drawing. When it is desired to restrict clinching to a particular side, a note shall specify:

CLINCH FAR SIDE or CLINCH NEAR SIDE

Unless this is so noted on the drawing, the shop will usually clinch against the harder or heavier material.

The edge margin and starting point of each row of stitches must be dimensioned on each drawing as shown in Figure 17.6333-1. When it is required to place the stitch at an angle to the centerline of the row in order to prevent cracking of the material being stitched, the symbol shall be shown at an angle and dimensioned as shown.

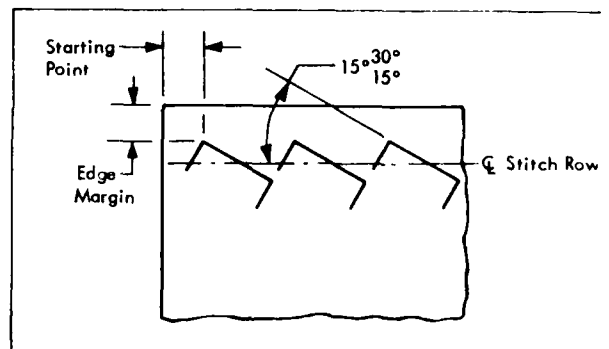


Figure 17.6333-1

17.633 METAL STITCHING

A. When stitching is necessary for assembly or repair, the appropriate material for the stitching is fiber, felt, fabric base impregnated plastic, or cotton webbing, etc., for aluminum alloy, mild steel, pressure-treated steel, brass, or copper sheet metal; considered for use is the given to metal stitching. In addition, more than gages of metal parts such as ammunition boxes, decks, and others may be assembled by stitching with a possible saving in production time and cost.

B. Comparatively brittle materials, such as methyl methacrylate, for the paper base impregnated phenolic and magnesium alloy sheet, etc., are not to be stitched. Some relatively brittle materials, such as hard rock phenolic, white fiber asbestos, and certain types of plastic, may be successfully stitched by using a metal backing strip, Figure 17.6331.2, under the rows of the stitches. For these materials, the use of the drawing pins and wire, optional use of a backing strip.

C. Splicing of the drawn flush in sheet metal, but their use in ducts, boxes, etc., is permitted at the discretion of the Proper Engineer. Splices can be drawn flush in soft materials.

D. When stitching parallel to the grain would tend to cause crack along a wood or other material with a definite grain, the stitch shall be placed at an angle of from 15° to 30° to the centerline of the sheet row. The exact angle within this range is at the option of the shop.

E. When stitches use .051 diameter zinc coated steel wire per specification MIL-W-6214 with a minimum tensile strength of 290,000 psi. The length of stitches approximately 5 inch and is formed from a minimum length of wire for work thicknesses up to 12 inch plus twice the extra thickness for work over 12 inch.

17.6331 EDGE MARGIN AND SPACING

Stitches are to be located 12 inch from a flange on the side of the work except where the stitch is directed and from 12 to 31 inch from a flange on the lower side of the work. The greater clearance is to be used for the repair work. The recommended minimum edge margin is shown in Figure 17.6331.1.

The recommended spacing is as follows:

A. The recommended spacing for a single row of stitches in ducts, boxes, etc., is at pressure where linear loadings are not critical. The spacing is to be considered the maximum design spacing for the shop. The shop may increase row spacing of stitches to 20 inches.

B. The spacing for metal to metal joints taking light loads.

C. The spacing for rubber, fiber, felt, or nonstressed metals.

D. The spacing for asbestos, canvas, etc.

The above stitching spacing are in no way engineering standards, and are not to be used for other purposes. Stitch patterns and recommended row spacing for pressure tight seams have not been determined.

The above given maximum stitch spacing in rows is 20 inches with 12 inches considered the shop minimum. The minimum row spacing for metal stitches is 19 inches. See Figure 17.6331.1 for application of these minimums. The drawing nominal dimensions for margin and spacing with the tolerances applied, should not be less than the minimums given.

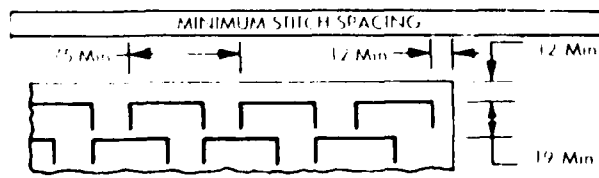


Figure 17.6331.1

End loops in cotton webbing strips 1 inch wide or less for attaching to cleats, rings, buckles, etc., may be made with metal stitching. A minimum of two stitches shall be used and spaced as shown in Figure 17.6331.2.

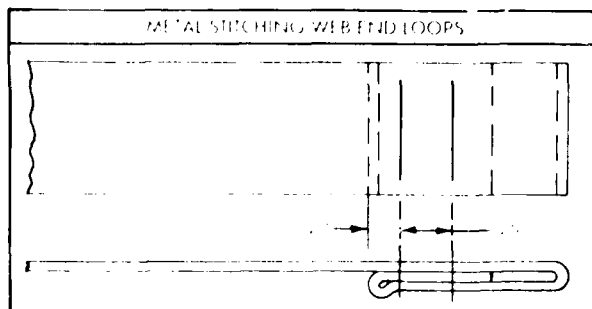


Figure 17.6331.2

17.6332 CAPACITIES AND DIMENSIONS

The maximum recommended material thickness values for satisfactory production stitching on present equipment are given in Figure 17.6332.1. The principal dimensions of present Boring equipment are shown in Figure 17.6332.2.

STAPLING MACHINE CAPACITY FOR VARIOUS MATERIALS ②			
Material	Number of Sheets and Remarks ①	Max. Total Thick. (in.)	Max. Single Sheet Thick. (in.)
Clad 2024-0, 3003	4 sheets of .040	.160	.102
Clad 2024-T3	2 sheets of .040	.080	.064
Type 302 Annealed Corros. Resist. Steel	2 sheets of .020	.040	.032
Type 302 1/2 Hard Corros. Resist. Steel	2 sheets of .016	.032	.020
18-8 Full Hard Stainless Steel	1 sheet of .020	.020	.020
Wood and Plywood, Rubber, Rubber-banded Canvas, Canvas Card-board and Asbestos	.75 possible on fine grained wood.	.75	--
Plastic, Hard Plywood (Compressed and Impregnated.)	Type of plastic and amount of compression are governing factors.	.38	--
Molded Phenolic, Hard Rubber, Porcelains	Too brittle; cracking tendency does not permit stitching	--	--

















① Any combination of gages of any one metal, the sum of which does not exceed the maximum total thickness listed above, can be stitched, providing that no individual sheet of the combination exceeds the maximum single sheet gage listed for that material.

② Specific recommendations cannot be made for applications which use combinations of metal and soft non-metallic materials. In such cases, trial tests should be made, consult the applicable staff.

Figure 17.6332.1

17.63 SPECIAL FASTENERS

17.631 PINS USAGE CHART

PIN TYPE	PART NUMBER	MATERIAL	REMARKS
Flat Head Pin 	MS16552	STEEL	 Recommended Use: In shear applications where little or no tension load exists, such as fork and eye connections. Use in place of bolt and nut will save weight.
Dowel 	NAS 607	STEEL CASE HARDENED	 Recommended Use: As an alignment index in symmetrical assemblies to avoid improper installation. Dowel pin and mating guide hole must have diameter larger than any bolt holes to insure pin can only fit in correct hole.
Two Hole 	BAC P18C	2024-T STEEL	 Recommended Use: In place of flat head pin when direction of removal is unknown at time of installation.
Quick Release 	BAC P18A1 BAC P18A2 NAS 1333 1346	4130 STEEL	 Recommended Use: Primarily in shear applications where quick disassembly is necessary. Handle types available: Ring (illustrated), "L", "T", or button. Available in drive out or non-drive out types.
Spring Pins 	MS16552	STEEL AND CRES	 Recommended Use: In shear applications when installed in drive fit holes. Design limits and hole sizes: Per MS33547.
Seal Retainer Pins 	BAC P18G	CRES	 Recommended Use: To attach seal cloth to BAC-1520-484 or BAC-1520-470 seal extrusion.
Safety Pin 	MS29523	CRES	 Recommended Use: To attach safety chain to structure.
Cotter Pin 	MS24665	STEEL CRES	 Cotter Pin Recommended Usage: As a safety retaining device. Cadmium plated steel pins may be used with cadmium plated fasteners in temperatures up to 450°F. CRES pins should be used in corrosive areas or in non-magnetic applications up to 800°F.

NOM BOLT SIZE		#10	1/4	5/16	3/8	7/16	1/2	9/16	5/8	3/4	7/8	1	1 1/8	1 1/4	
STEEL	MS24665 - DASH NOS	134			287			357		359		360		362	
CRES		153			304			374		376		377		379	
NICU		191			338			408		410		411		413	
NOM COTTER PIN SIZE		1/16 x 3/4			3/32 x 1 1/4			1/8 x 1 1/2		1/8 x 1 3/4		1/8 x 2		1/8 x 2 1/2	

Figure 17.631-1

17.64 WASHERS, SPACERS AND SHIMS

17.641 WASHERS

Washers shall be selected from the following standards in the order of preference shown for the application needed.

To protect the surface of the structure during installation of a fastener by tightening, one standard washer may be used under either the bolt head or the nut (whichever is being turned).

A maximum of two additional washers may be used to allow for grip adjustment of the bolt.

For prevention of dissimilar metal corrosion between washer and structure see the finish document listed in DTA Book 81, Section 14.

TYPE	STD PART DWG NO.	MATERIAL	RECOMMENDED USAGE
Plain	MS20002	Heat-Treated Alloy Steel	Per ①, ②, and ③
	BACW10BN		
	AN960	Al Alloy (Clad 2024-T3 or T4). Carbon steel, CRES and brass.	General usage ①, ②, ③, ④, ⑤, and ⑥
	BACW10AT	Steel and Alum Alloy	Large I.D. for use with tapered shank fasteners per ①, ②, ③, and ④.
	AN970	Steel	Large OD for use on wood.
	MS27183	Steel	Thicker and larger than AN960 per ①, ②, and ④.
	BACW10P		General usage for washers not found in other standards.
	NAS1197	5052 Al Alloy	Per ④ with magnesium.
Countersunk	MS20002	Heat-Treated Alloy Steel	To obtain a clearance with the large head-to-shank radii on high strength fasteners, in designs where stress will not approve the required countersinking in the material under the fastener head. Also ② and ④.
	BACW10BN		
Lock-Split	MS35337	Steel CRES and Bronze	Where not restricted per AND10476.
	MS35338		
Lock-Tooth	MS35336		
	MS35790	Carbon Steel and Bronze	See Standard Page 70.7.1.0
Counter Bore	AN975	Steel	With AN386 Taper pins.
Self Aligning	BACW10BT	Steel	Concave and convex washers are used together.
Vibration Stop	AN8013	Steel and Al Alloy	With BAC-S14C vibration insulators (shock mounts per AND10405 and AND10407).
Bearing Retainer	MS19070	Steel	With MS19068 lock nuts to retain bearings.
	BACW10Q	Steel	With ball bearing, self-aligning rod ends to prevent bolt head from slipping through end in case of loss of balls.
Dimpled 100°	BACW10U	Steel and Al Alloy	Per ④ with 100° csk fasteners.
	BACW10Z	5052 Al	
Pre-Load Indicating	BACW10AM	Heat-Treated Alloy Steel	For 220 KSI Bolts
	BACW10AP		For 160 KSI Bolts
	BACW10AQ		For 125 KSI Bolts















Used for accurate control of preload in bolt to obtain maximum fatigue life.

- ① Used under nut to compensate for difference in bolt grip length and material thickness per 19.512.
In the interest of weight saving, two washers are recommended as a maximum for any one application. However, the use of more washers is preferred to the use of a bolt of special length or washer of special thickness.
- ② To distribute bearing load over a greater area to prevent compression of material under bolt head, screw head or nut.
- ③ To prevent galling of aluminum or aluminum alloy sheets less than .061 thick and other soft materials when bolts, screws, or nuts are tightened, or by lock washers (per AND10476).

- ④ To insulate dissimilar metals against corrosion. Wherever possible, the washer material should be similar to the material upon which it rests rather than to the bolt or nut material so that corrosion, if it exists, is created between the replaceable bolt and washer instead of washer and fitting or sheet. Use 5052 aluminum alloy washers with magnesium alloy per DM, Book 81, Sect. 14 0323.
- ⑤ Where material next to nut is steel, use MS20002 steel washers. Use 2024-T3 or 2024-T4 washers (AN960 for sizes 1" and smaller; BACW10P for larger) if material next to nut is aluminum alloy.
- ⑥ Used next to plastic laminates to prevent crazing caused by driving solid rivets and swaged collars, see DM, Book 81 Sect. 24.311.

Figure 17.641-1

17. 642 SHIMS, PLATE NUTS

TYPE	PART NO.	MATERIAL	NUT SIZE	THICKNESS	REMARKS
Plain Plate Nut Shim  Type W  Type T  Type F	NAS463	1010 Steel or better	No. 6, 8 & 10	.016, .032, .063 & .090	For general use with plate nuts.
	NAS463C	Cres (301, 302, 321, or 347)	1/4, 5/16 & 3/8		
	NAS463D	5052-H36			
	NAS463DD	2014, 2024, 7075, or 5052			
	BAC-S18L (Type W only)	2024-T4	7/16	.072 & .156	
	BAC-S18M	Magnesium	No. 6, 8 & 10 1/4, 5/16 & 3/8	.125	
	BAC-S18U	2024-T4	1/4, 5/16 & 3/8	.125, .188, .250 & .312	
Floating Plate Nut Shim  Type X  Type Y  Type B  Type C	NAS463	1010 Steel or better	No. 6, 8 & 10	.016, .032, .063 & .090	For general use with plate nuts.
	NAS463C	Cres (301, 302, 321, or 347)	1/4, 5/16 & 3/8		
	NAS463D	5052-36H			
	NAS463DD	2014, 2024, 7075			
	BAC-S18M	Magnesium	No. 6, 8 & 10 1/4, 5/16 & 3/8	.125	
Countersunk Plate Nut Shim  Type W  Type T  Type F	NAS500-NAS500C	1010 Steel or better	No. 8, 10 & 1 1/4	.080, .090 & .125	For use with 100° dimpled sheet. Use of csk plate nuts preferred to use of shims.
	NAS500D	Cres (301, 302, 321 or 347)			
	NAS500DD	5052-36H			
		2014, 2024, 7075, 5052			
Miniature Plate Nut Shim  Type A  Type B  Type C  Type D	NAS 1195	2014, 2024, 5052, or 7075	No. 2 thru .375	.032 and .063 See Standards Page	For use with miniature plate nuts.

Recommended Use: With plate nuts, to increase material thickness to accommodate grip of bolt. When attaching plates, panels, etc., which would be removed for maintenance in metals of varying thicknesses it is preferable to use shims so bolts may all be of same grip length to avoid installation errors. Use washers per 17.641 with hex nuts. Drawing Callout: Per PM, D 4900

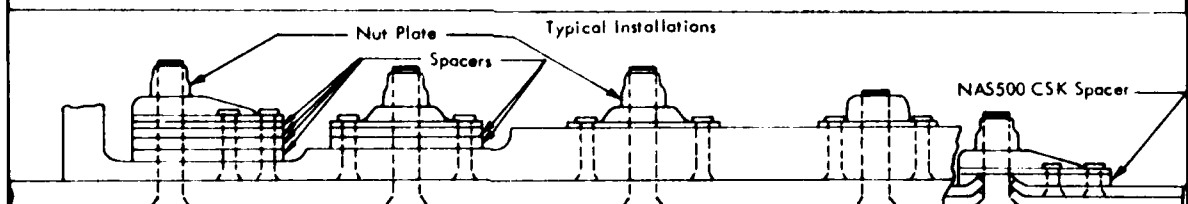


Figure 17.642-1

17.643 SPACER, SANDWICH BOARD

-111-









STYLE	PART NO.	MATERIAL	FASTENER NOM DIA	REMARKS ①	TYPICAL INSTALLATION ②
 Sleeve	BAC-S18AB	2024-T4 Sleeve	No. 10 1/4 5/16	For use in primary aluminum structural sandwich with skins thicker than .040	 See Standards Page for applicable fasteners.
 Type A Plug for Countersunk Fasteners	BAC-S18AB	7075-T6 Plugs			
 Type B Plug for Protruding Head Fasteners		CRES See Standards Page	No. 10 1/4 5/16	For use in primary steel structural sandwich with skins greater than .040	
	BAC-S18AC	2024-T4	No. 8 No. 10 1/4	For use in secondary aluminum structural panels with skins thinner than .040 or secondary structural load attachments in primary panels with skins thinner than .040 Dimple formed with hot dimpling dies.	 May be used with any 100° CSK fasteners which will fit the specified inside diameter except pull type lockbolts. See Standards page.
		416 CRES	No. 8 No. 10 1/4	As above in steel or titanium panels	
	BAC-S18AD	2024-T4	No. 8 No. 10 1/4	Especially designed for flooring attachment; skin thicknesses less than .040. May be used in any secondary loading & spacer application. Dimple formed with hot dimpling dies.	 May be used with any 100° CSK fasteners which will fit the specified inside diameter except pull type lockbolts. See Standards page.
		CRES See Standards Page		As above in steel or titanium panels.	
① Strength of these joints is dependent upon the sandwich construction. Consult the applicable structural staff unit for information.					
② The note, INSTALL PER BAC 5085, shall be added to applicable drawings.					

Figure 17.643-1








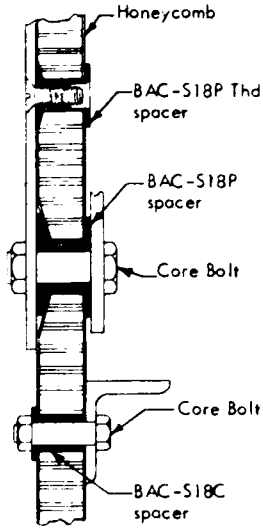

STYLE	PART NO.	MATERIAL	FASTENER NOM DIA	REMARKS	TYPICAL INSTALLATION
Sandwich Board Spacers  Sleeve Type A  Plugs Type A  Sleeve Type B  Type B  Thd Sleeve Type A  Type C  Thd Sleeve Type B	BAC-S18P	2024-T3 2024-T4 & 6061-T6	No. 8, 10 and 1/4	For use in sandwich board, balsa wood, etc. to pre- vent crushing of material. Type A, B, or C, plug may be used with either Type A or B sleeve. For installation data see Standards page.	
		2024-T4	10-32	For use as a self-locking tapped hole in sandwich board, etc. Type A, B, or C plug may be used with either Type A or B sleeve. See Standard page for installation data.	
Flanged Spacer 	BAC-S18C	2017-T4 or 2024-T4	1/8 & 5/32 Rivet No. 6, 8, 10 & 1/4	Stronger in shear than S18P. See BAC-S18D for installation data.	

Figure 17.643-2

17.644 RIVET, SPACER HEAD, BLIND




STYLE	PART NO.	MATERIAL	FASTENER NOM DIA	REMARKS	TYPICAL INSTALLATION
Spacer Head, Blind Rivet  Pull-Thru Stem  Break-Off Stem	BAC-R15Z BAC-R15BY BAC-R15CC	5056-F	1/8, 5/32 & 3/16	Head used to space sheets. Installed with Cherry or Olympic rivet gun. Break-off type (preferred with blind rivets) limited to applications where the broken stem can be retrieved on blind side. See Std pg for installation.	

Figure 17.644-1

17.645 SPACER, RIVET AND BOLT


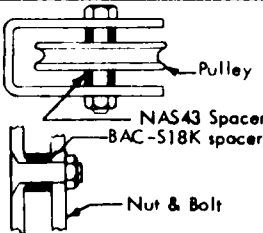


STYLE	PART NO.	MATERIAL	FASTENER NOM DIA	REMARKS	TYPICAL INSTALLATION
 Spacer	NAS42	2024-T & 4130 or 8630 Steel	3/32 thru 3/8 rivet	Gen Usage: Spacing sheets, wire bundle clamps, pulley guards, etc. with rivets.	
	NAS 43	2024-T & 4130 or 8630 Steel	No. 4 thru 1.00	Same usage as NAS42 with bolts & screws except not for pulley guards.	
 CSK Spacer	BAC-S18K	2024-T or 6061-T	No. 8, 10 and 1/4	For use with top sheet dimpled.	

Figure 17.645-1

17.646 SPACER, PLATE NUTS



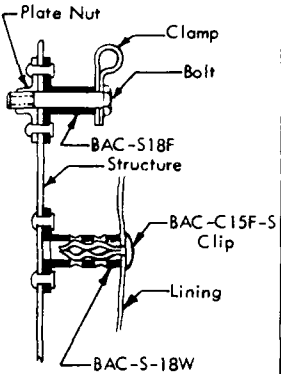


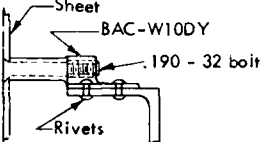



STYLE	PART NO.	MATERIAL	FASTENER NOM DIA	REMARKS	TYPICAL INSTALLATION
Plate Nut Spacers  Two Lug Type  One Lug Type	BAC-S18F	Plate 2024-T	No. 10	For general stand-off spacer usage with nut plates. Two lug type preferred where space permits.	
	BAC-S18G	Tube 6061-T	1/4 & 5/16		
	BAC-S18R	Plate 2024-T	No. 10		
	BAC-S18S	Tube 6061-T	1/4		
Lining Spacer 	BAC-S18W	Plate 2024-T Tube 6061-T		To attach lining with BAC-C15F-S clips.	

Figure 17.646-1

17.647 NUT, SPACER PLATE

SPACER PLATE NUTS	STD NO.	MATERIAL	THREAD	TYPICAL USAGE
Heavy Duty 	BAC-N10DW	Cast 356-T6 Forged 2014-T6	.10-32	For stand-off attachment of equipment etc. parallel to mounting surface 
Light Weight 	BAC-N10DY	2014-T6	.10-32	
Two Lug Light Weight 	BAC-N10DZ	2014-T6	.10-32	
	BAC-N10DX	2014-T6	.10-32	

Drawing Callout Per PM 94B1 Section 10

Figure 17.647-1

17.648 RADIUS FILLERS

Radius fillers are allowed a maximum gap of .040 per BAC 5300. When less maximum gap is required to obtain increased tension loads or reduce deflection, the allowable maximum gap should be noted on the drawings as follows:

MAXIMUM GAP BETWEEN RADIUS FILLER AND THE RADIUS OF FORMED PART (OR EXTRUSION) SHALL BE .XXX.

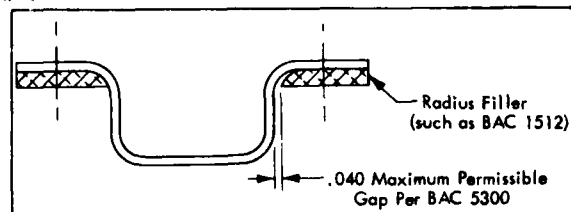


Figure 17.648-1

APPENDIX I - BOEING DESIGN MANUAL

SECTION 26 ADHESIVE BONDING

- 26.01 General
- 26.02 References
 - 26.021 Structural Adhesives
 - 26.022 Non-structural Adhesives
- 26.1 Advantages of Adhesive Bonding
- 26.2 Types of Adhesive Bonding
 - 26.21 Structural Bonding
 - 26.22 Non-structural Bonding
- 26.3 Forms of Adhesives
- 26.4 Design of Adhesive Bonded Joints
- 26.5 Design of Adhesive Bonded Parts
- 26.6 Structural Bonding - Design Information
 - 26.61 Design of Adhesive Bonded Structures
 - 26.611 Metals Suitable for Structural Adhesive Bonding
 - 26.612 Selection of an Adhesive Bonding System
 - 26.6121 Selection of Adhesives
 - 26.613 Cured Bond Line Thicknesses
 - 26.614 Drawing Callout
 - 26.62 Adhesive Bonded Honeycomb Sandwich Panels
- 26.7 Non-structural Adhesive Bonding - Design Information
 - 26.71 Selection of an Adhesive System
 - 26.711 Selection of Adhesives
 - 26.712 Surface Requirements for Non-structural Bonding
 - 26.713 Cost Information
 - 26.714 Drawing Callout

SECTION 26 ADHESIVE BONDING

26.01 GENERAL

This section contains information to aid in the selection of adhesives for structural and non-structural applications. It also presents guidance concerning typical joint configurations and data on strength and comparative cost.

26.02 REFERENCES

Documentation and specifications for structural bonding are quite different from non-structural bonding because of the rigid controls required for structural bonding, and consequently are listed separately.

26.021 STRUCTURAL ADHESIVES

A. BMS - BEING MATERIAL SPECIFICATIONS

1. Sheet Stock

BMS 5-69 Laminated Aluminum Sheets - Structurally Bonded

2. Adhesive Systems

BMS 5-42 Structural Adhesives for Metal-to-Metal Assemblies AF 9330 System.

BMS 5-51 Moderate Temperature Curing Structural Adhesive System.

BMS 5-70 Structural Adhesives for Metal to Metal Sandwich Assemblies FM61 System.

BMS 5-80 Moderate Temperature Curing Structural Adhesive System.

BMS 5-89 Corrosion Inhibiting Adhesive Primer

BMS 5-90 Structural Foaming Adhesives

BMS 8-30 Structural Foam-in-Place Adhesive

B. BAC - PROCESS SPECIFICATIONS

BAC 5452 Structural Foam Bonding

BAC 5514-542 Structurally Bonding Metal-to-Metal.

BAC 5514 Common Bonding Requirements for Structural Adhesives Systems.

BAC 5514-551 Structural Bonding with Moderate Temperature Curing Adhesives (BMS 5-51).

BAC 5514-570 Structural Bonding with BMS 5-70.

BAC 5514-580 Structural Bonding with Moderate Temperature Curing Adhesives (BMS 5-80).

BAC 5514-589 Application of Corrosion Inhibiting Adhesive Primer

BAC 5514-590 Structural Bonding with Foaming Adhesives

26.022 NON-STRUCTURAL ADHESIVES

The following specifications should be called out when applicable as indicated by Figures 26.711-1, 26.711-2 and Paragraph 26.714.

A. BAC SPECIFICATIONS

BAC 5010 Application of Adhesives

BAC 5038 Processing of Acrylic Plastics

BAC 5407 Structural Bonding of Metal to Wood or Plastics

BAC 5444 Bonding Shims and Fillers

BAC 5447 Processing of Thermoplastic Sheet Materials

BAC 5472 Bonding of Cork Composition Ablative Insulation Material.

26.1 ADVANTAGES OF ADHESIVE BONDING

A. An adhesive distributes stresses more uniformly throughout the bonded area than mechanical fasteners.

B. A bonded exterior joint in an airplane or aerospace vehicle presents a smooth aerodynamic surface to the elements, thus eliminating the drag caused by non-flush mechanical fasteners.

C. The use of an adhesive bond can reduce the weight of the system.

D. With the proper selection of the adhesive, the continuity of an adhesive-bonded joint reduces the probability of leakage, and therefore, can eliminate the need for extra gaskets or sealants. This is an important advantage over rivets where buckling of thin metal sheets takes place between rivets, making gasketing or sealing mandatory.

E. Adhesive bonding may be faster and less expensive than other fabrication techniques such as welding, brazing or mechanical fastening with rivets.

F. Galvanic action will not normally result from the bonding of dissimilar metals. The adhesive used is generally a good dielectric and thus can bond and insulate simultaneously.

G. With proper care to prevent warpage, the use of elastomeric adhesives permits the bonding of dissimilar materials with widely differing coefficients of expansion. This is primarily applicable to nonstructural bonding.

H. Bonded sandwich construction presently offers the optimum strength-weight ratio for certain structural applications. See Section 216 for design information.

I. As a result of the more uniform load distribution, structural adhesive bonding increases component fatigue life.

J. The visco-elastic characteristic of adhesives in laminated sheets improves resistance to sonic fatigue.

26.2 TYPES OF ADHESIVE BONDING

26.21 STRUCTURAL BONDING

Structural bonding is used in primary and secondary structural components of aircraft. It is required. Structural bonding requires processes that can be used in and out of the factory during processing, fabrication, coating, and assembly, and bonding techniques required in structural bonding because of the joint carrying capacity in the assembly must meet.

Design information on structural adhesive bonding is given in 26.6 and structural adhesive bonded honeycomb sandwich panels in Section 216.

26.22 NON-STRUCTURAL BONDING

Non-structural adhesives are considered those adhesives that may fail in service without endangering the safety of the aircraft. They are not used where structural integrity is required as the bond strength/reliability is of a lower order. Non-structural adhesives are used for joining rubber, foam, plastics, fabrics, leather and metals, while structural bonding mainly concerns metal-to-metal fastening. In general, the shear strength of non-structural adhesives is in the range of 200-1200 psi and the peel strength ranges from 10 to 30 lb. in. per inch width.

Non-structural bonding is generally faster and less expensive than structural bonding in those applications where structural integrity is not mandatory.

Design information on non-structural adhesive bonding is given in 26.7. Non-structural adhesive bonded sandwich panels are a unique system in themselves, not representing adhesive bonding as such; information may be found in Section 218 (new).

26.3 FORMS OF ADHESIVES

Adhesives are available in two basic forms: (1) dispersed in a fluidizing carrier solvent, either organic or aqueous; and (2) free of volatile carrier. The latter includes films, solvent free pastes, powders, and hot melts.

The first form of adhesive is most common because air drying can be employed in many cases to remove the carrier fluid for development of a good bond; also, common paint brushes or spray guns can be used to apply them, depending on the usage.

The carrier-free adhesives are rapidly gaining favor as the most practical for assembly line structural bonding. They provide the strongest adhesive bonds obtainable. In this class of adhesives are (1) adhesive films, unsupported or supported; (2) lump and powder adhesives which are heated or cured by heat or solvent reaction; (3) pastes, solvent free, which must be cured to develop cohesive strength. The epoxy resin based paste adhesives are among the most versatile adhesives available.

26.4 DESIGN OF ADHESIVE BONDED JOINTS

A. JOINT DESIGN. To realize maximum efficiency from adhesives, joints should be expressly designed for adhesive bonding. The detailed stress analysis of an adhesive bonded joint is difficult partly because of the nonlinear stress-strain characteristics of adhesives. Stress analysis has shown that stresses are not uniformly distributed across the adhesive joint, being greatest at the free edges of the glue line.

B. TYPES OF JOINTS. Selection of adhesive joint design is a compromise between strength and joint preparation cost. The design of metal to metal joints is influenced by the magnitude and direction of the load the joint will have to bear. Figure 26.4-1 shows several possible joint configurations. In non-structural applications little more than selection of a desired joint configuration is required. However, in structural applications, more detailed consideration must be given to the effects of the individual joint on the part configuration and load distribution.

C. ANGLE JOINTS. The lower portion of Figure 26.4-1 presents an evaluation of angle joints for resistance to cleavage against four directions of stress application. When heavy sections are bonded, the parts should be designed so that the adhesive is in shear. Cleavage stresses should be avoided or minimized whenever possible.

D. BUTT JOINTS. Butt joints are easily fabricated but are impractical because of probable failure when loaded in tension. In cases where a butt joint must be made, a bonded shear component should exist along at least part of the bond line.

E. LAP JOINTS. Lap joints are the most commonly used adhesive joints. Peak stresses develop at the ends of the lap due to the eccentricity of loading resulting from the finite thickness of the joint and the differential strain induced between adherends and adhesive by the load.

F. SCARF JOINTS. Scarf joints are butt joints where the joint angle is less than 90°. The joint is relatively costly to produce. Because of machining requirements it can not be used on thin stock.

G. JOGGLE LAP JOINTS. Joggle laps are a means of lining up tensile forces in joining thin sheet or parts but should be avoided if complete sealing of the joint is required.

26.4 DESIGN OF ADHESIVE BONDED JOINTS (Continued)

H. STRAP JOINTS. The strap, double strap, recessed double strap, beveled double strap, half lap and double lap all provide good resistance to bending stresses.

I. STRESS CONCENTRATIONS. Stress concentrations

at the ends of a lap joint tend to result in an apparent failing stress lower than the actual or theoretical value. (This apparent failing stress is defined as the observed breaking load divided by the lap area). It has been found that the failing stress is independent of the width of overlap but diminishes with increasing length of overlap. Figure 26.4-2 shows the effect of overlap length at room temperature.

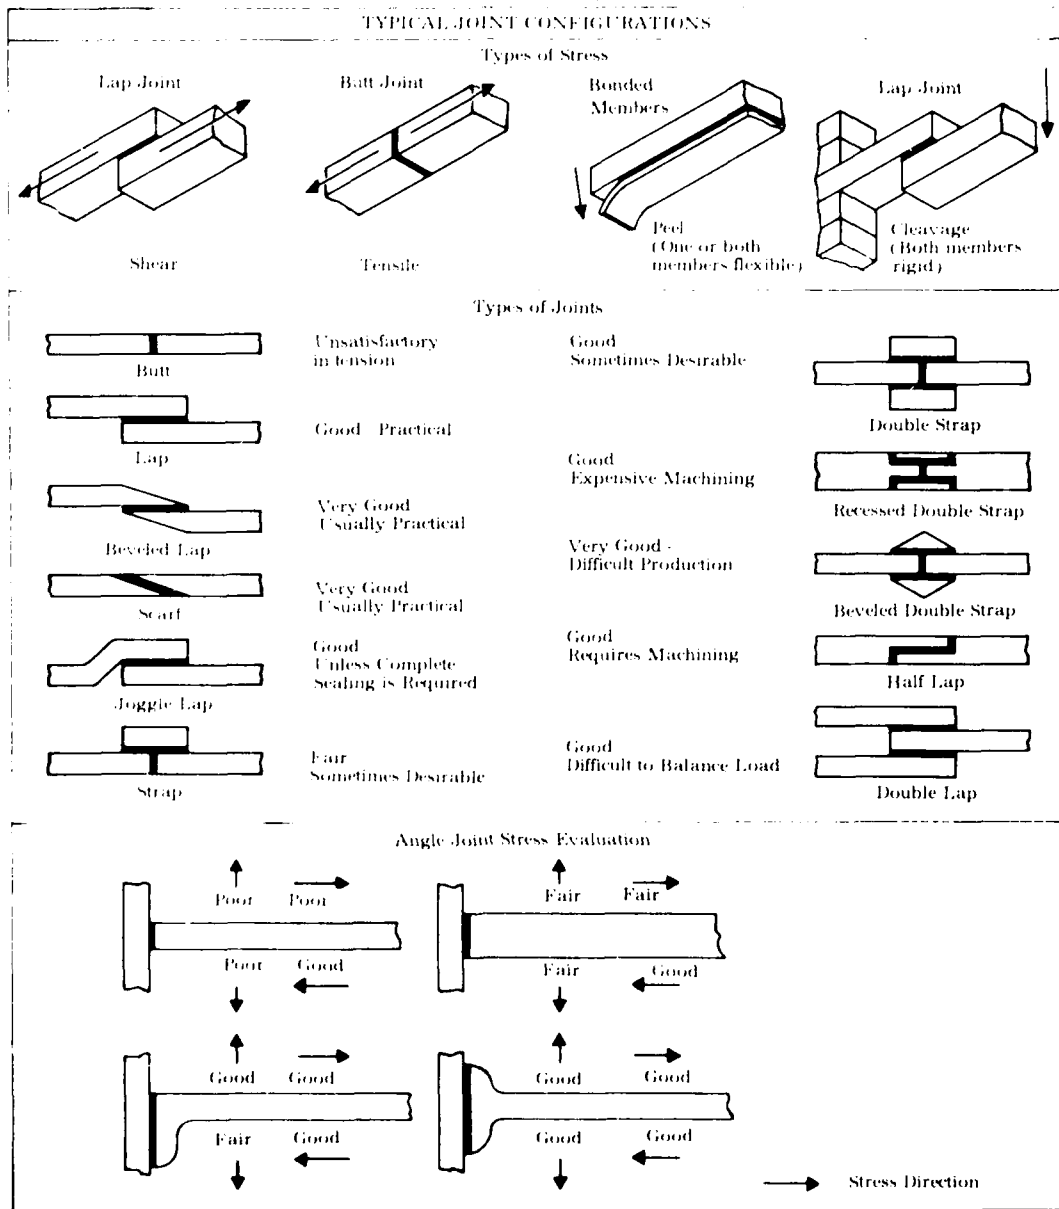


Figure 26.4-1

26.4 DESIGN OF ADHESIVE BONDED JOINTS (Continued)

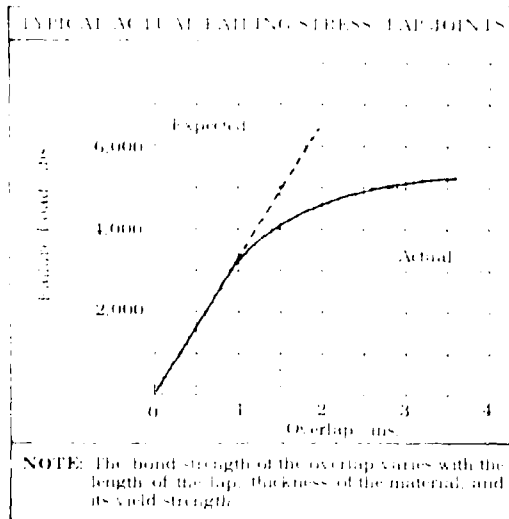


Figure 26.4-2

26.5 DESIGN OF ADHESIVE BONDED PARTS

When designing parts for adhesive bonding, the following basic design guides should be followed if the maximum strength of the adhesive is to be achieved:

- A. Stiffness and thermal expansion coefficients of the adherends should be as similar as possible.
- B. Arrange the adhesive bond in shear or compression avoiding flatwise tension and peel.
- C. Stress concentrations at edge of joints can be reduced in heavier structures by tapering the edge of adherends or using stepped doublers.
- D. Make the bond area large enough to carry the required load.
- E. Make the contours of mating structures as similar as possible to ensure uniform pressure application to all sections of the bondline.

26.6 STRUCTURAL BONDING DESIGN INFORMATION

26.61 DESIGN OF ADHESIVE BONDED STRUCTURES

A. **LOAD DISTRIBUTION.** Uniform load distribution is necessary to obtain optimum joint efficiency and fatigue life. Close coordination with both the materials technology organization and the tooling group is necessary in order to avoid excessive production costs. The following objectives apply for optimum adhesive bonding design:

1. Minimize any stress concentrations in the adhesive bond.
2. Provide efficient distribution of loading to the attached component.
3. Apply stresses in shear or compression.

B. **CURING ESSENTIALS.** Extensive processing is required in structural bonding. The bonding process requires:

1. Even pressure distribution to ensure proper contact during the flow and wetting stages of the cure; consequently, dimensional tolerances are very critical. These tolerance problems can occur when nested parts having contact are bonded.
2. Temperature application as uniform as possible to provide even curing of all sections of the bond.

C. **DESIGN OBJECTIVES.** The above requirements make it necessary to design parts and details which can be easily fabricated.

D. **DESIGN PRECAUTIONS.** In the design of assembly or installation of bonded structures the following precautions should be taken:

1. Avoid locating fasteners in the vicinity of joggles.
2. Consider the effect of any possible corrosive attack.

**THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC**

**26.611 METALS SUITABLE FOR STRUCTURAL
ADHESIVE BONDING**

Figure 26.611-1 lists metals that may be bonded.

MATERIAL	SERIES
Wrought Aluminum Alloy	2024
	3003
	5052
	5456
	6061
	7075
	7079
	7178
Corrosion-Resistant Steel	A1
Magnesium	AZ31 HE131
Titanium	Ti-6Al-4V
	Ti-8Al-1Mo-1V
	Ti-CP

Figure 26.611-1

B. ENVIRONMENTAL CONSIDERATIONS. Service conditions or resistance to environmental factors that must be taken into account include the following:

1. Type of loading
2. Operating temperature
3. Fluid exposure: JP-4 fuel, BMS 3-11 Hydraulic Fluid, oil spray, etc.
4. Corrosion

C. STRENGTH CONSIDERATIONS. Strength considerations that must be accounted for include:

1. Tensile shear strength
2. Peel and fatigue strengths
3. Creep strength
4. Flexibility, stability, etc.

**26.612 SELECTION OF AN ADHESIVE BONDING
SYSTEM**

A. CHOICE OF ADHESIVES. For structural bonding the class known as thermosetting adhesives is used. Two primary thermosetting types are the epoxy and phenol-formaldehyde (commonly called phenolic resin) systems. Modifiers are added to give desired properties. Other thermosetting resins are available but are not used to a great extent. Figures 26.6121-1 and 26.6121-2 present information for assisting in the selection of an adhesive system. DMS 4A3, Section 512, presents design allowable information for the various structural adhesive systems.

IMPORTANT NOTE: Electrolytic corrosion during processes will cause weakness in the bonding of the profile of the aluminum alloy sheet. A major factor is the use of, for example, bonding per BAC 5514 of the epoxy resin assembly with the BMS 5-42 adhesive system. To protect the aluminum alloy material, the temperature of the process is 32°F for assembly as indicated. The use of mechanical properties of the material as reported in the temperature and corrosion data of exposure design Manual, series 81A series, in the NAVAIR subcommittee provides data on the resulting reduced values.

26.6121 SELECTION OF ADHESIVES

Figures 26.6121-1 and 26.6121-2 provide information on the selection and mechanical properties of structural adhesives.

ADHESIVE SELECTION CHART FOR STRUCTURAL BONDING				
Process Specification BAC No.	Adhesive System BMS Number	Type of Structure	In-Service Temperature Limitations °F	Remarks
5514-542	5-42	Metal-to-Metal (1) Structures	250	Specify for bonding of sheet doublers and stiffeners of aluminum alloy, magnesium alloy, or titanium.
5514-551	5-51	Metal-to-Metal Structure Aluminum Honeycomb Sandwich (1) (2)	180	Specify for machined honeycomb assemblies for laminated and square edge assemblies. For bonding of sheet doublers and stiffeners of aluminum and titanium.
5514-570	5-70	Aluminum Honeycomb Sandwich	300	Specify for machined honeycomb laminated edge and square edge honeycomb assemblies.
5514-580	5-80	Metal-to-Metal Structure Aluminum Honeycomb Sandwich (1) (2)	180	Alternate to BAC 5514-551
<p>(1) Laminated sheet is available as BMS 5-69. Typical drawing callout shall be by the note: TWO PLY 0XXX SHEETS LAMINATED PER BMS 5-69. The note shall refer to the applicable parts by flag in the stock size and material column of the parts list.</p> <p>(2) See BMS 4-4 and 4-6 for honeycomb core drawing callouts</p>				

Figure 26.6121-1

26.6121 SELECTION OF ADHESIVES (Continued)

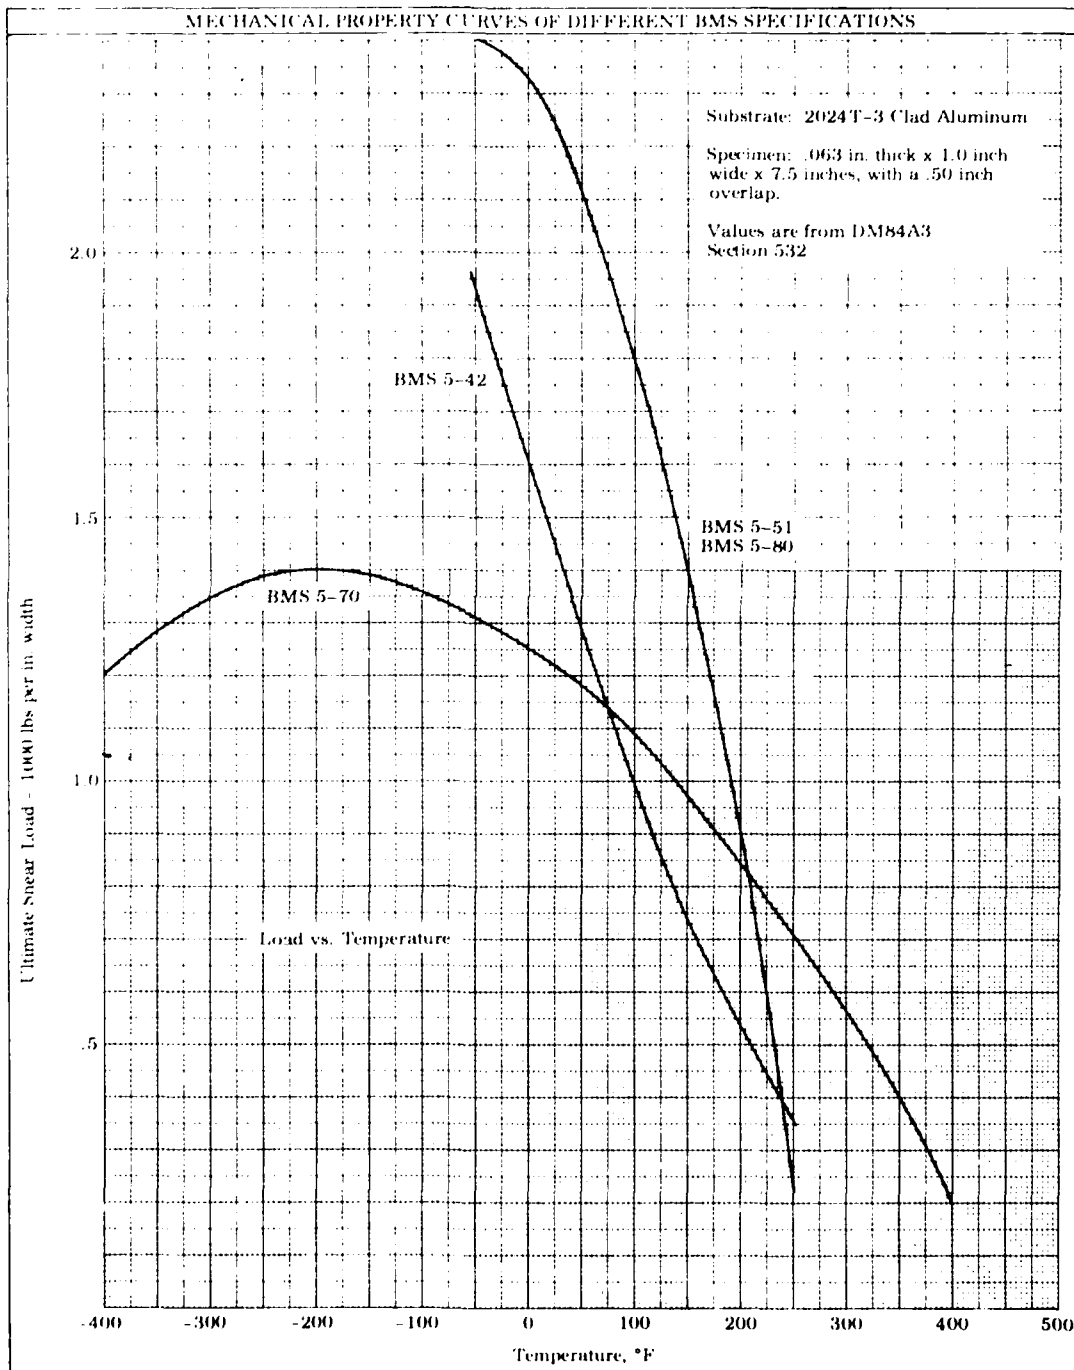


Figure 26.6121-2

26.613 CURED BOND LINE THICKNESSES

The cured nominal bond line thickness for structural adhesives varies, depending on the usage of the adhesive, curing pressure, width of the overlap and the chemical nature of the adhesive. The values given in Figure 26.613-1 are for typical wide area bonds (12" x 12") and would vary if the overlap was smaller.

CURED BOND LINE THICKNESSES AND WEIGHTS		
Adhesive	Cured Nominal Bond Thickness (inches)	Nominal Weight lb/ft
BMS 5-42 (1) Type 1 with Type 2, Grade A Type 2, Grade B Type 3, Grade C	.009 .011 .004	.055 .07 .03
BMS 5-51 (1) Type 1 with Type 2, Grade 5 Type 2, Grade 10 Type 3, Grade 15	.003 .008 .012	.03 .06 .08
BMS 5-70 (3) (Type 1 Liquid Adhesive with Type 2 Tape Adhesive) Bonded per BAC 5413	.01	.085
BMS 5-80 (1) Type 1, Grade A or Grade B with Type 2, Grade 5 Type 2, Grade 10 Type 2, Grade 15	.005 .010 .015	.03 .06 .08

(1) Cured bond line thickness will vary with pressure and width of overlap.

(2) Heavy scrim in the bond line keeps bond thickness fairly uniform regardless of pressure or length of overlap.

(3) This is a very high flow adhesive. Narrow bond overlaps (.50 to .625) will have a nominal .006 in. bond line. Wide overlaps with the same pressure will have .01 to .012 inch thick bond lines.

Figure 26.613-1

26.614 DRAWING CALLOUT

Drawings shall callout the adhesive system and process by the following:

BOND WITH BMS 5 xx PER BAC 54xx

BAC 5514 "Common Bonding Requirements for Structural Adhesive Systems", collects and specifies all the common processes for all structural bonding adhesive systems. A BAC 5514 dash-numbered specification is used for each specific adhesive systems individual processing requirements. For ease of reference, the dash number will be the three digits of the BMS numbers. Therefore, the BMS will not need to be called out. The callout will then be:

BOND PER BAC 5514 551 (BAC 5514 580 OPTIONAL)

The callout shall be referred to by flags in the appropriate place on the field of the drawing and in the material column of the list of materials for both details and their assemblies.

NOTE: For drawing callout of specific processes and/or materials, see the references in 26.021.

26.62 ADHESIVE BONDED HONEYCOMB SANDWICH PANELS

Honeycomb sandwich structures consist of two high density faces or skins separated by a relatively light weight stabilized core. The function of the core is to stabilize and separate the faces and to resist transverse shear loads and local crushing loads normal to the faces. The selection of the core and face materials will depend upon the particular requirements the structure must meet.

The designations, structural and non-structural, are used to describe the two types of bonded sandwich construction. Non-structural sandwich panels are covered in Section 218.

Structural sandwich panels are covered in Section 216.

26.7 NON STRUCTURAL ADHESIVE BONDING - DESIGN INFORMATION

26.71 SELECTION OF AN ADHESIVE SYSTEM

A. The following considerations should apply when selecting non structural adhesive systems:

1. The materials to be bonded; their surface condition (rough or smooth, porous or non porous); their susceptibility to "crazing" (acrylic and polystyrene plastics); flexibility; method of prebond treatment.
2. The environmental resistance of the adhesive bonded joint to moisture, oils and greases, BMS 3-11 Hydraulic Fluid, ozone, fuels and solvents, temperature (also cyclic temperature change), radiation, and fluids such as cleaning materials, coffee, urine, etc.
3. The type of loading to which the adhesive-bonded joint will be subjected, i.e., fatigue, shear, tension, peel, vibration, and their strength requirements.
4. The method of adhesive application, i.e., manual brush, extension gun, spray, dip, roller coat and trowel.
5. The assembly requirements, i.e., assembly location such as factory or field, the access of bonding tools such as spray guns, rollers, vacuum bagging equipment, bonding jigs, elevated temperature curing equipment (ovens and heat guns).

6. The curing requirements, i.e., temperature (elevated or room), pressure and cure time.
7. Special requirements such as color, electrical properties, and high frequency heating from nearby electronic equipment including radar and antenna systems.
8. The materials to be bonded must be resistant to corrosion resulting from the action of harmful substances present in, or produced from the adhesive used. Although this type of action is comparatively rare, it must be recognized and avoided.

Examples:

- a. Some epoxy compounds react detrimentally with copper and brass.
 - b. Some neoprene adhesives react with moisture to release hydrochloric acid.
 - c. Some silicone adhesives react detrimentally with copper and brass.
9. Bonding cost considerations are heavily influenced by the labor involved in application. Figure 26.713-1 shows cost of bonding a one-foot square area. Even under these comparable conditions, the method of application can cause total costs to vary over 300%. For large areas, high production, or peculiar shapes, consult the Materials Technology organization for cost analysis and guidance.

B. When the design of non structural joints approaches any of the limitations noted in Figure 26.711-2 consult the Materials Technology organization.

THIS PAGE IS BEST QUALITY PRACTICABLE
COPY FURNISHED TO DDC

26.711 SELECTION OF ADHESIVES

A. The adhesives shown in Figure 26.711-1 are recommended for nonstructural bonding applications.

B. Thermosetting adhesives (i.e., Types 38, 54, 59, etc.) are relatively rigid and exhibit high tensile and shear strength (see Figure 26.711-2 whether the load be applied at a fast rate (dynamic), or a constant load (static).

They also have good fatigue characteristics. However, rigid adhesives have relatively poor bonding qualities when stressed in peel or cleavage.

C. Some adhesives show high tensile and shear strength but have poor resistance to constant or vibrating stresses. The rubber based adhesives (i.e., Types 40, 48, 53, etc.) have low tensile or shear strength, but because of film elasticity, develop high peel or cleavage strength.

SUGGESTED BAC 5010 ADHESIVE TYPES FOR VARIOUS COMBINATIONS OF SURFACES																	
Adhesives	BAC 5038																
Acrylics	12	17	30														
Cellulose	40	48															
Cork	12	44	30	40	12	38											
	48	48	40	48	40	48											
Felt	12	59	30	40	38	40	34	38	30	34							
	48	48	48	48	48	48	48	48	48	48							
Glass, Ceramics	12	59	30	40	12	38	12	38	38	40	38	40	44	54			
	48	48	40	48	48	48	48	48	48	48	48	48	48	48			
Leather	12	59	30	48	12	38	12	38	38	48	12	38	12	48			
	48	48	48	48	48	48	48	48	48	48	48	48	48	48			
Nylon	12	59	40	48	38	40	38	48	38	40	38	44	38	48	38	44	58
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Steel and Aluminum	12	48	40	48	48	40	48	48	40	48	12	38	12	48	12	40	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Brass and Copper	12	44	40	44	40	44	12	48	40	48	12	40	12	48	12	40	48
	51	48	48	51	48	51	44	48	44	48	44	48	44	48	44	48	48
Nylon	12	44	12	40	40	48	12	38	38	40	38	40	12	38	38	40	48
	51	48	48	51	48	51	48	51	48	51	48	51	48	51	48	51	48
Paper Cardboard	12	59	12	30	12	30	12	30	30	34	12	30	12	30	12	30	34
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Phenolics	12	44	30	40	12	38	40	38	44	38	40	38	44	38	44	38	44
	51	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Polyester & Epoxy Formulates	12	44	30	40	38	40	34	38	44	38	40	38	44	38	44	38	44
	51	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Polyurethane A B S ①	12	59	17	30	30	38	30	38	38	48	12	38	12	38	12	38	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Polyurethane Foam	12	12	48	12	48	12	48	12	48	12	48	12	48	12	48	12	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Polyurethane Chloride, Flexible	12	12	48	12	48	12	48	12	48	12	48	12	48	12	48	12	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Polyurethane Chloride, Rigid	14	18	48	51	48	18	18	14	18	14	18	14	18	14	18	14	18
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Rubber, Butyl	12	59	40	48	40	48	40	48	40	48	40	48	40	48	40	48	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Rubber, Butyl	14	14	44	44	44	44	44	44	44	44	44	44	44	44	44	44	44
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Rubber, Neoprene	12	59	40	48	40	48	40	48	40	48	40	48	40	48	40	48	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Rubber, Silicone	60	68	60	68	60	68	60	68	60	68	60	68	60	68	60	68	68
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Teflon	12	59	30	40	38	40	12	34	30	40	38	40	14	18	38	40	48
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Wood	12	59	30	40	12	30	38	12	38	38	40	19	38	12	30	12	30
	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48	48
Adhesives	Cellulose	Cork	Fabrics	Felt	Glass Ceramics	Leather	Nylon	Steel and Aluminum	Brass and Copper	Nylon							

Figure 26.711-1 (Continued)

[illegible]

Figure 26.711-1

IMPORTANT

Steps Necessary To Select The Correct Adhesive

2. Check the process documents and specifications under 26.022. If your bonding job is covered by one of the documents or specifications, callout that particular document or specification. If your job is not covered by any document or specification, proceed to Step 3.
3. Select the possible adhesive types found in Figure 26.711-1 by matching the substrates.
4. Referring to Figure 26.711-2, select the proper adhesive for your job. Determine which (if any) of the possible adhesives meets the requirements for this job. See Figure 26.711-2 for important criteria to consider, i.e., BMS 3-11 Hydraulic Fluid, oil, fuel and water resistance, etc. Consult Figure 26.713-1 to compare costs of suitable adhesives.
5. For any applicable criteria not covered by Figures 26.711-2 and 26.713-1, consult the Materials Technology organization for recommendations.
6. Drawing callout for the adhesive you have selected is described in 26.714.

26.711 SELECTION OF ADHESIVES (Continued)

ADHESIVE PROPERTIES				
Buyer's Spec. No.	Manufacturer's Designation or BMS No.	Description	Visual Appearance	Physical Properties & Primary Uses
	Bostik 1008A Bostik 1008B Accelerator Bostik 1007 Primer	A black two component, room temperature curing Neoprene base adhesive in a Toluene vehicle.	Black, brushable syrup.	Tough, flexible, contact type rubber cement used for bonding & splicing Neoprene rubber & Neoprene coated fabric to themselves. Not recommended for de-icing boots.
9	Cyclohexanone	Cyclohexanone vinyl solvent for bonding vinyl parts or films to themselves.	Very thin, clear, pale amber liquid.	Used for bonding vinyl parts or films to themselves.
12	BMS 5-55	A one part synthetic rubber base adhesive in a naphtha vehicle.	Brown, thin, brushable liquid.	A flexible contact cement. Provides immediate strength without clamping. Will not craze acrylics.
17	Laquer Thinner per Federal Specification TT-T-296.	A blend of solvents used for bonding Styrene & Cellulosic plastics to themselves.	A clear, water thin liquid.	A clear liquid used for bonding Polystyrene, A-B-S, & Cellulosic plastics to themselves.
19	Lauxite RF-2905 2905 Hardener Castophen RS-216 FM-60M Catalyst Catalin 726 Accelerator 30 Bostik 1007 Primer	A two component, resorcinol resin base, formaldehyde catalyzed, room temperature curing adhesive.	Black, medium, brushable syrup.	A rigid adhesive high in tensile & shear strength. Used for bonding wood to wood & wood to wood laminates. For flyaway & non-flyaway applications.
30	BMS 5-43	A one part, room temperature setting Nitrocellulose base adhesive in a Ketone & Ester vehicle.	Clear, pale yellow, medium syrup.	A transparent, rigid thermoplastic adhesive, which dries rapidly to give immediate strength. Will craze acrylics & other thermoplastics. Used for bonding wood, paper, felt & cork to themselves & to each other.
34	BMS 5-56	A one part, water dispersed rubber base adhesive.	Cream colored, thin paste.	A light amber flexible contact adhesive. Easy application, non-flammable, & possesses very little odor. Used for bonding paper, charts & placards, felt, fabric, & other porous materials to metal & wood.
38	BMS 5-29, Type I EC-776 Primer	A two part, Polyamide resin, Epoxy base adhesive.	Clear, light yellow, medium-heavy syrup.	A rigid general purpose Epoxy adhesive high in tensile & shear strength. Used for bonding Polyester & Phenolic fiber-glass laminates & metals to themselves & each other. Not to be used on copper or brass.

Figure 26.711-2 (Continued)

26.711 SELECTION OF ADHESIVES (Continued)

ADHESIVE PROPERTIES (Continued)							
BAC 5010 Type No.	Resistance To Liquids	Application & Cure	Flash Point	180° Peel Strength	Shear Strength	Temperature Limitations	Drawing Callout
5	Resistant to water & oil. Poor resistance to fuel. Not BMS 3-11 resistant.	Brush application. Cures at room temperature.	40°F	MIL-W-5665, Type II, Class 3, (cotton webbing) bonded to 2024-T3 aluminum. 8 lbs/in (2)	MIL-W-5665, cotton webbing bonded to aluminum: 539 psi (2)	200°F	BAC 5010 TYPE 5
9	Restricted only by the properties of the vinyl.	Brush or spray, by solvent evaporation.	93°F	Slightly less than material being bonded.	Slightly less than material being bonded.	Restricted only by the properties of the vinyl.	BAC 5010 TYPE 9
12	Resistant to water. Poor resistance to oils & fuel. Not BMS 3-11 resistant.	Brush or spray. Cures by solvent release. May be reactivated with naphtha.	54°F	MIL-W-5665, Type II, Class 3, (cotton webbing) bonded to 2024-T3 aluminum. 10 lbs/in (2)	MIL-W-5665 (cotton webbing) bonded to aluminum: 80 psi (1)	-30°F to 125°F	BAC 5010 TYPE 12
17	Restricted only by the properties of the plastics.	Brush or dip. Cures by solvent evaporation.	Below 60°F	Slightly less than material being bonded.	Slightly less or sometimes greater than the material being bonded.	Restricted only by the properties of the plastics.	BAC 5010 TYPE 17
19	Resistant to water, oil, & fuels.	Brush or spreader. Cure at room temperature or with aid of heat up to 130°F. Requires clamping during cure.	Resin: 102°F Activator: 177°F	MIL-R-6855, Class 1, Grade 60, Buna-N rubber bonded to 2024-T3 aluminum. 9 lbs/in (2)	Bond is stronger than wood where density is .76 or less.	300°F	(3)
30	Fair resistance to water, oils, & fuels. Cannot stand continuous immersion. Not BMS 3-11 resistant.	Brush or roller coat. Cures by solvent evaporation.	0°F	MIL-W-5665, Type II, Class 3, (cotton webbing) bonded to 2024-T3 aluminum. 6 lbs/in (2)	MIL-W-5665 (cotton webbing) to aluminum: 300 psi (1)	200°F	BAC 5010 TYPE 30
34	Fair resistance to water & oils. Poor resistance to fuels. Not BMS 3-11 resistant.	Brush, spatula or sprayed. Cures by solvent evaporation.	Above 80°F	MIL-W-5665, Type II, Class 3 (cotton webbing) bonded to 2024-T3 aluminum. 1.5 lbs/in (2)	MIL-W-5665 (cotton webbing) to aluminum: 55 psi (1)	-20°F to 200°F	(4)
38	Resistant to fuel, oil, & BMS 3-11. Fair resistance to water.	Stiff brush, spatula, roller, or spreader. Cures at room temperature or with aid of heat up to 250°F. Requires contact pressure.	Part AB: 395°F Part CD: 468°F	2024-T3 aluminum bonded to 2024-T3 aluminum. 3.7 lbs/in (2)	Aluminum to aluminum: 1000 psi (1)	160°F	(5)

Figure 26.711-2 (Continued)

26.711 SELECTION OF ADHESIVES (Continued)

ADHESIVE PROPERTIES					
BAC 5010 Type No.	Manufacturer's Designation or BMS No.	Description	Visual Appearance	Physical Properties & Primary Uses	Resistance To Liquids
40	BMS 5-14	A one part, Buna-N base, room temperature curing adhesive in a Ketone vehicle.	Light brown to dark amber, medium, brushable syrup.	A tough, flexible contact type adhesive with good peel strength. Provides immediate strength without clamping. Should be used where good fuel resistance is required & odor is not objectionable. Bonds fabrics, felt, cork, wood, Buna-N rubber, glass, metals, & vinyl plastics.	Resistant to water, oil, & fuels. Not BMS 3-11 resistant.
44	BMS 5-19	A two part, Polysulfide rubber base room temperature curing adhesive & sealant. 100% solids.	Thick, brown paste.	Cures to a tough flexible rubber, with good peel strength. Used for bonding nonporous materials such as phenolic & polyester laminate, & metals to themselves & to each other where a flexible adhesive with good peel strength is required. The gap filling properties of this adhesive are very good.	Resistant to fuel, water, & salt spray. Poor resistance to BMS 3-11.
45	BMS 5-58 A-4094 ⑦	A two part, room temperature vulcanizing Silicone rubber.	Light brown, pourable paste.	Cures to a flexible rubber. Used for bonding Silicone rubber sheet and extrusions to metals & plastics or to themselves. Its use is limited to applications where bond strength is not critical.	Resistant to water. Poor resistance to oil & fuel. Fair BMS 3-11 resistance.
46	A-4000 Silicone Adhesive A-4000 Catalyst A-4014 Primer ⑦	A two component, Silicone resin, room temperature curing adhesive.	Water clear, thin syrup.	A contact type Silicone adhesive. Cures to a resilient film. Used for bonding silicones to themselves or other materials. Its use is limited to applications where bond strength is not critical.	Resistant to water. Poor resistance to oil & fuel. Fair BMS 3-11 resistance.
47	BMS 5-57	A one part, Silicone base, room temperature curing, pressure sensitive adhesive.	Clear to milky, medium syrup.	Pressure sensitive adhesive. May be used for low strength applications up to 600°F such as bonding low density insulation material.	Resistant to water. Poor resistance to oil & fuel. Not BMS 3-11 resistant.
48	BMS 5-30	A one part Buna-N base adhesive in an ester solvent.	Tan to amber, brushable, medium syrup.	A tough, flexible, low odor, contact type adhesive with good peel strength. Should be used in areas where passenger comfort is a consideration. Bonds fabrics, felt, cork, wood, Buna-N rubber, glass, metals, & vinyl plastics.	Resistant to water, oil, and fuels. Not BMS 3-11 resistance.
49	BMS 5-34	A two component Polysulfide-Epoxy, room temperature curing adhesive.	Off-white, brushable syrup.	A tough rigid adhesive. Used where BMS 3-11 resistance is required.	Resistant to BMS 3-11, oil, and fuels. Poor water & salt spray resistance.
50	BMS 5-36	A one part, non-solvent, rapid setting, room temperature curing adhesive.	A colorless, slightly milky, low viscosity liquid.	Tough, quick setting adhesive for soft rubber (BMS 1-28) & for bonding strain gauges. Very expensive. Use on small parts only.	Poor resistance to water & salt spray. Resistant to BMS 3-11, oil, and fuels.

Figure 26.711-2 (Continued)

26.711 SELECTION OF ADHESIVES (Continued)

ADHESIVE PROPERTIES (Continued)						
BAC 5010 Type No.	Application & Cure	Flash Point	180° Peel Strength	Shear Strength	Temperature Limitations	Drawing Callout
40	Brush or spray. Cure by solvent evaporation. May be reactiv- ated with methyl ethyl Ketone up to 24 hours after application.	30°F	15 lbs/in; MIL- W-5665 (cotton webbing) to aluminum. ①	175 psi; MIL- W-5665 (cotton webbing) to aluminum. ①	300°F	BAC 5010 TYPE 40
44	Knife, spatula or pressure gun. Cures by vulcan- ization at room temperature or at temperatures up to 180°F. Requires contact pressure during cure.	Above 80°F	20 lbs/in; see BMS 5-19 ①	278 psi; aluminum to aluminum. ②	200°F	BAC 5010 TYPE 44
45	Knife or spatula. Cures by vulcan- ization at room temperature. Requires contact pressure during cure.	Above 80°F	Very low peel strength.	135 psi; aluminum to aluminum. ①	- 70°F to 300°F	BAC 5010 TYPE 45
46	Brush. Cures by polymerization at room tempera- ture. Does not require clamp- ing.	60-90°F	BMS 1-22 bonded to 2024-T3 aluminum. 7.8lbs/in ②	MIL-W-5665 Type II, Class 3, (cotton webbing) bonded to 2024-T3 aluminum. 281 psi ②	- 65°F to 400°F	BAC 5010 TYPE 46
47	Brush or spray. Becomes tacky by solvent evaporation.	70°F- 100°F	1.5lbs/in; MIL-W-5665 to aluminum. ①	2024-T3 aluminum to aluminum 10 psi. ①	- 65°F to 600°F	BAC 5010 TYPE 47
48	Brush or spray. Cures by solvent evaporation. May be reactiv- ated with methyl ethyl Ke- tone up to 24 hours after ap- plication.	30°F	MIL-W-5665, Type II, Class 3, (cotton webbing) bonded to aluminum 17 lbs/in ②	100 psi; MIL- W-5665 to aluminum. ①	300°F	BAC 5010 TYPE 48
49	Knife or spatula. Cures by poly- merization at room temperature. Requires clamping during cure.	Part A, 472°F Part B, 277°F	Rigid adhesive. Very low peel strength.	200 psi; MIL- W-5665 to aluminum. ①	160°F	BAC 5010 TYPE 49
50	Brush or swab. Cures at room temperature by moisture ab- sorption.	176°F	BMS 1-11, Grade 40, Neoprene rubber bonded to 2024-T3 aluminum 30.6 lbs/in ②	BMS 1-11, Grade 40, to aluminum. Also alumi- num to aluminum. 100 psi ①	180°F	⑥

Figure 26.711-2 (Continued)

26.711 SELECTION OF ADHESIVES (Continued)

ADHESIVE PROPERTIES (Continued)					
BAC 5010 Type No.	Manufacturer's Designation or BMS No.	Description	Visual Appearance	Physical Properties & Primary Uses	Resistance To Liquids
51	BMS 5-31	A two component polysulfide base room temperature curing adhesive.	A translucent, brownish-green paste.	A tough flexible adhesive. Used primarily to bond Nylon & Mylar to themselves & other materials. Should be used when resistance to vibration and fuel is a factor.	Resistant to water, fuel, & oils. Poor resistance to BMS 3-11 & salt spray.
52	BMS 5-60	A two component Epoxy, low viscosity, quick setting, room temperature curing adhesive.	Clear amber, low viscosity liquid.	Quick setting. Good electrical properties. Used for bonding phenolic, laminated sheet & metal-clad.	Resistant to BMS 3-11, oil, & fuel. Poor resistance to water & salt spray.
53	Gaco N-29 Cold bond Gaco N-39 Accelerator Gaco N-15 Primer	A two component, Neoprene base, room temperature curing adhesive.	Medium viscosity syrup. Olive drab to black color.	A tough, flexible contact adhesive. Used for bonding and splicing Neoprene rubber and Neoprene rubber coated fabrics to themselves & with a primer to metals.	Resistant to water and oil. Poor resistance to fuels. Not BMS 3-11 resistant.
54 Grade 1	BMS 5-25 Grade 1	A two component, aluminum filled, room temperature curing, Epoxy resin base adhesive.	Red paste	A rigid adhesive high in tensile & shear strength, but poor in peel strength. Used for bonding metal to metal in non-structural applications where high strength is required. Bonds metals, plastics, wood, glass and fiberglass laminates to themselves & to each other. Do not use for bonding copper & brass. Good filling properties.	Resistant to BMS 3-11, oil, and fuel. Poor resistance to water and salt spray.
54 Grade 3	BMS 5-25 Grade 3		Gray paste		
56	Epon 828 Pyromellitic Dianhydride Accelerator	A two component, high temperature curing, Epoxy resin adhesive.	Canary yellow syrup.	A rigid adhesive high in tensile and shear strength, but poor in peel strength. Used for bonding Teflon to metal. Good at high temperatures.	Resistant to water and oil. Poor resistance to fuels. Not BMS 3-11 resistant.
58	EC-880	A one component, room temperature setting synthetic rubber adhesive.	Light tan, brushable syrup.	Synthetic rubber contact cement. Good flow resistance, heat resistance. Synthetic rubber to metal, wood, & most other surfaces.	Resistant to water and oil. Poor resistance to fuels. Not BMS 3-11 resistant.
59	Epon 913	A two component room temperature or heat curing Epoxy resin base adhesive.	Dark gray paste	A rigid Epoxy resin system, high shear strength. Bonds metal, Buna-N rubber, acrylics, wood, & glass to themselves & to each other. Good bond strength to oily metals.	Resistant to fuel, oil, BMS 3-11, & water. Not resistant to salt spray.
60	Q-3-0121 RTV 1200 Primer ①	A one component room temperature vulcanizing Silicone rubber.	Creamy, white paste.	Cures to a white rubbery solid. Excellent peel strength and good electrical insulating properties. Good adhesion to Silicone rubber and most other materials.	Resistant to water and ozone. Poor resistance to oil. Fair resistance to BMS 3-11. Not fuel resistant.
68	93-046 RTV 1200 Primer ①	A two component room temperature vulcanizing Silicone rubber adhesive.	Heavy black paste.	Cures to a tough black rubbery solid. Very high peel strength. Adheres well to glass, cured Silicone rubber, cork, phenolic, Epoxy, Silicone resin laminates and most metals.	Resistant to water and ozone. Poor resistance to oil. Fair resistance to BMS 3-11. Not fuel resistant.

Figure 26.711-2 (Continued)

26.711 SELECTION OF ADHESIVES (Continued)

ADHESIVE PROPERTIES (Continued)						
BAC 5010 Type No.	Application & Cure	Flash Point	180° Peel Strength ①	Minimum Shear Strength ①	Temperature Limitations	Drawing Callout
51	Knife or spatula. Cures by polymerization at room temperature. Requires contact pressure during cure.	Above 150°F	10 lbs/in Mylar to aluminum. 5 lbs/in, Nylon to aluminum. ①	90 psi Mylar to aluminum. 150 psi, Nylon to aluminum. ①	-65°F to 160°F	BAC 5010 TYPE 51
52	Brush. Room temperature curing. Requires contact pressure during cure.		Rigid adhesive - very low peel strength.	500 psi, BMS 8-20 (phenolic laminate) to BMS 8-20. ①	250°F	BAC 5010 TYPE 52
53	Cures upon solvent evaporation by room temperature vulcanization.	Base, 34°F; Activator, 83°F.	MIL-W-5665, Type II, Class 3 (cotton webbing) bonded to 2024-T3 aluminum 12.9 lbs/in ②	MIL-W-5665, Type II, Class 3 (cotton webbing) bonded to 2024-T3 aluminum 267 psi ②	200°F	BAC 5010 TYPE 53
54 Grade 1	Knife or spatula. Cures by polymerization at room temperature or at temperature up to 200°F. Requires contact pressure during cure.	150°F	Rigid adhesive - very low peel strength.	1000 psi, aluminum to aluminum. ①	160°F	BAC 5010 TYPE 54 GRADE 1
54 Grade 3	Knife or spatula. Cures by polymerization at a temperature of 200°F to 350°F. Requires contact pressure during cure.	150°F	Rigid adhesive - very low peel strength.	1100 psi, aluminum to aluminum. ①	300°F	BAC 5010 TYPE 54 GRADE 3
56	Knife or spatula. Cures by polymerization at 350°F under 5 to 15 psi.		Rigid adhesive - very low peel strength.	2024-T3 aluminum bonded to aluminum 1863 psi ①	350°F	BAC 5010 TYPE 56
58	Brush or spray. Cures upon solvent evaporation at room temperature		MIL-W-5665 Type II, Class 3 (cotton webbing) bonded to aluminum 36 lbs/in ②	MIL-W-5665 Type II, Class 3 (cotton webbing) bonded to aluminum 410 psi ②	-20°F to 250°F	BAC 5010 TYPE 58
59	Knife or spatula. Cures by polymerization at room temperature or at temperature up to 180°F. Requires contact pressure during cure.		Rigid adhesive - very low peel strength.	2024-T3 aluminum to aluminum 404 psi. ②	180°F	BAC 5010 TYPE 59
60	Knife or spatula. Cures at room temperature by moisture absorption. Requires contact pressure during cure.		BMS 1-22 Silicone rubber bonded to 2024-T3 aluminum. 30 lbs/in	BMS 1-22, sandwiched between 2024-T3 aluminum lap shears. 234 psi ②	-85°F to 400°F	BAC 5010 TYPE 60
68	Spatula, trowel, or sealant gun. Cures at room temperature.				-70°F to 500°F	BAC 5010 TYPE 68

Figure 26.711-2 (Continued)

26.711 SELECTION OF ADHESIVES (Continued)

- ① Refer to minimum BMS requirement.
 - ② Refer to the average test results of T6-3133.
 - ③ 1. Wood flyaway application: BAC 5010, TYPE 19, METHOD I.
2. Wood non-flyaway application: BAC 5010, TYPE 19, METHOD II.
3. Bonding wood & Buna-N rubber to metals: BAC 5010, TYPE 19, METHOD III.
 - ④ 1. General application: BAC 5010, TYPE 34, METHOD I.
2. Bonding vinyl or polyurethane foams to metal: BAC 5010, TYPE 34, METHOD II.
 - ⑤ 1. General application: BAC 5010, TYPE 38.
2. Bonding to metal surfaces: BAC 5010, TYPE 38, SPECIAL METHOD I.
3. Non-structural metal to metal bonding: Using glass scrim: BAC 5010, TYPE 38, SPECIAL METHOD II.
 - ⑥ 1. General application: BAC 5010, TYPE 50, METHOD I.
2. Primer application only, for bonding thin rubber gaskets, complicated parts and where one highly plasticized surface is involved: BAC 5010, TYPE 50, METHOD II.
 - ⑦ Required on non-silicone rubber surfaces.
- NOTE: When the design of nonstructural joints approaches any of the limitations shown here, consult the Materials Technology organization for recommendations.

Figure 26.711-2

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY FURNISHED TO DDC

26.712 SURFACE REQUIREMENTS FOR
NON-STRUCTURAL BONDING

A. ALODIZED ALUMINUM SURFACES. No bonding restrictions when alodized per BAC 5719.

B. ANODIZED ALUMINUM SURFACES. No bonding restrictions when anodized per BAC 5019.

C. CHROMADIZED CLAD ALUMINUM SURFACES. No bonding restrictions when chromadized per BAC 5798.

D. BMS 10-11, TYPE 1, PRIMER OR BMS 10-53 PRIMER. No bonding restrictions when BMS 10-11, Type 1 Primer or BMS 10-53 Primer is applied per BAC 5736 or BAC 5745.

E. ZINC CHROMATE PRIMED SURFACES. Bonding to zinc chromate primed surfaces is allowed only:

1. When the bonded parts are completely and mechanically supported by means other than adhesives (Note: mechanical holding waived for overhaul and repair).
2. Where bolts, lining materials, paper, or felt are to be bonded.
3. Where the adhesive is used primarily to facilitate assembly.

Zinc chromate primer should be omitted from bonding areas on the original design or may be removed prior to bonding, whichever is more feasible.

F. ORGANIC PAINT FINISHES. Bonding is allowed, but not desirable, over epoxy enamel. Bonding is not allowable over:

1. Alkyd Enamel
2. Acrylic Enamel
3. Vinyl Paint
4. Nitrocellulose Lacquers

All organic finishes should be omitted from bonding areas (including epoxy enamel) in the original design or they may be removed later if this is more feasible.

G. CADMIUM PLATED STEEL. No bonding restrictions on cadmium plated steel which meets the requirements of Federal Specification QQ-P-416, Type 1, or BAC 5718 and BAC 5701 which specify chromate post plate treatment. See the applicable model finish specification for proper finish callout. Where the chromate post plate treatment is not allowed, contact the Materials Technology organization for bonding instructions.

H. CADMIUM PLATED TITANIUM. No bonding restrictions on cadmium plated titanium which meets the requirements of BAC 5804 and specifies chromate post plate treatment. See the applicable model finish specification for proper finish callout. Where the chromate post plate treatment is not allowed, contact the Materials Technology organization for bonding instructions.

I. POLYTETRAFLUOROETHYLENE (TFE - TEFLON). Teflon must be surface treated prior to bonding. There are no bonding restrictions on surface treated Teflon (purchased as "bondable" one-piece or on Teflon etched per BAC 5481 or BAC 5550).

- ① Where etching facilities exist.

26.713 COST INFORMATION

Comparative costs of adhesive bonding are given in Figure 26.713.1.

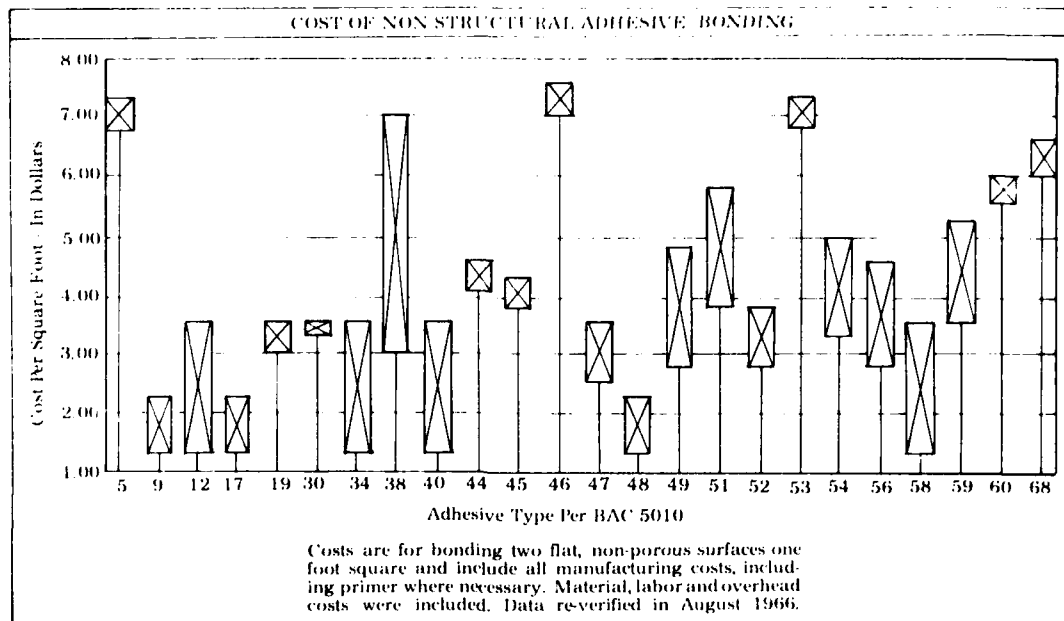


Figure 26.713.1

26.714 DRAWING CALLOUT

To obtain the proper drawing callout for nonstructural adhesive bonding follow the steps outlined in the footnote to Figure 26.711-1 and use the appropriate BAC 5010 Type number as indicated in Figure 26.711-2. The callout shall appear on the drawing as:

BOND PER (Drawing callout from Figure 26.711-2).

Example: BOND PER BAC 5010, TYPE 38, SPECIAL METHOD 1.

The callout shall be referred to by flags in the appropriate place on the field of the drawing and in the material column of the list of materials for both details and their assemblies.

NOTE: For drawing callout of specific processes and/or materials, see the references in 26.022.

LIST OF REFERENCES

1. "The Fastener Population Bomb," *American Machinist Magazine*, April 17, 1972.
2. *Assembly Directory and Handbook*, Hitchcock Printing Company, Wheaton, Illinois, 1969.
3. Walter Schwenk, *Fabrication Techniques for Rivet Fasteners Utilizing 55-Nitinol*, Interim Technical Report IR-85R-2 (IV), Air Force Materials Laboratory, March-May 1973.
4. C. R. McKenney and J. G. Baker, "Explosion-Bonded Metals for Marine Structural Applications," *Marine Technology*, July 1971.
5. V. D. Linse, R. H. Wittman, and R. J. Carlson, *Explosive Bonding*, DMIC Document 225, Battelle Memorial Institute, Columbus, Ohio.
6. F. R. Baysinger, "Welding Aluminum to Steel Using Transition Insert Pieces," *Welding Journal*, February 1969.
7. H. E. Otto and S. H. Carpenter, "Explosive Cladding of Large Steel Plates With Lead," *Welding Journal*, July 1972.
8. R. H. Whittman, "The Explosive-Bonding Process: Applications and Related Problems," ASTM E AD67-177, April 1967.
9. Private Correspondence with C. R. McKenney, Marketing Representative, Metal Classing Section, E. I. du Pont de Nemours and Company, February 28, 1973.
10. L. Farbo, Boeing Laboratory Test Report LSR-2852, New Orleans Test Facility, November 26, 1969.
11. L. A. Becker, *Evaluation of Bimetallic Couple for Use on Naval Combat Ships*, Naval Ship Research and Development Center Report 3634, May 1971.
12. *Marine Technology Magazine*, July 1971.
13. R. S. Koogler, "Fabrication Cost Comparison Study--Welded Aluminum/Steel, Bimetallic Strip Versus Mechanical Fastening," Project Order 2-0094.
14. Robert Yearick, "Shipshape for a Big Catch," *Du Pont Magazine*, July-August 1972.
15. F. E. Hamren, "Liquid Natural Gas Ships--A New Construction Approach," *Maritime Reporter and Engineering News*, February 1, 1973.
16. Personal Communication with C. R. McKenney, E. I. du Pont de Nemours and Company, April 1973.

ADDITIONAL SOURCES OF INFORMATION

1. Altenburg, C. J. and R. J. Scott, *Design Considerations for Aluminum Hull Structures*, Gibbs and Cox Ship Structure Committee Report 218, USCG, 1971.
2. "American Shipbuilders Turn to Automated Welding to Compete," *Welding Engineer*, April 1969.
3. Cantrell, D., *Bonding Metal-to-Metal Riveted Structure With Room Temperature Curing Adhesive*, D6-7132, Boeing Commercial Airplane Company, September 1961.
4. Cline, C. L., "An Analytical and Experimental Study of Diffusion Bonding," *Welding Journal Supplement*, November 1966.
5. DeLollis, N. J., "Adhesives for Metals--Theory and Technology," *Industrial Press*, 1970.
6. *Establishment of Parameters and Limitation of Explosive Welding*, Pratt & Whitney Aircraft Report PWA-FR-1528, August 27, 1965.
7. "Friction Welding: Versatile Joiner of Dissimilar Metals," *Welding Engineer*, December 1970.
8. Gatsek, Leo F., *Bonding and Welding of Dissimilar Metals*, NASA Publication SP-5018.
9. Hawkins, S., G. H. Levine, and R. Taggart, *A Limited Survey of Ship Structural Damage*, Ship Structure Committee Report 220, USCG, 1971.
10. Holtyn, C. H., "Aluminum--The Age of Ships," Presented to the Society of Naval Architects and Marine Engineers, New York, November 10, 1966.
11. Holtyn, C. H., *Shipbuilding Guide to Aluminum Construction*, Reynolds Metals Company, 1963.
12. Lowenberg, A. L., and P. D. Watson, *Recommended Emergency Welding Procedure for Temporary Repair of Ship Steels*, Ship Structure Committee Report 195, May 1969.
13. *Machine Design Magazine*, Fastener reference issue, 1972.
14. Roderick, Robert L., *American Machinist Magazine*, McGraw-Hill, December 28, 1970.
15. Scott, R. J., and J. H. Somella, *Feasibility Study of Glass-Reinforced Plastic Cargo Ship*, Gibbs and Cox Ship Structure Committee Report 224, USCG, 1971.
16. Turner, M. J., "Manual Vs. Machine Welding in Shipbuilding," *Welding Engineer*, August 1972.

ACKNOWLEDGEMENTS

Appreciation is expressed to the following for their assistance:

- o Lockheed Shipbuilding & Construction Company, Seattle, Washington
- o Tacoma Boat Building Company, Tacoma, Washington
- o Aerojet General, Surface Effects Ships Division, Tacoma, Washington
- o Commanding Officer, USS Bridget (DE-1024), Pier 91, Seattle, Washington
- o E. I. du Pont de Nemours & Company, Metal Classing Division, Wilmington, Delaware
- o Naval Ship Research and Development Center, Annapolis, Maryland
- o Bath Iron Works, Bath, Maine
- o Newport News Shipbuilding and Dry Dock Company, Newport News, Virginia
- o Boeing Aerospace Company, Naval Systems Division, Seattle, Washington
- o Northwest Technical Industries, Inc., Port Angeles, Washington
- o Nickum & Spaulding Associates, Inc., Seattle, Washington

Unclassified

Security Classification

DOCUMENT CONTROL DATA - R & D		
<i>(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)</i>		
1. ORIGINATING ACTIVITY (Corporate author) Boeing Commercial Airplane Company P. O. Box 3707 Seattle, Washington 98124		2a. REPORT SECURITY CLASSIFICATION Unclassified
		2b. GROUP
3. REPORT TITLE A SURVEY OF FASTENING TECHNIQUES FOR SHIPBUILDING		
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Final Technical Report		
5. AUTHOR(S) (First name, middle initial, last name) Nobuo Yutani Thomas L. Reynolds		
6. REPORT DATE September, 1973	7a. TOTAL NO OF PAGES 135	7b. NO OF REFS 16
8a. CONTRACT OR GRANT NO N00024-73-C-5077	9a. ORIGINATOR'S REPORT NUMBER(S) D6-26283-1	
b. PROJECT NO SR-207	9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) SSC-260	
10. DISTRIBUTION STATEMENT Distribution of this document is unlimited.		
11. SUPPLEMENTARY NOTES	12. SPONSORING MILITARY ACTIVITY Naval Sea Systems Command	
13. ABSTRACT This report is aimed at defining fastening processes and techniques that are not widely used in ship construction today in terms of their applicability and potential for improving cost, construction, reliability, and maintenance of hull structures and attachments. The study includes similar and dissimilar metal-to-metal and metal-to-nonmetal joints, a generic fastener matrix of typical fasteners, fastener installation equipment and processes, proposed applications of explosion-bonded materials, and cost comparisons of various fabrication techniques. Fusion welding, diffusion bonding, friction welding, and adhesive bonding are discussed. Several fastener standards and vendor proprietary fasteners are included as figures. Extractions from Boeing Design Manual sections on mechanical fastening and adhesive bonding are included as reference attachments. Fastening systems and techniques that merit further study or verification are identified.		

DD FORM 1 NOV 66 1473

Unclassified

Security Classification

Unclassified

Security Classification

14	KEY WORDS	LINK A		LINK B		LINK C	
		ROLE	WT	ROLE	WT	ROLE	WT
	Final technical report Fastening techniques Deckhouse attachments Systems installation Outfitting Explosive bonding Fasteners Adhesive bonding Bonding techniques Structural fasteners Bimetallics Trimetallics Watertight compartment penetrations Riveting Bulkhead penetrations Electromagnetic riveting Hole preparation Drilling Transition joints						

Unclassified

Security Classification